



JRC SCIENCE FOR POLICY REPORT

Techno-economic and environmental assessment of construction and demolition waste management in the European Union

Cristóbal, J., Caro, D., Foster, G., Pristerà, G.
Gallo, F., Tonini, D.

2023



This publication is a Science for Policy report by the Joint Research Centre (JRC), the European Commission's science and knowledge service. It aims to provide evidence-based scientific support to the European policymaking process. The contents of this publication do not necessarily reflect the position or opinion of the European Commission. Neither the European Commission nor any person acting on behalf of the Commission is responsible for the use that might be made of this publication. For information on the methodology and quality underlying the data used in this publication for which the source is neither Eurostat nor other Commission services, users should contact the referenced source. The designations employed and the presentation of material on the maps do not imply the expression of any opinion whatsoever on the part of the European Union concerning the legal status of any country, territory, city or area or of its authorities, or concerning the delimitation of its frontiers or boundaries.

Contact information [optional element]

Name:
Address:
Email:
Tel:

EU Science Hub

<https://joint-research-centre.ec.europa.eu>

JRCXXXXXX

EUR XXXX XX

Print ISBN XXX-XX-XX-XXXXX-X ISSN XXXX-XXXX doi:XX.XXXX/XXXXXX XX-XX-XX-XXX-XX-C

PDF ISBN XXX-XX-XX-XXXXX-X ISSN XXXX-XXXX doi:XX.XXXX/XXXXXX XX-XX-XX-XXX-XX-C

Add the following hyperlink to the doi above: <https://doi.org/XXXXXX>

Luxembourg: Publications Office of the European Union, 20XX [if no identifiers, please use Brussels: European Commission, 20XX or Ispra: European Commission, 20XX or Geel: European Commission, 20XX or Karlsruhe: European Commission, 20XX or Petten: European Commission, 20XX or Seville: European Commission, 20XX depending on your unit]

© European Union or European Atomic Energy Community, 20XX [Copyright depends on your directorate, delete as applicable: European Atomic Energy Community for Dir. G, European Union for rest of JRC]



The reuse policy of the European Commission documents is implemented by the Commission Decision 2011/833/EU of 12 December 2011 on the reuse of Commission documents (OJ L 330, 14.12.2011, p. 39). Unless otherwise noted, the reuse of this document is authorised under the Creative Commons Attribution 4.0 International (CC BY 4.0) licence (<https://creativecommons.org/licenses/by/4.0/>). This means that reuse is allowed provided appropriate credit is given and any changes are indicated.

For any use or reproduction of photos or other material that is not owned by the European Union or European Atomic Energy Community, (delete as applicable) permission must be sought directly from the copyright holders. The European Union or European Atomic Energy Community (delete as applicable) does not own the copyright in relation to the following elements:

- Cover page illustration, © Miguel Montero Alonso
- [page XX, element concerned], source: [e.g. Fotolia.com]

[When indicating the inclusion of third party elements, please check if the licensor makes any recommendation on a specific way to attribute.]

How to cite this report: Author(s), *Title*, Editors, Publisher, Publisher City, Year of Publication, doi:XX.XX/XXXXX (where available), JRCXXXXXX. [Always use the PDF/online doi in the citation, even for the print version of the publication.]

Printed by [Xxx] in [Country] [This will not be present in the ONLINE version.]

1. Introduction and policy background.....	7
1.1 Objectives of the study.....	8
2. CDW characterisation: generation and composition.....	10
2.1 Relevant material fractions for CDW in the European Waste Code (EWC).....	10
2.2 CDW characterisation based on a literature review of reported data.....	11
2.3 Theoretical material fraction generation potential via MFA modelling.....	15
2.4 Focus on infrastructure waste.....	19
2.4.1 Management practices for infrastructure waste.....	22
3. Technologies and processes for CDW management.....	24
3.1 Established and prospective recycling and preparing for reuse processes.....	28
3.1.1 Concrete.....	28
3.1.2 Wood.....	29
3.1.3 Metals: steel and aluminium.....	29
3.1.4 Polyvinylchloride (PVC).....	30
3.1.5 Expanded polystyrene (EPS).....	30
3.1.6 Gypsum.....	31
3.1.7 Bricks.....	31
3.1.8 Ceramics and tiles.....	32
3.1.9 Mineral insulation: glass wool and stone wool.....	32
3.1.10 Glass.....	33
3.1.11 Excavated soil.....	34
3.1.12 Dredging spoils.....	35
4. CDW management in the EU27.....	37
4.1 Mineral fraction.....	37
4.2 Metals, plastic, wood and glass.....	40
4.3 Soil waste.....	41
4.4 Dredging spoils.....	41
4.5 Overview of current CDW management pathways and recovery rates in EU27.....	42
5. Assessment of environmental and economic impacts of CDW management.....	45
5.1 Material and Methods.....	45
5.1.1 Goal, scope and functional unit.....	45
5.1.2 System boundaries.....	45
5.1.3 Impact categories.....	46
5.1.4 Scenario definition.....	46
5.1.5 Inventory.....	50
5.1.6 Uncertainty propagation analysis.....	50
5.1.7 Sensitivity analyses.....	50
5.2 Assessment results.....	51
5.2.1 Life cycle assessment results.....	51

5.2.2	Environmental life cycle cost results.....	53
5.2.3	Sensitivity analysis results.....	55
6.	Potential for preparing for reuse and recycling in the EU27.....	57
6.1	Potential for recycling.....	57
6.2	Potential for preparing for reuse.....	57
6.3	GHG savings and costs in increased recycling and preparing for-reuse scenarios.....	62
7.	Economic and non-economic market barriers.....	67
8.	Limitations of the study and further research.....	69
8.1	Limitations related to the quantification of CDW generation and treatment.....	69
8.2	Limitations related to excavated soils and dredging spoils.....	69
8.3	Limitations related to the environmental and economic assessment.....	70
9.	Stakeholder Consultation.....	71
9.1	Dialogue on the techno-economic and environmental assessment report and workshop with stakeholders.....	71
9.2	Stakeholder Survey Results.....	71
9.3	Stakeholder impact on final report.....	73
10.	Conclusions.....	74
	References.....	76
	List of abbreviations and definitions.....	85
	List of boxes.....	87
	List of figures.....	88
	List of tables.....	89
	Annexes.....	90
Annex 1.	Remaining impact categories results.....	90
Annex 2.	Sensitivity results for wood fraction including the cascading use and greener energy use.....	97

Abstract

Construction and demolition waste (CDW) accounts for more than one third of all waste generated in the EU. The European Commission is taking important legislative and non-legislative steps to ensure CDW is managed in an environmentally sound manner and contributes to the circular economy. This report reviews, analyses and reconciles data on CDW generation, composition and management at EU27 level. It also performs an environmental and techno-economic assessment of the most important management technologies through life cycle assessment and environmental life cycle costing, to provide data for further feasibility assessments of preparation for reuse and recycling objectives for individual material fractions. Results show that, provided uptake of best available technologies, recycling and preparation for reuse are preferred over incineration and landfilling for most of the individual material fractions of CDW because of the associated environmental benefits. However, such shift comes with increased financial costs for most materials, except for soils and dredging spoils, for which uncertainties are however significant. The study further estimates the potential for recycling and preparation for reuse for each individual material fraction of CDW, indicating that 83% of CDW can potentially be sent to preparing for re-use and recycling (of which potentially 16% to preparing for re-use). This would lead to additional 33 Mt CO₂ eq. savings annually at a net cost of 6.7 billion EUR when assuming recycling only.

CONFIDENTIAL – WORK IN PROGRESS

Acknowledgements

The authors would like to acknowledge all the organisations that participated in the stakeholder consultation for having contributed to the study with valuable inputs and feedback.

Authors

Cristóbal García, Jorge¹

Caro, Dario²

Foster, Gillian²

Pristerà, Giulia¹

Gallo, Federico¹

Tonini, Davide²

¹ European Commission, Joint Research Centre, Directorate D – Sustainable Resources, Land Resources and Supply Chain Assessments unit (D3)

² European Commission, Joint Research Centre, Directorate B – Growth and Innovation, Circular Economy and Sustainable Industry unit (B5)

CONFIDENTIAL – WORK IN PROGRESS

Executive summary

The objective of this study is to provide techno-economic and environmental assessment of CDW management in the EU27, focusing on individual material fractions and including soil that is usually excluded from the scope of most analyses. The report: i) provides a detailed review of the data available on CDW generation, composition and treatment at EU level; ii) provides an overview of CDW management technologies and processes for the different material fractions to identify key technologies and compile inventory data; iii) provides the environmental impacts and costs of managing individual material fractions of CDW via different technologies and processes; and iv) explores future scenarios reflecting improved CDW management at EU27 level. Finally, the economic and non-economic barriers are discussed as well as the limitations of the study and the feedback (survey results) from the stakeholders.

Policy context

The Waste Framework Directive (WFD; Directive 2008/98/EC; European Commission, 2008), later amended in 2018 (European Commission, 2018a) regulates the management of CDW in the EU. In Article 11(2)(b) of Directive 2008/98/EC it is highlighted that by 2020 the preparing for reuse, recycling and other material recovery, including backfilling operations using waste to substitute other materials, shall be increased to a minimum of 70% by weight. For CDW, the current average recovery rate in the EU is about 89%, which is higher than the 70% by weight goal. However, it should be noted that current recovery mainly produces low-quality recycled aggregates for use as backfilling material or road construction sub-basis in the best-case scenario. Despite the potential high market value of some CDW fractions such as bricks, ceramics, wood and PVC, they are typically not reused or recycled for the same application or function for which they originally were produced. Rather, they are mostly recovered to become aggregates or incinerated or landfilled. For this reason, the European Commission has accompanied the revised WFD with guidance documents, for example, the 'EU Construction and Demolition Waste Management Protocol' (European Commission, 2016; non-binding guidelines on how to properly treat CDW), 'Guidelines for audits before demolition of building' (European Commission, 2018b); and 'Circular Economy – Principles for Building Design' (European Commission, 2020a). More recently, the Commission has signalled that it is considering a revision of EU waste legislation, focusing on preparing for reuse and recycling objectives for CDW and its material-specific fractions (Article 11(6) of the WFD). In brief, the European Commission is motivated to promote circular economy approaches in the construction industry ecosystem, and a revision of EU waste legislation provides an opportunity to improve the sustainability performance of construction and demolition sector. Sustainable and circular use of excavated soil from construction and demolition waste, which is in line with the EU soil strategy for 2030 (European Commission, 2021a), is also an objective.

Main findings

Using Life Cycle Assessment and Environmental life cycle Costing we find that advanced material-specific reuse and recycling processes create significantly higher GHG savings and better environmental performances than incineration and landfill, and are also better than recycling processes only producing recycled aggregates for road construction or backfilling. This is true for almost all material fractions, except in a few cases that are duly explained in this document.

We find that at EU27 level, the **preparing for re-use and recycling rate potential could be in the range of 27%-100%** across the individual material fractions of CDW investigated, **averaging 83% for the whole CDW** (these values should be interpreted as the proportion of waste generated that can be 'sent for preparing for re-use and recycling'). Notice that this figure is calculated excluding the mixed inert waste fraction (ca. 14% of total CDW) and soil and dredging spoils (excluded from the recovery rate target of the EU Waste Framework Directive). When defining the recovery of the mixed interaction as recycling in the equation, the total recycling rate of CDW would rise to as much as 97%¹. As for the **potential for preparing for re-use alone**, we estimated that this could vary between **0-50%** depending on the material fraction, **averaging 16% for the CDW in total** (to be interpreted as 'sent for preparing re-use'; 14% when considering preparing for re-use

¹ Our estimate of 83% is thus not directly comparable with the current EU27 recovery rate of CDW of 79%, as estimated by Eurostat because the latter includes mixed inert waste (which we did not include in the calculation leading to 83%). If a comparison should be made, the value of 97% should be used instead (assuming that all mixed inert waste fraction can be recycled as recycled aggregates).

losses). These values should be considered as preliminary estimates, based on existing literature and specific case studies, especially for the case of preparing for re-use.

Based on these figures, two scenarios are developed and analysed, first a scenario for a maximum recycling rate and second a maximum preparation for re-use and recycling rate. The first scenario is done by reducing landfilling and incineration to the minimum and assuming implementation of the best performing recycling processes following a best available methods approach; although, the re-use rate is kept at the same levels as today. The second scenario follows the same exact assumptions as the first but prioritises preparing for re-use whenever applicable and to the maximum extent technically possible. The results of the assessment show that, compared to the baseline (*status quo* management of CDW in the EU27; and using 2020 waste generation figures) and excluding soil and dredging spoils, a total annual reduction of ca. 33 Mt CO₂ eq. at a net cost of approximately 6.7 billion EUR would be achieved with the maximum recycling potential scenario and a total reduction of ca. 48 Mt CO₂ eq. with a net cost saving of approximately 6.8 billion EUR would be achieved with the maximum preparation for re-use and recycling scenario. The cost savings due to a maximum of reuse scenario are due to the theoretical savings gained by reusing in place of processing the waste via incineration, landfilling and recycling (as it is the case in the baseline year 2020) and should be considered as a theoretical tendency rather than an accurate cost estimate. Remarkably, using a Marginal Cost Abatement Curve, the study shows that all material fractions contained in CDW truly have non-negligible potential contributions to GHG reductions and environmental savings at below the current CO₂ price, except for wood and concrete waste.

Key conclusions

Current recycling and/or recovery of CDW is mainly based on production of recycled aggregates mostly for use as road basis or backfilling. Yet, more advanced processes and technologies exist that can increase the value of the products recovered and the environmental performance of the recycling itself. These span from re-use of selected material fractions (e.g. bricks, aluminium, steel, and wood) to advanced processes that recover cement and high-value recycled aggregates for structural uses from concrete waste. While such processes and technologies are available or may be available in the short-term, they are generally more costly than landfilling and incineration. The costs are higher, even when an average landfill tax on inert waste disposal is included. The reason is the increased financial costs for processing and selective demolition. However, when accounting for external costs (monetised environmental emissions), recycling pathways bring overall societal savings. From a purely financial perspective, significantly higher landfill taxes (above the levels in the current study (19 EUR t⁻¹), as applied in selected member states (up or more than 100 EUR t⁻¹, e.g., in the Netherlands), have proven to discourage disposal and favour recycling or recovery operations. Still, this does not ensure that recovery is steered towards high-quality material recycling for use in high-value markets and applications. To this aim, other complementary measures and/or instruments may be necessary. The findings of this study indicate that significant environmental benefits can be obtained from improved re-use and recycling of individual material fractions of CDW. We show that not only concrete, but basically all waste material fractions truly have a relevant contribution to GHGs and environmental savings when recovered rather than wasted.

Related and future JRC work

The information contained in this report is supported and complemented by the analyses presented in the following additional studies: Damgaard et al. (2022), Caro et al. (2023), Cristóbal et al. (forthcoming), and Pristerà et al. (forthcoming). Also, JRC plans to perform a subsequent study to identify policy measures to improve CDW management.

Quick guide

This report is organized in ten sections as follows. Section 1 presents the introduction and the policy background of the report and the objectives of the study. Section 2 is focused on the CDW characterisation including the quantification and the composition of the different fractions at EU level. It includes a theoretical material fraction generation potential estimated via MFA, which is estimated without the mixed fraction. Section 3 summarises the main technologies used to manage the individual material fractions of CDW. Section 4 details the management of each individual CDW material fraction, including a final summary of the current management pathways in the EU. Section 5 introduces the methodology and results of a life cycle assessment and environmental life cycle costing performed for the different waste management options of the different CDW fractions. Section 6 assess two scenarios to unravel the potential benefits of increasing the recycling and preparing for reuse of the different CDW fractions. Section 7 analyses the economic and non-economic market barriers for CDW. Sections 8 and 9 presents the limitations of the study and the stakeholder consultation results, respectively. Finally, section 10 derives the conclusions of the study.

1. Introduction and policy background

All waste generation has social, economic, and environmental impacts associated with it, as well as a loss of valuable materials and resources within the economy. Construction and demolition waste (CDW) accounts for more than one third of all waste generated in the EU. This fact makes CDW an important target for the EU to ensure its management in an environmentally sound way and to ensure it contributes to the circular economy. Thus, in the last two decades, the European Commission has taken clear steps towards the efficient use of resources, including waste prevention, mainly through different communications, legislation (including Directives to be transposed at national level), and guidelines.

Management of CDW in the EU is regulated by the EU Waste Framework Directive (WFD; Directive 2008/98/EC; European Commission, 2008), later amended in 2018 (European Commission, 2018a). The target set in Article 11(2)(b) of Directive 2008/98/EC reads: “by 2020, the preparing for reuse, recycling and other material recovery, including backfilling operations using waste to substitute other materials, of non-hazardous construction and demolition waste excluding naturally occurring material defined in category 17 05 04 in the list of waste shall be increased to a minimum of 70% by weight.” The main changes in the management/reporting of CDW introduced by the amended WFD as of 2018 consists of: i) a revised definition of backfilling, to further clarify the distinction between backfilling and other recovery operations, notably recycling, and ii) an increased frequency of reporting to the Commission via Eurostat (2-year instead of 3-year).

As for the **revised definition of backfilling**, the amended WFD reads “backfilling means any recovery operation where suitable non-hazardous waste is used for purposes of reclamation in excavated areas or for engineering purposes in landscaping. Waste used for backfilling must substitute non-waste materials, be suitable for the aforementioned purposes, and be limited to the amount strictly necessary to achieve those purposes”. This is stricter than the earlier definition in Commission implementing decision 2011/753/EU (European Commission, 2011), which reads “backfilling means a recovery operation where suitable waste is used for reclamation purposes in excavated areas or for engineering purposes in landscaping and where the waste is a substitute for non-waste materials”.

The rules for the **frequency and calculating the recovery rate**² and related reporting to the Commission via Eurostat are detailed in the EC implementing decision 2011/753/EU, later amended in the EC implementing decision 2019/1004/EU (European Commission, 2019). Eurostat’s guidance document for reporting of CDW recovery according to the abovementioned rules is available to Member States, and it is regularly updated (European Commission, 2022a). CDW reporting has a frequency of 2-years, and must follow the format detailed in 2019/1004/EU (European Commission, 2019) and must include the data collected within one-calendar-year. As for the measurement point, for reporting the amount of CDW material recovered (the numerator of the recovery rate), Art. 2(2) of Commission Decision 2011/753/EU sets out that “the weight of the waste prepared for reuse, recycled or materially recovered shall be determined by calculating the input waste used in the preparation for a final recycling or other final material recovery processes. A preparatory operation prior to the submission of the waste to a recovery or disposal operation is not a final recycling or other final material recovery operation. Where waste is collected separately or the output of a sorting plant is sent to recycling or other material recovery processes without significant losses, that waste may be considered the weight of the waste, which is prepared for re-use has undergone other material recovery.” In other words, the amount of CDW reported as recovered reflects the amount of waste that enters the final material recovery process. As for the generated CDW (the denominator of the recovery rate), Member States have two options to calculate and report it, i.e., a general method provided by Eurostat in the guidance document (European Commission, 2022a) or their own national data, if deemed to be more accurate.

The current recovery rate of the EU for the year 2020 varies from 63% (Finland) to 99% (Luxembourg) with an average of 89% for the EU³. As illustrated later in this document, such recovery often reflects recovery pathways that mainly produce low-quality recycled aggregates (RA) from the mineral fraction of CDW for use as backfilling material or road construction sub-basis in the best-case scenario. For example, a relatively low share of such RA is currently used for structural concrete applications (8.2%) (Pacheco et al., 2023), while cement (a carbon-intensive material) is not recovered at all. Other material fractions of potentially high market value such

² The recovery rate for CDW and the calculation methods are defined in Annex III of 2011/753/EC and is equal to ‘CDW material recovered divided by CDW material generated’. The recovery includes preparing for reuse, recycling and other material recovery operations including backfilling operations.

³ These figures may be found in the Eurostat website under the Circular Economy Indicators (CEI WM_040) and are also reported in section 4 of this document.

as bricks, ceramics, wood and PVC are typically not reused or recycled for the same application/function for which they originally were produced, but rather recovered as aggregates in the best scenario (e.g., bricks and ceramics) or incinerated or landfilled (PVC and wood). These recovery pathways, notably recycling into aggregates, while certainly diverting the waste from landfills, result in products with low market value and often low quality (process denominated as downcycling), overall incurring low environmental benefits and circularity.

To foster better management practices and the circular economy in the construction and demolition sector, the European Commission has accompanied the revised WFD with guidance documents such as the 'EU Construction and Demolition Waste Management Protocol' (European Commission, 2016; non-binding guidelines on how to properly handle this waste stream), 'Guidelines for audits before demolition of building' (European Commission, 2018b) and 'Circular Economy – Principles for Building Design' (European Commission, 2020a). More recently, in the context of the construction and buildings key value chain under the **Circular Economy Action Plan** (European Commission, 2020b), the Commission has pointed out that:

- it would and subsequently did adopt a proposal for a revised Construction Product Regulation on 30 March 2022, taking this opportunity to improve the sustainability performance of construction products, introducing recycled content requirements for certain construction products;
- promote circular economy approaches in the construction industry ecosystem (European Commission, 2022b) and the development of digital logbooks for buildings;
- use Level(s), which is the European framework for sustainable buildings, to integrate life cycle assessment in public procurement and the EU sustainable finance framework (the latter was achieved by the adoption of Annex 2 to the Commission Delegated Regulation supplementing Regulation (EU) 2020/852 on the EU Environmental Taxonomy (European Parliament and the Council, 2020));
- consider a revision of EU waste legislation, focusing on preparing for reuse and recycling objectives for construction and demolition waste and its material-specific fractions (Article 11(6) of the WFD);
- promote soil-related initiatives, aiming to increase safe, sustainable, and circular use of excavated soils. This last point is in line with the EU soil strategy for 2030 (European Commission, 2021a) that promotes the waste hierarchy introduced in the WFD and states that excavated soils should be reused in the same or another location (most excavated soils are clean, fertile and healthy), and if not possible they should be prioritised for recycling or some other form of recovery rather than landfilling.

The European Commission has also published a Transition Pathway for Construction (European Commission, 2023c), which aims to offer a bottom-up and co-created understanding of the scale, cost, and conditions for resilience, competitiveness, and the green and digital transition of the construction ecosystem, including actions related to CDW.

1.1 Objectives of the study

The overall aim of this report is to compile data and provide techno-economic and environmental assessment of the CDW management options, focusing on individual material fractions (including the excavated soils that are usually excluded from the scope of most analyses). This report intends to support further policymaking on CDW objectives proposals for preparing for reuse and recycling and its material-specific fractions in accordance with the WFD. The specific objectives of this study are:

- review, analyse and reconcile data on CDW generation, composition and treatment at EU level to be used in subsequent analysis;
- review the literature on CDW management technologies for the different fractions in order to identify key technologies and compile technical data for further modelling;
- establish life cycle inventories for selected CDW management technologies from the reviewed literature;
- conduct a life cycle assessment (LCA) and environmental life cycle costing (ELCC) for the selected CDW management options for the studied CDW fractions;
- explore the maximum potential for improved CDW management at EU level.

Note that this report is supported by the following complementary studies and associated publications:

- Damgaard et al. (2022): providing a detailed review of the data reported across MS for CDW generation and management as well as a material flow analyses of CDW from buildings in the EU for 2020 and 2050.
- Caro et al. (2023): providing a detailed environmental (via LCA) and socio-economic assessment (via ELCC) of CDW management.
- Cristóbal et al. (forthcoming): providing a detailed environmental (via LCA) and socio-economic assessment (via ELCC) of excavated soil and dredging spoil management.
- Pristerà et al. (forthcoming): provided a detailed analysis of selective demolition and design for deconstruction measures as means of achieving a reduction of CDW and a prioritization of preparing for reuse and high-quality recycling options.

CONFIDENTIAL – WORK IN PROGRESS

2. CDW characterisation: generation and composition

2.1 Relevant material fractions for CDW in the European Waste Code (EWC)

CDW is composed of different waste fractions and materials that are registered under specific codes according to the two main coding systems applied within the EU: the List of Waste (LoW) and the EWC-Stat. The former is the waste classification in the EU for administrative purposes and is structured in 20 chapters, mainly according to the source of waste (i.e., the economic sector or process of origin). The latter is a substance-oriented aggregation of the waste types defined in the LoW. It is possible to unambiguously convert the waste types classified according to the LoW into the EWC-Stat waste categories that is the main method reported in the Commission Decision 2011/753/EU (European Commission, 2011) setting out the rules and calculation methods for the compliance monitoring (European Commission, 2022a). Table 1 shows the relation of LoW and EWC-Stat codes for the CDW material fractions considered in this report.

Table 1. Description of the CDW fractions considered in this study with a correlation of the LoW and EWC-stat codes.

CDW fractions	Considered in scope	LoW code	EWC-stat
Mineral waste	Mineral waste	17 01	W12.1
Concrete	Concrete	17 01 01	W12.11
Bricks	Bricks	17 01 02	W12.11
Tiles and ceramic	Tiles and ceramic	17 01 03	W12.11
Other materials from road demolition	EXCLUDED		
Mixed/other mineral/inert waste	Mixed/other mineral/inert waste	17 01 07	W12.11
Asphalt waste	Bituminous mixtures containing coal tar	17 03 02 ⁽¹⁾	W12.12
Plastic	Plastic	17 02 03 / 19 12 04 ⁽²⁾	W07.42
Metal	Metal	17 04	W06
Mixed metals, incl. cables	Mixed metals	17 04 07, 17 04 11	W06.32, W06.26
Ferrous	Ferrous	17 04 05 / 19 12 02	W06.11
Non-ferrous	Non-ferrous	17 04 01, 17 04 02, 17 04 03, 17 04 04, 17 04 06 / 19 12 03	W06.24, W06.23, W06.25, W06.26
Glass	Glass	17 02 02 / 19 12 05	W07.12
Wood	Wood	17 02 01 / 19 12 07	W07.53
Gypsum	Gypsum	17 08 02	W12.11
Insulation	Insulation	17 06 04	W12.13
Paper and cardboard	Paper and cardboard	NA ⁽³⁾ 19 12 01	W07.23

Mixed waste, generic	Mixed waste, generic	17 09 04 / 19 12 09	W12.13 / W12.81
Mix of non-hazardous, non-inert wastes			
Mix of inert and non-hazardous, non-inert wastes			
Others			
Soil	Soils		
Unpolluted	Soils and stones	17 05 04	W12.61
Polluted	Soils and stones containing dangerous substances	17 05 03*	W12.61
Dredging spoil	Dredging spoils		
Unpolluted	Dredging spoils	17 05 06	W12.71
Polluted	Dredging spoils containing dangerous substances	17 05 05*	W12.71
Track ballast	Track ballast		
Unpolluted	Track ballast	17 05 08	W12.11
Polluted	Track ballast containing dangerous substances	17 05 07*	W12.11
Hazardous waste (excl. hazardous soil, dredging spoil, track ballast)	Hazardous waste (excluding hazardous soil and dredging spoil)	17 01 06*, 17 02 04*, 17 03 01*, 17 03 03*, 17 04 09*, 17 04 10*, 17 06 01*, 17 06 03*, 17 06 05*, 17 08 01*, 17 09 01*, 17 09 02*, 17 09 03*	W12.11, W12.12, W10.22, W12.13, W12.21, W07.73

(1) In green, the codes that were excluded in Damgaard et al. (2022) but included in this study.

(2) In red, the LoW entries that according to the Commission Decision 2011/753/EC (Annex III) shall also be included in the calculation of CDW recovery targets but that in this study have not been considered since it was not possible to know whether they were generated from the treatment of waste coming from construction and demolition activities.

(3) There is no LoW code for Paper and Cardboard within the Construction and demolition waste category (Chapter 17) of the European Waste Catalogue (EWC, Commission Decision 2014/955/EC).

Note: Any waste marked with an asterisk (*) in the list of waste shall be considered as hazardous waste. It is important to highlight that reporting obligations are only for non-hazardous wastes excluding soils and dredging spoils (i.e., naturally occurring materials).

Source: Adapted from Damgaard et al. (2022).

2.2 CDW characterisation based on a literature review of reported data

According to the literature review by Damgaard et al. (2022), which includes more than 90 reports and articles (comprising Eurostat sources, techno-scientific literature, and country-specific data obtained via stakeholders and environment agencies), the generation of CDW in the EU27 in 2018 amounted to ca. 848 Mt when including soil, track ballast, dredging spoils, and asphalt (Table 2). When excluding soil, track ballast, dredging spoils, and asphalt the quantity of CDW generated amounted to ca. 276 Mt. The authors provide a detailed breakdown of the CDW material fraction composition at EU27 level (Table 3) as well as at Member State level (for these, the reader is referred to the original document by Damgaard et al., 2022).

The main messages from the literature review are:

- A high variation in the amount of reported CDW generation exists across Member States, from 0.02 t/capita in Bulgaria to 3.72 t/capita in Malta (excluding soil, track ballast, dredging spoils and asphalt).
- The largest material fraction on average in CDW, when excluding excavated soil waste, is the mineral fraction (77%). It consists mainly of concrete and bricks, followed by metal (4.3%), wood (2.3%), and gypsum (1.4%). However, great variation exists across Member States, notably for wood (reaching 18-21% in Sweden and Finland).
- A high variation in the amount of reported soil waste generation exists across Member States, from almost zero in Malta to significant amounts in Finland and Luxembourg, where soil waste is the largest fraction of CDW. This is likely related to the way soil from excavation is classified at Member State level (by-product versus waste) and thus reported.
- The level of detail reported for the material fraction composition varies greatly across Member States. For some countries (e.g., Denmark, Germany, Luxembourg, Netherlands), data are available for almost all material fractions, including a breakdown into the different components of the mineral fraction (concrete, bricks, tiles and ceramic), which might indicate a good level of source separation. Other countries, e.g., Belgium, Bulgaria, Cyprus and Finland, only report mineral waste data in aggregated form, possibly reflecting poor practices within source segregation and selective demolition. In addition, these countries also report data for plastic, metal, glass, wood and hazardous waste. This further supports the argument that the reported CDW data do not necessarily represent the actual material composition, but rather reflect CDW management practices.
- Many Member States report a high share of 'mixed CDW' fraction. This fraction ranges from 5% (Germany) to 100% (Poland), possibly suggesting poor practices within source segregation and selective demolition. Notice that data for the "mixed CDW" fraction are not available in Eurostat datasets as Eurostat does not include it.
- The data for insulation are likely to refer only to mineral insulation as polymer-based insulating material would be likely sorted and classified as plastic waste. However, this remains unclear in the reporting.
- CDW data for Italy were adjusted, as the categorisation of the main Italian CDW fraction as LoW code 17 09 04 (indicating a mix of waste from construction and demolition) was understood as a misclassification; as this main fraction is, to a large extent, used to produce RA. A more accurate classification that better reflects the actual material composition of Italian CDW was suggested to be LoW code 17 01 07. The revised CDW composition for Italy is used for further assessment.

Table 2. Current CDW generation in 29 European countries, as well as total CDW generation for all 27 Member States (EU27) and for EU27 + Norway. CDW data are presented as both incl. and excl. soil, track ballast, dredging spoils and asphalt, with a detailed focus on soil waste generation.

	Total CDW generation <u>incl.</u> soil, track ballast, dredging spoils and asphalt [t]	Total CDW generation <u>excl.</u> soil, track ballast, dredging spoils and asphalt [t]	Total soil waste generation [t]	Per capita CDW generation <u>excl.</u> soil, track ballast, dredging spoils and asphalt [t/capita]	Per capita CDW generation <u>excl.</u> asphalt, <u>incl.</u> soil [t/capita]	Per capita soil waste generation [t/capita]
Austria	48 961 689	11 521 240	37 440 449	1.29	5.50	4.21
Belgium	26 791 280	22 960 461	2 973 938	1.99	2.25	0.26
Bulgaria	384 408	161 090	74 535	0.02	0.03	0.01

Croatia	1 239 094	646 163	582 492	0.16	0.30	0.14
Cyprus	1 048 713	333 468	715 245	0.38	1.18	0.81
Czechia	14 422 791	4 262 791	9 442 000	0.40	1.28	0.88
Denmark	14 162 000	3 818 000	9 139 000	0.66	2.23	1.57
Estonia	2 917 272	1 260 097	1 599 472	0.95	2.15	1.20
Finland	23 676 196	1 871 918	21 789 333	0.34	4.28	3.94
France	252 951 500	53 151 500	175 110 000	0.79	3.39	2.60
Germany	201 345 300	72 215 800	108 582 300	0.87	2.17	1.31
Greece	3 244 848	1 440 182	1 730 862	0.13	0.30	0.16
Hungary	7 399 179	3 520 557	3 808 105	0.36	0.75	0.39
Ireland	2 857 434	733 745	2 123 689	0.15	0.58	0.43
Italy	56 681 821	43 045 079	13 600 000	0.72	0.95	0.23
Latvia	390 530	385 959	4 571	0.20	0.20	0
Lithuania	934 554	890 240	44 297	0.32	0.33	0.02
Luxembourg	5 121 118	432 067	4 481 481	0.69	7.85	7.16
Malta	1 975 105	1 915 040	65	3.72	3.72	0
Netherlands	101 562 751	24 317 000	7 766 598	1.40	1.84	0.45
Poland	15 322 360	4 523 831	10 071 815	0.12	0.38	0.27
Portugal	2 035 326	1 696 938	338 234	0.16	0.20	0.03
Romania	1 584 229	965 633	618 596	0.05	0.08	0.03
Slovakia	3 322 470	859 643	1 542 577	0.16	0.44	0.28
Slovenia	4 934 998	1 085 440	3 022 189	0.52	1.96	1.44
Spain	39 539 766	14 807 048	24 729 360	0.31	0.84	0.52
Sweden	12 959 008	3 627 928	8 885 143	0.35	1.21	0.86
Norway	4 650 868	1 750 394	2 702 226	0.33	0.83	0.50
UK	145 116 633	71 788 216	62 009 410	1.07	2.00	0.93
Total EU27	847 765 740	276 448 858	450 216 346	0.78	1.86	1.08

Total EU27 + Norway	852 416 608	278 199 252	452 918 572	0.76	1.82	1.06
----------------------------	-------------	-------------	-------------	------	------	------

Source: Damgaard et al. (2022).

Table 3. Current average CDW composition (expressed as % of the total per capita CDW amounts) for EU27 and EU27+Norway. Data are presented both excluding and including soil, track ballast, dredging spoils, and asphalt.

CDW	Total CDW generation excl. soil, track ballast, dredging spoils and asphalt		Total CDW generation incl. soil, track ballast, dredging spoils and asphalt	
	EU27	EU27+Norway	EU27	EU27+Norway
Mineral waste	77.0%	76.6%	27.5%	27.4%
Concrete	24.0%	23.9%	8.6%	8.5%
Bricks	5.0%	4.9%	1.8%	1.8%
Tiles and ceramics	1.2%	1.2%	0.4%	0.4%
Mixed/other mineral/inert waste	46.9%	46.6%	16.8%	16.7%
Plastic	0.2%	0.2%	0.1%	0.1%
Metal	4.3%	4.3%	1.5%	1.6%
Mixed metals	0.5%	0.5%	0.2%	0.2%
Ferrous	3.4%	3.4%	1.2%	1.2%
Non-ferrous	0.4%	0.4%	0.1%	0.1%
Glass	0.2%	0.2%	0.1%	0.1%
Wood	2.3%	2.5%	0.8%	0.9%
Gypsum	1.4%	1.5%	0.5%	0.5%
Insulation	0.3%	0.3%	0.1%	0.1%
Paper and cardboard	0.2%	0.3%	0.1%	0.1%
Mixed waste, generic	12.3%	12.0%	4.4%	4.3%
Hazardous waste (total, excluding hazardous soil and dredging spoil)	1.8%	2.0%	0.6%	0.7%
Soil (hazardous and non-hazardous)	-	-	54%	54.2%
Dredging spoil (hazardous and non-hazardous)	-	-	9.2%	9.1%
Track ballast and asphalt	-	-	1.0%	1.0%

TOTAL	100%	100%	100%	100%
--------------	------	------	------	------

Source: Adapted from Damgaard et al. (2022).


2.3 Theoretical material fraction generation potential via MFA modelling

The data reported to EU or national authorities (e.g., Table 2), from which the EU27 average is reported in Table 3, is derived and is highly affected by the demolition, separation and management practices applied. This can be easily seen as almost 50% of the material is reported as 'mixed'. To estimate the theoretical potential of each individual material fraction of CDW (i.e., how much is theoretically present in CDW regardless of the demolition and separation/management techniques, and that could potentially be recovered), Damgaard et al. (2022) performed MFA modelling. The MFA modelling was established by dividing the EU in four macro-regions (northern, southern, eastern and western). The material stock and flows in EU in 2020 were calculated for four Member States as representatives of the four regions. Material stock refers to the mass of materials contained in the building stock. The flows refer to both the inflow and outflow of materials from and to the building stock. Inflow describes the materials used for construction and renovation, while outflow refers to waste originating from demolition at end of life and renovation. For this, several input datasets were required. Once the data on the building stock composition in 2020 in EU27 was established, using the stock quantities as a baseline, the flows originating from the building stock were subsequently calculated using construction, demolition and renovation rates. Finally, the stock and flow quantities were multiplied with the material intensities (materials in the different building stocks) that represent the four regions, building types, and construction years. A similar approach was applied for 2050, taking however into account projected increases in renovation waves and in related use of specific materials, such as insulation.

The benefit of using this MFA modelling approach over the reported CDW data is the added detail the modelling can offer regarding the individual material fractions and the origin of materials (building types and building ages). This modelling approach also allows separating and excluding infrastructure waste from building CDW. While modelling assumptions and background data used are thoroughly detailed in Damgaard et al. (2022), the MFAs for year 2020 and 2050 are illustrated in Figure 1 and Figure 2 respectively, and the CDW composition for both points in time in Table 4.


CONFIDENTIAL - WORK IN PROGRESS

Figure 1. MFA showing the origin of building-related material flows from countries, regions, building types and demolition and renovation activities in 2020 in the EU27 (infrastructure waste not included). Notice that the total inflow of material to construction and renovation was estimated to ca. 1 004 000 kt.

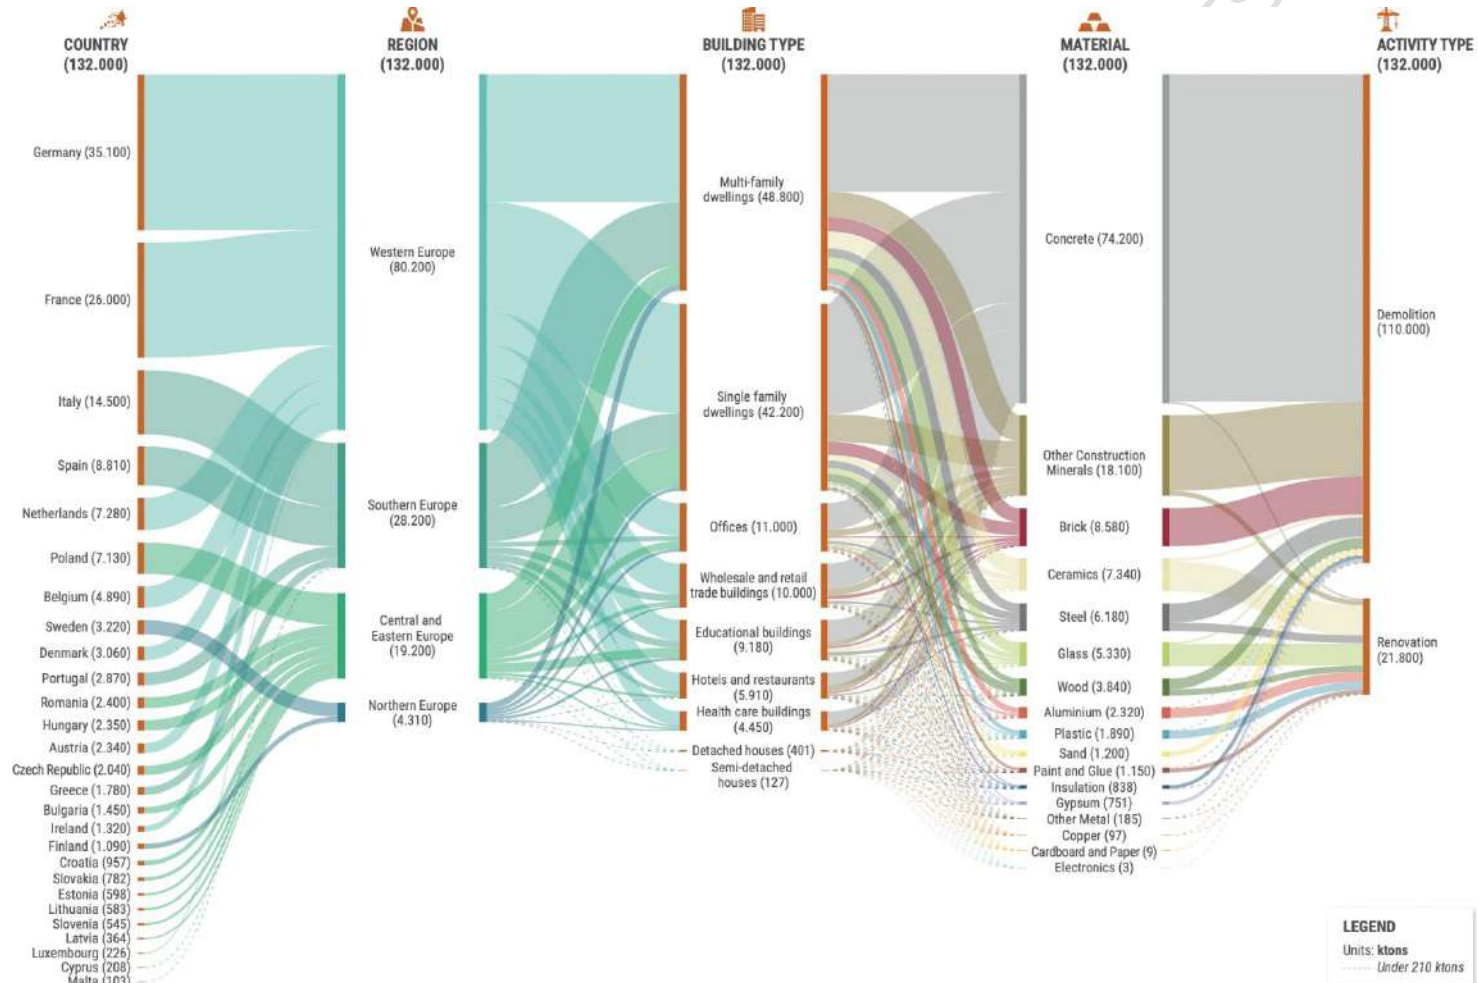

Source: Damgaard et al. (2022)

Figure 2. MFA showing origin of building-related material flows from countries, regions, building types and demolition and renovation activities in 2050 in the EU27 (infrastructure waste not included). Notice that the total inflow of material to construction and renovation was estimated to ca. 1 594 000 kt.

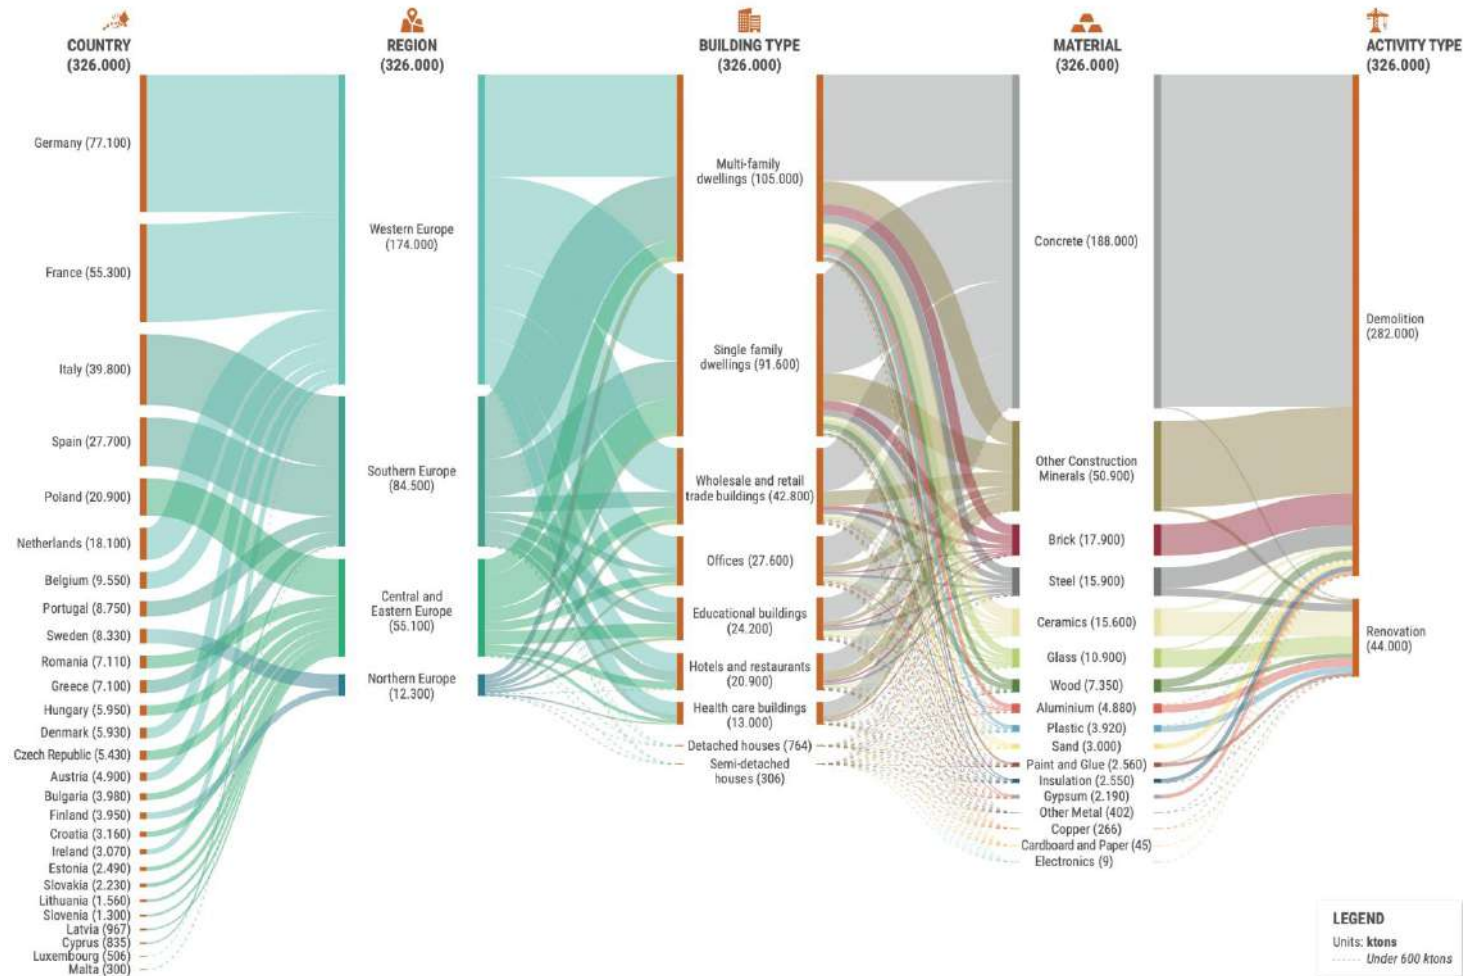

Source: Damgaard et al. (2022)

The main messages from the MFA modelling are:

- In 2020, demolition is responsible for 83% of material flows (ca. 110 Mt), while renovation is responsible for 17% (ca. 22 Mt; (Figure 1). Projecting waste generation to 2050, demolition will be responsible for 83% of material flows (ca. 110 Mt), while renovation for 17% (ca. 22 Mt; Figure 2)
- In 2020, the total outflow from demolition and renovation represents only about 13% of the inflow to construction and renovation (1004 Mt; from Damgaard et al. (2022)). In 2050, the total outflow from demolition and renovation represents about 20% of the inflow to construction and renovation (1 594 Mt; from Damgaard et al. (2022))⁴. From a circular economy perspective, this means that even if all material outflows are prepared for reuse and recycled, only a share of the primary material needed for construction and renovation could be substituted.
- The material composition of demolition and renovation differs significantly. For instance, renovation is responsible for a larger share of the ceramics, glass and insulation material (e.g., replacement of kitchen, bathroom, toilets and energy-related interventions; see Figure 1- Figure 2), whereas demolition is mainly about concrete.
- The material fractions most abundant in the outflow are concrete, other construction minerals, and bricks (Table 4). These materials are mainly used in the foundation and structure of buildings, and typically have a high (embodied carbon) density. From a circular economy (material efficiency) and climate change mitigation perspective, this is an argument in favour of the transformation (reuse) of buildings as opposed to new construction. Building transformation maintains the structural elements of a building, which allows for the retention of 80-90% of the materials on-site, while only substituting the outfitting, finishes and mechanical and electrical installations, which represent a relatively small fraction of the total material mass.
- It is projected that by 2050 concrete and the insulation fraction will increase, while wood, plastic, ceramics and glass will decrease slightly. Since concrete is such a dominant fraction (from a weight perspective), the percentage change in the other fractions is relatively small (Table 4).
- Overall, concrete represents by far the largest material fraction in 2020 and 2050, with 56.2% and 57.6% respectively. Other construction minerals increase from 13.7% to 15.6%, while bricks decrease from 6.5% to 5.5%. Steel remains roughly the same. Wood decreases from ca. 3% to 2.3%, while insulation increases from 0.6% to 0.8% (Table 4).
- Plastics are responsible for 1.4% and 1.2% of the total outflow of CDW in 2020 and 2050, respectively (Table 4).

Table 4. Theoretical CDW composition from building demolition and renovation activities estimated via MFA. Notice that this composition only refers to CDW from buildings and excludes infrastructure waste and soil waste. As such, it cannot be directly compared to the fractional composition reported for CDW as a whole in Table 3.

Material fraction	Year 2020		Year 2050	
	kt	%	kt	%
Aluminium	2 323	1.8%	4 883	1.5%
Brick	8 583	6.5%	17 937	5.5%
Cardboard and Paper	9	0.01%	45	0.01%
Ceramics	7 340	5.6%	15 632	4.8%
Concrete	74 169	56.2%	187 891	57.6%

⁴ Damgaard et al., 2022 (See Figure 22 for 2020 and Figure 27 for 2050 and related additional material).

Copper	97	0.07%	266	0.08%
Electronics	3	0.002%	9	0.003%
Glass	5 328	4.0%	10 895	3.3%
Gypsum	750	0.6%	2 187	0.7%
Insulation ⁽¹⁾	839	0.6%	2 547	0.8%
Other Construction Minerals	18 09	13.7%	50 85	15.6%
Other Metal	184	0.1%	402	0.1%
Paint and Glue	1 148	0.9%	2 562	0.8%
Plastic	1 889	1.4%	3 921	1.2%
Sand	1 195	0.9%	3 004	0.9%
Steel	6 174	4.7%	15 893	4.9%
Wood	3 835	2.9%	7 351	2.3%
Total	131 956	100%	326 275	100%

⁽¹⁾ Insulation materials in the MFA modelling include wall, floor, and roof insulation of various material compositions: inorganic (e.g., glass wool or stone wool), organic (e.g., cellulose insulation) or polymer based (e.g., EPS and PUR).

Source: (Damgaard et al., 2022; elaborated from Table F15 and F20 of the supplementary information provided along with the main report).

2.4 Focus on infrastructure waste

According to Damgaard et al (2022), infrastructure waste is waste from infrastructure activities, i.e., construction, maintenance, renovation and demolition of roads, bridges, tunnels, and other infrastructures. Thus, **infrastructure CDW** includes the different **asphalt waste fractions** (i.e., bituminous mixtures not containing coal tar – LoW code 17 03 02 that mainly consist of aggregates, a binder (such as bitumen⁵ binder) and additives (e.g., rejuvenators, anti-stripping agents). According to Arm et al (2014), the asphalt waste fraction includes three major types of products, i.e., asphalt-based paints (that represent a very small minority of the use of asphalt and are not subject for recycling activities), roofing asphalts and paving asphalts that are a mixture of mineral aggregate, bituminous binder (up to 7%) and filler (Arm et al., 2014).


Along with the asphalt stream, national CDW data from Austria (BIO by Deloitte, 2015a), Germany (BIO by Deloitte, 2015b), and Sweden (BIO by Deloitte, 2015c) confirm **track ballast** as infrastructure waste from the construction/disassembling of railroad tracks. Finally, **concrete** is a CDW stream belonging to both infrastructure and building waste and therefore it is reported as a whole, making it difficult to identify the quantity originating from infrastructure only.

A mini-literature review is herein performed based on the systematic approach proposed by Denyer & Tranfield (2009) to assess the qualitative-quantitative characterisation and management practices as inclusive as possible, and to produce a general picture of the current situation avoiding bias. Specifically, based on literature information in ScienceDirect⁶, we herein refer to 'qualitative characterisation' when there is a correlation between CDW and infrastructure activities, and refer to 'quantitative characterisation' and 'management practice' when information on quantity and end-of-life (EoL) management practices is available, respectively. A synthesis of the method of analysis is provided in Figure 3.

⁵ Bitumen is the product of the non-destructive distillation of crude oil in petroleum refining.

⁶ <https://www.sciencedirect.com>

Figure 3. Materials and methods for the literature review on infrastructure CDW.

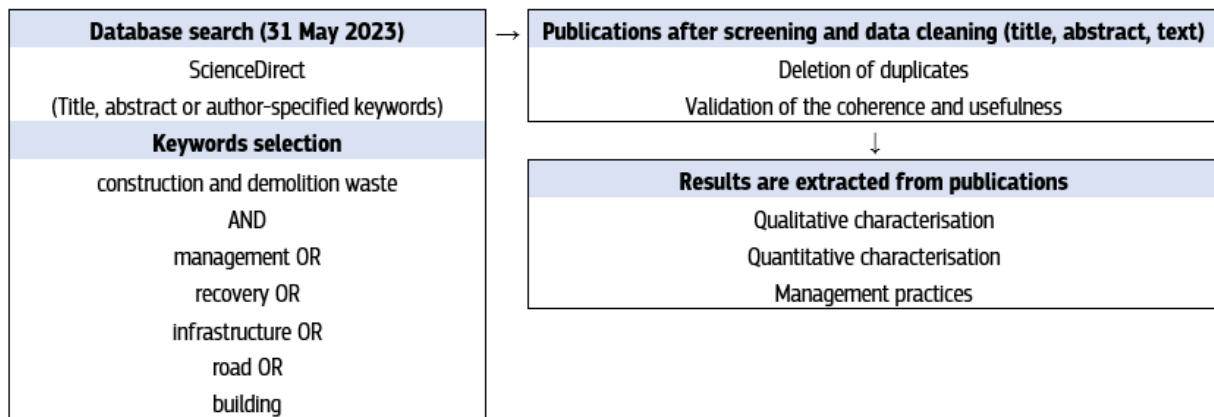

Source: Own elaboration

As shown in Figure 3, the following keywords were entered to conduct the search: “construction and demolition waste”; “management”; “recovery”; “infrastructure”; “road”; “building”. Keywords were inputted on the 31st of May 2023. The choice of keywords is based on the aim of the research, and the results of the bibliographic review are shown in Table 5.

Table 5. Numbers of publications according to the material collection process.

KEYWORD 1	KEYWORD 2	KEYWORD 1+2	
		N° of publications	N° of publications after screening and data cleaning
Construction and demolition waste	Management	325	112
	Recovery	73	
	Infrastructure	54	
	Road	91	
	Building	236	

Source: Own elaboration

Given the base keyword “construction and demolition waste” and each of the five measurement evaluation keywords mentioned above, many publications are detected (column “N° of publications”). From this articles pool, a subset of 112 studies is identified from ScienceDirect database after screening and data cleaning processes in the form of deletion of duplicates and validation of the coherence and usefulness for the purpose of the mini review. At the end of the sorting process 13 relevant papers are characterised in which a correlation between infrastructure waste and concrete, asphalt or track ballast is detected (see Table 6).

Table 6. Qualitative characterisation of the detected publications.

Reference	Qualitative characterisation		
	Concrete	Asphalt	Track ballast
Arm et al., 2017		X	X
Lederer et al., 2020	X	X	
Menegaki & Damigos, 2018	X	X	
Mhatre et al., 2021	X	X	X
Youcai & Sheng, 2017	X	X	

El-Haggar, 2007	X	X	
Zhang et al., 2022		X	
De Melo et al., 2011		X	
Fatta et al., 2003		X	
Gálvez-Martos & Istrate, 2020	X	X	
Sáez et al., 2014	X	X	
Cristiano et al., 2021	X	X	X
Roque et al., 2016	X		X

Source: Own elaboration

Eight of the selected sources apply to the EU context (either to country-specific or general frameworks). Concerning the **qualitative characterisation**, asphalt is recognized as infrastructure waste either alone (De Melo et al., 2011; Fatta et al., 2003; C. Zhang et al., 2022) or together with concrete (El-Haggar, 2007; Gálvez-Martos & Istrate, 2020; Lederer et al., 2020; Menegaki & Damigos, 2018; Sáez et al., 2014; Youcai & Sheng, 2017) or track ballast (Maria Arm et al., 2017; Cristiano et al., 2021; Mhatre et al., 2021; Roque et al., 2016).

No detailed information is available in the 13 studies analysed to perform a systematic characterisation of infrastructure waste in terms of **quantity generated**. These studies however confirm concrete, asphalt and track ballast as the most relevant CDW flows related to infrastructure. Using the Eurostat database, it is not possible to determine the amounts of infrastructure waste of all the Member States, as this is reported as part of the mineral waste fraction (i.e., W121 Mineral construction and demolition wastes) and not as individual category (i.e., LoW code 17 03 02 for bituminous mixtures, and 17 05 08 for track ballast).

Additional literature insights (see the first column of

Table 7) report infrastructure (asphalt) waste data for 7 of the 23 analysed countries. Due to the lack of data, two secondary raw materials streams deriving from infrastructure CDW, the reclaimed asphalt pavement and asphalt recycled aggregates, are considered as possible proxies and compared with the asphalt waste fraction to obtain a more complete picture. The **reclaimed asphalt** is generated due to maintenance, reconstruction, resurfacing, or to obtain access to buried utilities and is covered by harmonized European standards, while the **asphalt recycled aggregates** are reprocessed granular materials previously used in construction of infrastructure (UEPG, 2023). Specific data for reclaimed asphalt from the European Asphalt Pavement Association (EAPA) are found (EAPA, 2023), covering 12 of the 23 countries analysed in the current study (i.e., Austria, Belgium, Croatia, Czechia, Denmark, France, Germany, Hungary, Ireland, Slovakia, Slovenia, Spain). These data are reported in the second column of

Table 7 while data from the Aggregates Europe – UEPG are shown in the third column (UEPG, 2023) and apply to 16 of the 23 countries analysed (i.e., Austria, Belgium, Bulgaria, Cyprus, Denmark, Finland, France, Germany, Greece, Malta, Netherlands, Poland, Portugal, Slovakia, Spain, Sweden). The significant differences between the asphalt waste fraction and the two secondary raw material flows (e.g., asphalt recycled aggregates is up to 7 times larger than the asphalt waste fraction in France) is related to the fact that both reclaimed asphalt and asphalt recycled aggregates are often not reported as waste, especially if prepared for reused/recycled on-site, as also highlighted in Arm et al. (2017). However, the lack of a suitable level of detail of data does not make it possible to perform a systematic comparison and thereby draw any overall conclusion. Therefore, room for improvement exists. The annual reporting on material recovery from CDW according to Commission Decision 2011/753/EU (European Commission, 2011) and Commission Implementing Decision (EU) 2019/1004 (European Commission, 2019) could represent a starting point from which to extrapolate the individual fractions of the Member States, with a particular focus on infrastructure waste asphalt (LoW code 17 03 02) and track ballast (LoW code 17 05 08) (see Table 3). In this respect, though the asphalt and track ballast average compositions do not exceed the 1% of the overall CDW amount, only five of the 27 Member States (i.e., Czechia, Denmark, France, Germany and Luxembourg) are represented within that percentage making it less significant and very uncertain. It would be desirable to standardise the data collection methods at the European level so

that all Member States can contribute with the same level of detail (e.g., indicating the individual LoW codes rather than EWC-stat category).

Table 7. Amounts and comparison between asphalt waste fraction in the European countries and asphalt secondary raw materials (reclaimed asphalt and asphalt recycled aggregates).

Country	(1) Asphalt waste fraction (Source: Damgaard et al., 2022; BIO by Deloitte, 2015a; BIO by Deloitte, 2015d) [t year ⁻¹]	(2) Reclaimed asphalt (Source: EAPA, 2021) [t year ⁻¹]	Δ% between (1) and (2)	(3) Asphalt recycled aggregates (Source: UEPG, 2021) [t year ⁻¹]	Δ% between (1) and (3)
Austria	2 402 000	900 000	167%	4 000 000	-67%
Belgium	-	1 506 000		22 000 000	
Bulgaria	-	-		1 000 000	
Croatia	-	390 000		-	
Cyprus	-	-		400 000	
Czechia	508 000	2 500 000	-392%	-	
Denmark	1 169 000	1 172 000	-0.26%	3 000 000	-157%
Finland	-	-		5 200 000	
France	9 300 000	6 042 000	54%	67 900 000	-630%
Germany	15 416 500	11 600 000	33%	76 000 000	-393%
Greece	-	-		600 000	
Hungary	-	160 000		-	
Ireland	-	500 000		-	
Italy	636 902	-		-	
Luxembourg	203 599	-		-	
Malta	-	-		300 000	
Netherlands	-	-		24 300 000	
Poland	-	-		7 000 000	
Portugal	-	-		200 000	
Slovakia	-	70 946		600 000	
Slovenia	-	79 000		-	
Spain	-	2 495 000		3 500 000	
Sweden	-	-		5 800 000	

Source: Own elaboration.

2.4.1 Management practices for infrastructure waste

Concerning the asphalt waste fraction, mainly asphalt pavement, recycling processes include operations such as milling, crushing, sieving (screening), blending (Ali & Rojali, 2023; EAPA, 2023) and clearing with magnetic

separators (El-Haggar, 2007). Recycling asphalt to produce new asphalt⁷ in either stationary or mobile plants is well-established, using different techniques to include the reclaimed asphalt in hot mix, warm/half warm mix or cold mix. There are often restrictions on the quantity of reclaimed asphalt to be used in the mix according to the standard EN 13108-8 (EAPA, 2023). Besides, it is possible to recycle the reclaimed asphalt through hot in-place recycling processes performed by specialised machines where the road surface is heated, milled and the asphalt mix is recycled in place (Arm et al., 2014). It is also possible to recycle asphalt as unbound aggregates through a crushing process. Specifically, reclaimed asphalt could be used as road base with other crushed and screened aggregates, new paving material, and asphalt products by mixing it with new asphalt binders. Finally, reclaimed asphalt can be sometimes mixed with other recovered materials for backfilling purposes or used in unspecified backfilling as it is (Arm et al., 2017). For some countries, such as Germany, available data from stakeholders (Kreislaufwirtschaft Bau, 2023) show that for bituminous mixtures (LoW code 17 03 02), in 2020, 92.9 % were recycled, 3 % were backfilled and 4.1 % were disposed of in landfills. Roofing asphalt can also be recycled into paving asphalt by existing techniques (Barry et al., 2014), acknowledging that even if the quantity of this material is small compared to paving asphalt, the bitumen content is not negligible (Arm et al., 2017).

For the track ballast, preparing for reuse again as track ballast is possible through a cleaning process using rail-mounted machines, where a residual fine-grained fraction that cannot be used as track ballast is removed (Arm et al., 2017). Track ballast when resulting from demolition or excavation of rail tracks is commonly recycled as aggregate in asphalt production or unbound applications. The recycling operation can include crushing in order to produce a certain desired particle size. The substitutability factor for both options (preparing for reuse and recycling) is usually one, i.e. the quality of the recycled material is equivalent to that of the primary material. Finally, track ballast can be recovered through backfilling substituting other aggregates/soil in backfilling operations (in this case the substitution factor will depend on the filling materials' properties as compared to track ballast) (Arm et al., 2014). Finally, for concrete, since as mentioned before this fraction is a CDW stream belonging to both infrastructure and building activities, the main management options are reported in section 3.1.

⁷ According to Arm et al. (2017) it is not considered preparing for reuse since formally it does not fulfil the WFD definition.

3. Technologies and processes for CDW management

Based on a literature review, this section summarises the main technologies (with different Technology Readiness Levels; TRL) used to manage the individual material fractions of CDW (see Table 8). Note that management options for contaminated fractions or containing hazardous substances are different from the processes used for non-contaminated wastes. Since the quantity of contaminated or hazardous waste is limited (around 1-2% of the total generated), and the management options are case-specific depending on the specific contamination levels and substances, herein only management options for non-contaminated and non-hazardous wastes are reported. A reference to the demolition process, either conventional demolition (CD) or selective demolition (SD), that foster the different management technologies is done. Besides, this section makes a reference to the enabling measure known as ‘Design for Deconstruction (DfD)⁸’, referring to a group of measures taken at the design phase of buildings and construction products that contribute to increasing circularity within the sector, by promoting reuse and recycling at the end of life of a building.

By way of a literature review, information was collected pertaining to different building materials and their (potential) handling in three contexts: conventional demolition (status quo), selective demolition and DfD, with the goal of describing current practice and highlighting areas for improvement. Further info on this can be accessed in a separate publication (Pristerà et al., forthcoming) that goes deeper into the analysis considering four building types differentiated on the basis of their structural material (concrete, masonry, steel and timber; this classification has its roots in the Eurocodes; European Commission, 2023b).

Table 8: Summary of technologies and management options reported in the literature for the different CDW material fractions. CD: Conventional demolition; DfD: Design for Deconstruction; SD: Selective demolition.

Waste fraction	Enabling process/measure	Management option	Main output	Potential material substituted	Reference	TRL
Concrete	CD	Recycling ⁽¹⁾	Recycled aggregates	Sand/Gravel	(C. Zhang et al., 2020)	9
	CD, SD	Recycling	Cementitious material Recycled aggregates	Cement Sand/Gravel	(Gebremariam et al., 2020; C. Zhang et al., 2020)	7-8
	CD	Landfill	-	-	(Data by Ecoinvent)	9
	SD, DfD	Preparing for reuse	Concrete material	Concrete	(Marsh et al., 2022)	9
Wood	SD, CD	Recycling	Particle board	Particle board	(Faraca, Tonini, et al., 2019)	9
	CD	Landfill	-	-	(Data by Ecoinvent)	9
	SD, CD	Incineration	Electricity & heat	Electricity & heat	Multiple refs ⁽²⁾	9
	DfD, SD	Preparing for reuse	Structural timber/wood	Wood	(Whittaker et al., 2021)	9

⁸ Design for adaptability, design for disassembly, design for longevity and durability and reversible building design, henceforth grouped under the term **design for deconstruction (DfD)**, are all methods by which this goal can be achieved.

Steel	SD, CD	Recycling	Iron ingot	Iron ingot	(Rigamonti et al., 2009)	9
	CD	Landfill	-	-	(Data by Ecoinvent)	9
	DfD, SD	Preparing for reuse	Steel	Steel	(Coelho et al., 2020)	9
Aluminium	SD, CD	Recycling	Aluminium ingot	Aluminium ingot	(Rigamonti et al., 2009)	9
	CD	Landfill	-	-	(Data by Ecoinvent)	9
	DfD, SD	Preparing for reuse	Aluminium	Aluminium	(Diyamandoglu & Fortuna, 2015)	9
Plastic PVC	SD, CD	Recycling (mechanical)	Polyvinylchloride	Polyvinylchloride	(Faraca, Martinez-Sanchez, et al., 2019)	9
	SD, CD	Recycling (chemical)	Polymer Base chemicals	Polymer Base chemicals	(Lase et al., 2023)	4-9
	SD, CD	Landfill	-	-	(Data by Ecoinvent)	9
	SD, CD	Incineration	Electricity & heat	Electricity & heat	Multiple refs ⁽²⁾	9
Plastic EPS	SD, CD	Recycling (mechanical)	Polystyrene	Polystyrene	(European Commission, 2023a)	9
	SD, CD	Recycling (chemical)	Polymer Base chemicals	Polymer Base chemicals	(Lase et al., 2023)	4-9
	SD, CD	Landfill	-	-	(Data by Ecoinvent)	9
	SD, CD	Incineration	Electricity & heat	Electricity & heat	Multiple refs ⁽²⁾	9
Gypsum	SD, CD	Recycling	Plasterboard	Plasterboard	(Pantini et al., 2019)	9
	SD, CD	Recycling (retarder in cement)	Recycled gypsum	Natural gypsum	(Pantini et al., 2019)	9
	SD, CD	Recycling (in sewage sludge treatment)	Recycled gypsum	Natural gypsum	(Pantini et al., 2019)	9
	SD, CD	Recycling (agriculture)	Recycled gypsum	Lime	(Pantini et al., 2019)	9
	SD, CD	Landfill	-	-	(Data by Ecoinvent)	9

Ceramic & Tiles	SD, CD	Recycling ⁽¹⁾	Recycled aggregates	Sand/Gravel	(Fořt & Černý, 2020)	9
	SD	Recycling	Cementitious material	Cement	(Fořt & Černý, 2020)	6-7
	CD	Landfill	-	-	(Data by Ecoinvent)	9
	SD, DfD	Preparing for reuse	Ceramic material	Ceramic material	(Whittaker et al., 2021)	9
Glass wool	SD	Recycling	Glass wool fibres	Natural fibres	(Hendriks & Janssen, 2001) (Väntsi & Kärki, 2014)	8
	SD, CD	Recycling	Recycled aggregates	Sand/Gravel	(Väntsi & Kärki, 2014)	6-7
	CD	Landfill	-	-	(Data by Ecoinvent)	9
Stone wool	SD	Recycling	Stone wool fibres	Natural fibers	(Hendriks & Janssen, 2001) (Väntsi & Kärki, 2014)	8
	SD, CD	Recycling	Recycled aggregates	Sand/Gravel	(Väntsi & Kärki, 2014)	6-7
	CD	Landfill	-	-	(Data by Ecoinvent)	9
Bricks	CD	Recycling ⁽¹⁾	Recycled aggregates	Sand/Gravel	(Fořt & Černý, 2020)	9
	SD	Recycling	Cementitious material	Cement	(Fořt & Černý, 2020)	6-7
	SD	Recycling	Alkali activated blocks	Concrete	(Fořt & Černý, 2020)	6-7
	CD	Landfill	-	-	(Data by Ecoinvent)	9
	SD, DfD	Preparing for reuse	Brick	Brick	(REBRICK, 2013)	7-9
Glass	CD	Recycling	Recycled aggregates	Sand/Gravel	(Mohajerani et al., 2017)	9
	SD, DfD	Recycling	Flat glass	Flat glass	(Rigamonti et al., 2009)	9
	CD	Recycling	Other glass products (container glass)	Container glass	(Hestin et al., 2016)	9

	CD	Landfill	-	-	(Data by Ecoinvent)	9
	SD, DfD	Preparing for reuse	Glass	Glass	(Pristerà et al., forthcoming)	9
Excavated soil	-	Recycling	Individual components (sand, clay)	Sand/Gravel Clay	(Huang et al., 2022)	9
	-	Recycling - stabilisation	Stabilized soil	Concrete or Sand/Gravel	(Firoozi et al., 2017)	9
	-	Recovery - backfilling	Soil	Sand/Gravel	(Guyer, 2012) (Haas et al., 2020)	9
	-	Landfilling	-	-	(Hale et al., 2021).	9
	-	Preparing for reuse	Soil	Sand/Gravel	(Kataguirri et al., 2019)	9
Dredging spoil	-	Recycling (use on upland)	Dredged sediments	Depending on the use: Sand/Gravel Fertilizer	(Bates et al., 2015) (Apitz, 2010) (Ferrans et al., 2022).	9
	-	Recycling	Individual components (sand, clay)	Sand/Gravel Clay	(Henry et al., 2023)	9
	-	Recycling - stabilisation	Stabilized sediments	Concrete or Sand/Gravel	(Svensson et al., 2022)	9
	-	Recovery - backfilling	Dredged sediments	Sand/Gravel	(Apitz, 2010)	9
	-	Disposal (landfilling/open sea)	-	-	(Bates et al., 2015; Svensson et al., 2022)	9
	-	Preparing for reuse (use on aquatic habitat)	Dredged sediments	Depending on the use: Sand/Gravel Fertilizer	(Maryland Department of the Environment, 2017)	9

(1) This can also be considered as recovery – backfilling depending on final use

(2) Tonini et al. 2013; ARC, 2015; Martinez-Sanchez et al. 2015; Bisinella et al. 2018; Fruergaard et al. 2010

Source: Own elaboration.

3.1 Established and prospective recycling and preparing for reuse processes

What follows is a description of typical recycling and preparing for reuse processes that may apply to the individual fractions of CDW, but that are not necessarily applied in all circumstances and across all EU27 member states. Additionally, possible recycling processes that may apply in a future perspective are also briefly outlined to the extent that these descriptions are available in the techno-scientific literature or from stakeholders. Notice that, while currently preparing for reuse marginally taking place and only for some niche-applications, we nevertheless describe the possible enablers for increased (preparing for) reuse in selective demolition or DfD (largely taken, as mentioned before, from the study of Pristerà et al. (forthcoming)). Notice that, for simplicity, we generically talk about 'reuse', indicating both indirect and direct reuse and preparing for reuse. While landfilling and incineration (e.g., for high calorific content waste such as wood or plastics) are also mentioned as possible treatment routes for CDW material fractions, they are not described in detail as these pathways are well-known and thoroughly detailed elsewhere.

3.1.1 Concrete

Following conventional demolition, concrete waste is typically used in the production of recycled aggregates (RA), which are then used mainly for road construction and backfilling although higher value applications are in principle possible (e.g., in concrete production). The use of RA from concrete waste (typically technically referred to as recycled concrete aggregates (RCA) or sometimes coarse recycled concrete aggregates (CRCA)) for the production of structural concrete is currently limited as suggested in a recent JRC study (Pacheco et al., 2023). The authors underline that, in most Member States, recycled aggregate concrete (RAC) is hardly (or not at all) produced (RA account for only 8.2% of all aggregates produced in the EU27 in the year of 2019). The same authors estimate that 10-20% incorporation of RCA in current structural concrete production would be realistic (i.e., indicating a possible technically feasible recycled content for concrete in the EU market). If the concrete fraction is contaminated by other materials, notably organics and sulphates, landfilling is also a possible management option. For a thorough description of the state-of-play for RA market, the readers are referred to the detailed study by Pacheco et al. (2023).

Recycling

As for recycling, there are different technologies as described by C. Zhang et al. (2020) or Pacheco et al. (2023). The simplest and most widely applied one relies on a crushing process in order to mostly produce RA, while a minor fraction is RCA. To produce the RCA, the wet process is widely used (note that a dry process is also possible) producing coarse aggregate and two by-products: sieve sand and sludge. The former does not meet the quality standard of fine concrete aggregate; therefore, it cannot be used in new concrete manufacturing, and it is usually either used like RA for road construction or backfilling operations or disposed of in site elevation. Sludge is subject to waste operations and sent to landfill (C. Zhang et al., 2020). When selective demolition is implemented, the inert waste fraction normally has fewer impurities and can be used for the production of RA to be used for the production of structural concrete. This is typically recognised as a higher value application because of the circular and higher value of the end application (bounded use in structural concrete relative to less demanding unbounded use in road basis and backfilling) and because of the higher revenues for the recyclers. Potentially, the material can then be recycled multiple times.

Perspectives for recycling

An enhanced recycling process has been studied in the literature to produce a secondary aggregate that can be used for concrete production (Gebremariam et al., 2020; C. Zhang et al., 2020). This process is an extension of the process producing RA explained before and includes two innovative technologies to improve recycling of concrete waste, namely Advanced Dry Recovery (ADR) and Heating Air classification System (HAS). While ADR is used to sort out clean coarse aggregates for use in the production of structural concrete, HAS is used to produce clean fine aggregates by heating and separating the ultrafine hydrated cement components that can be used to replace virgin cement (i.e., relative to the production of solely RA, this allows to recover a share of the treated concrete waste as cement).

Perspectives for (preparing for) reuse

DfD measures aimed at enabling reuse include modular construction and prefabrication (i.e., the use of precast concrete elements). The use of dry mounting jointing methods, or other removable connections, can further facilitate disassembly and reduce the damages incurred by the concrete elements during the process. DfD can have varying results depending on the building element to which it is applied: e.g., precast columns and beams can often be recovered and reused, though there is a lack of an established market; the right type of joint can

make it possible to reuse concrete floor systems and precast concrete facades; interlocking concrete blocks can be used to building walls that can be easily disassembled.

3.1.2 Wood

Wood waste from CDW is often contaminated with preservatives and therefore classified as wood waste to be treated via incineration, other forms of energy recovery or landfilling (e.g., category III-IV in DK, Germany (Höglmeier et al., 2017)).

Recycling

The most common recycling process for wood waste is the production of particleboard panels. During this process, the waste undergoes pre-treatment (wood waste shredding followed by sieving, milling, and sorting of metals and other impurities contained in wood waste), then it is dried down to a ~6% moisture content (as percent of the wet weight, % ww) and sprayed with urea-formaldehyde resin, before being hot-pressed into a mat (Faraca, Tonini, et al., 2019). Wood waste constitutes ca. 80% ww of the feedstock for particleboard in Denmark (Vis et al., 2016), while urea-formaldehyde resin typically constitutes ca. 10% ww of the final product (Rivela et al., 2006). Any wooden by-products originating from the wood waste reprocessing stage are usually combusted in small-size biomass boilers. Foreign materials found in the collected wood waste are generally separated at collection points and sent to recycling (ferrous and non-ferrous metal impurities), landfilling (glass, stones, composite building materials), and incineration (plastics, textiles, cardboard, garden waste). Fly and bottom ashes originating from the combustion and incineration processes are generally sent to landfills for fly and bottom ash, respectively.

Perspectives for (preparing for) reuse

Following selective demolition, structural timber sections hold great potential to be reused with minimal treatment (e.g., cleaning and cutting), provided that they are free of damage. If not suitable for structural elements, timber could still potentially be reused in non-structural elements (Whittaker et al., 2021). Reuse is possible, to some extent, for both lightweight and heavyweight construction; however, large timber elements designed for key structural roles can be challenging to reuse or recycle effectively, as they are often used in combination with other materials from which separation is difficult. Smaller wood elements, as opposite to structural timber sections, are easier to damage during the demolition process and it is therefore more common for them to be recycled, incinerated or landfilled.

DfD measures have different applications in lightweight and heavyweight construction: in the former case, they tend to focus on individual building elements (e.g., walls), while in the latter they also include the production of three-dimensional re-usable modules. DfD approaches aimed at facilitating reuse include prefabrication and modular construction, as well as a focus on the employment of easily identifiable and removable connections (e.g., mechanical connections, metal plate connectors), in order to reduce any potential damage to building components. Moreover, it is often advisable to avoid superfluous treatments and finishes, thus reducing contaminants which may compromise the direct reuse potential of timber elements.

3.1.3 Metals: steel and aluminium

Recycling

Virtually, almost all steel and aluminium are collected for recycling regardless of the type of demolition process. Even when conventional demolition practices are applied, leading to collection of mixed CDW, downstream sorting processes can efficiently recover metals via advanced sorting technologies (X-ray fluorescent, Eddy current, laser induced breakdown spectroscopy, etc.) which are increasingly used to obtain high quality metal scrap fractions. In the recycling process producing iron scrap, iron waste is cut/sheared; a magnetic separator is then used to remove impurities, such as paper, plastics and non-ferrous metals. The separated ferrous metals thus obtained are cleaned at 90–95% and can be sent directly to a steel smelter (Rigamonti et al., 2009). The reprocessing of scrap ferrous metal is a well-established industry. As for aluminium, the recycling process, which results in the production of aluminium ingot, consists of aluminium waste undergoing pyrolysis and then being melted in a rotary kiln fed with natural gas. The resulting ingots are then sent to foundry for remelting (Rigamonti et al., 2009). The reprocessing of scrap aluminium metal is a well-established industry.

Perspectives for (preparing for) reuse

Selective demolition can enable preparing for reuse of selected components as steel purlins, columns and rafters, by reducing the damage incurred when the building is demolished. Moreover, steel products are easily

prepared for reuse owing to the methods of construction used, including use of bolted connections (Coelho et al., 2020). Similarly, selective demolition can enable preparing for reuse of aluminium products; that is the case for window frames, which can be collected from a building and prepared for reuse in their original application.

By implementing DfD measures, reuse can be enabled to different degrees, from in-situ reuse without component removal from the structure, to reuse of the whole structure in another location, to reuse of specific building components and their constituent products. Prefabrication and modular construction are effective DfD strategies for steel, as they are for timber and concrete, and bolted connections are recommended as a way to facilitate disassembly and, subsequently, reuse; fire protectants, however, can be an obstacle to the reuse of steel if they cannot be safely removed.

3.1.4 Polyvinylchloride (PVC)

Recycling

Following conventional demolition, soft polyvinylchloride (PVC) tends to be collected, sorted and sent to recycling to produce roofing sheets, while hard PVC is often recycled to PVC dust, chips and granulate. PVC pipes, in particular, can be recycled into new pipes. PVC can also be landfilled or treated in waste-to-energy treatment plants such as in the RecoChlor project⁹, in which chlorine from difficult-to-recycle EoL PVC products is recovered and recycled by producing hydrochloric acid (HCl), which is then reused in the chemical industry to obtain new products. Selective demolition generally leads to increased recycling rates and better recycled material quality.

In the mechanical recycling process producing PVC, waste undergoes a pre-treatment where it is shredded and sieved. Metal and other impurities are removed, and the plastic flow is sent to further processing and mechanical recycling. Any remaining materials are incinerated. The plastic reprocessing steps include grinding, washing, drying and pelletizing into recycled pellets that substitute for corresponding virgin materials (Faraca, Martinez-Sanchez, et al., 2019).

While mechanical recycling is a more established recycling option due to low energy resource demand, chemical recycling technologies are being developed to foster recycling and avoid reducing the quality of the recycled material relative to the quality required for plastics applications in building and construction (e.g., by solvolysis, dissolution, pyrolysis, gasification). This is exemplified in the VinylPlus project¹⁰.

Perspectives for recycling

Via selective demolition, window profiles made of PVC can be recycled and used in the production of new profiles, though this is a niche application.

3.1.5 Expanded polystyrene (EPS)

Following conventional demolition, EPS-based insulation is typically landfilled or incinerated. It is important to highlight that polymer-based insulation is often difficult to dismantle and individually collect.

Recycling

Expanded polystyrene (EPS) can go through closed-loop recycling, to produce new insulation, or open-loop recycling, to produce lightweight concrete, car parts, etc. In the recycling process producing EPS, plastic EPS is shredded to the right dimension and separated from metals and other impurities. Considering that 98% of EPS actually consists of air, solutions involving EPS compression are recommended. While the residues of waste products are generally incinerated, a recycling based on a solvent-based separation (dissolution) is typically applied. This process is supported by use of water, wastewater, nitrogen and energy. The resulting granules can be melted and remoulded into various products, usually the same product from which it came.

Perspectives for recycling and (preparing for) reuse

Selective demolition is expected to increase recycling rates of insulation plastic materials, while DfD can be applied to select the most appropriate insulation materials, in order to enable reuse, when possible, or further foster recycling. For instance, sprayed insulation (e.g., cellulose fibre, urea formaldehyde) should be avoided, as it is difficult to salvage during deconstruction. On the other hand, blown insulation can be safely extracted using

⁹Within VinylPlus project - <https://www.vinylplus.eu/>

¹⁰ VinylPlus project - <https://www.vinylplus.eu/>

appropriate techniques. Additionally, both rigid and flexible slab insulation solutions can be reused, though from a practical perspective it is easier to reuse the latter as rigid slabs are more easily damaged during the deconstruction process.

3.1.6 Gypsum

Following conventional demolition, gypsum is generally landfilled. However, plasterboards could be recycled into new plasterboards (closed loop) or used in cement production or as a soil improver (open loop).

Recycling

In the recycling process of gypsum, recyclers adequately segregate the plasterboard material (around 84% of the material), from cellulose materials (15.2%) and ferrous metals (0.02%) (to be recycled as well). Then, different recycling routes are possible, according to Pantini et al. (2019). In the recycling process producing new plasterboards (up to the recommended maximum content of recycled gypsum in new plasterboards of 30%), gypsum waste is already suitable for the use in the manufacturing process, as natural gypsum, when the dimension is below 15mm. Thus, shredding and secondary milling machines might be needed. It is recycled through a cycle of calcination and rehydration, requiring a relatively pure starting material (Vrancken & Laethem, 2000). Other recycling pathways will produce recycled gypsum to be used as additive in the cement production (with an addition limited at 5% of natural gypsum supply to avoid technical problems and a substitutability factor of 0.99:1 per kg natural gypsum), or in sewage sludge treatment plants for further use in agriculture (with no restriction of dosage as long as the final product has a CaO content of at least 15% and a substitutability factor of 0.9:1 per kg of natural gypsum), and the direct use in agriculture to improve soil properties is also an option (to substitute agricultural lime with a substitutability factor of 0.37:1).

Perspectives for recycling

The results of applying selective demolition on gypsum waste recycling vary depending on the gypsum product being targeted. Where plasterboards are concerned, selective demolition leads to better waste segregation and, therefore, it facilitates recycling to produce new plasterboard. Selective removal of gypsum plaster, on the other hand, is a labour-intensive process, and it is mainly undertaken with the goal of removing impurities from the stony fraction of CDW waste to better recycle it, rather than to recover the gypsum itself. In this context, landfilling remains a popular option even when selective demolition is applied, largely owing to economic barriers and the relatively low market value of the secondary material. The market for recycled gypsum is indeed impacted by the availability of flue gas desulphurisation gypsum.

Implementing DfD measures (e.g., dry construction methods) can contribute to reducing impurities within the waste fraction and improving its recyclability potential. However, whether recycling will actually occur still depends on the market value of the secondary material.

3.1.7 Bricks

Following conventional demolition, bricks are generally crushed together with other inert materials and used in the production of RA, to be employed in road construction and for backfilling purposes (not structural concrete). They can also be disposed of in a landfill.

Recycling

The recycling process to produce RA consists of several successive steps including handling, crushing, and screening to obtain a more homogenous ready-to-use material without impurities. A minor fraction of residues is resultant and generally sent to landfill. Typically, loading shovels, chain feeders, jaw crushers, conveyor belts, and vibrating devices powered by diesel or electricity are used in this process (Fořt & Černý, 2020). The produced RA are typically used in road construction and for backfilling purposes (not structural concrete; Pacheco et al (2023)).

Perspectives for recycling

A second recycling process produces material utilised as a Portland cement replacement, and it is an extension of the RA recycling process introduced earlier, with the main scope of producing a finer fraction, typically with d_{50} of $\sim 50 \mu\text{m}$ (Fořt & Černý, 2020). For this purpose, additional milling and vibration steps are employed. The last important step aimed at the achievement of pozzolanic activity of such material comprises drying at 70°C to remove excess water (Fořt & Černý, 2020). A third recycling process produces alkali activated blocks utilised as concrete replacement, and similarly to the previous technology the waste brick needs to be processed first to obtain a fine fraction with $d_{50} \sim 50 \mu\text{m}$ and then dried. Additionally, alkaline activators (e.g., sodium hydroxide,

sodium silicate) are used in the mix design. The mixture usually contains sodium hydroxide pellets, sodium silicate (water glass) with $\text{SiO}_2/\text{Na}_2\text{O}$ molar ratio of 1.6, sand, and finely milled brick dust, and provides mechanical performance comparable with common concrete-based composites (Fořt & Černý, 2020). These are however recycling processes with very low TRL value and not fully demonstrated at commercial scale.

Selective demolition leads to a decrease in impurities, and consequently, to the improved quality of the RA produced from this waste fraction. Though not yet implemented at large scale, this opens up the possibility of being able to use these aggregates in structural concrete. Other niche applications include the possibility of using the fine fraction obtained during the recycling process to produce masonry mortar, and the potential use of brick waste to substitute clay soil in the production of new unfired bricks.

Perspectives for (preparing for) reuse

Via selective demolition, it is possible to prepare CDW bricks for reuse. The REBRICK project (REBRICK, 2013) develops and demonstrates the technical viability to produce reusable bricks with market specifications. The CDW passes through an equipment that separates mortar and other materials, such as wires, cement, and wood from the bricks, and thus another system that separates whole bricks from damaged bricks. Thus, through a vibration-based system technology, concrete and cement from old bricks are cleaned and then reused. After being cleaned, they are manually sorted, and automatically stacked and wrapped.

Where DfD is concerned, the main strategy emerging from the literature review consists in the construction of mortar-free structures, in which the bricks are connected by way of steel plates and wall ties. Prefabrication of modular units further increases the reuse potential of this material.

3.1.8 Ceramics and tiles

Recycling

Following conventional demolition, ceramic and tiles are normally used to produce low-quality RA for road construction and backfilling, similarly to bricks. The RA produced from ceramics and tiles cannot be used for the production of structural concrete (Pacheco et al., 2023).

Perspectives for recycling

When selective demolition is applied, ceramics and tiles present several additional recycling opportunities, such as the possibility of being used as supplementary cementitious material or as a precursor to manufacture an alkali-activated binder (when comprising both red brick and tile waste) (Whittaker et al., 2021). These are however recycling processes with a very low TRL value and not fully demonstrated at commercial scale.

Perspectives for (preparing for) reuse

Ceramic normally undergoes the same processes described for (clay) bricks. Following selective demolition, the recovered ceramics can be prepared for reuse as floor or wall tiles through blending the ground ceramic fraction in resin and allowing it to harden in moulds (Whittaker et al., 2021). DfD solutions can target specific ceramic elements, such as floor tiles, to enable their reuse.

3.1.9 Mineral insulation: glass wool and stone wool

Upon conventional demolition, mineral insulation is considered unrecyclable in techno-scientific literature (eg, see Väntsi & Kärki (2014)) but some stakeholders mention recycling pathways for the brick industry as a possible avenue (specifically, mineral wool can be used in the production of masonry mortar) or as RA. Whenever the waste is contaminated, it is landfilled.

Recycling

Although there are several different options for glass wool and stone wool waste recycling in the literature, most of them refer to mineral wool waste from the production process, being more restricted when the origin is CDW. Thus, Väntsi & Kärki (2014) report the possibility to use mineral wool waste combined with low-melting illite clays to produce composite ceramics. Other products using recycled mineral wool waste, by dispersing them in a solution of cold water and blended with other fillers and binder ingredients could be ceiling tiles substituting other mineral fiber materials (with a substitution ratio of up to 1:1). Another possibility is to use mineral wool waste in cement-based composites as coarse aggregate or fine aggregate substituting natural aggregates significantly improving the compressive strength, splitting tensile strength, absorption, resistivity, and chloride-ion penetration resistance of the cement-based composite. Other recycling options are reported within the WOOL2LOOP project (WOOL2LOOP, 2020) such as the remelting of specifically glass wool waste by

burning it with natural gas with the aid of oxygen input and thus using the product again in construction sites, the addition of mineral wool previously pre-processed or milled to the expanded clay manufacturing process, or the complement of virgin materials in stone wool products. Hendriks & Janssen (2001) report a process to recycle glass wool through gasification in an oxygen-free environment (nitrogen), using the output fibres to produce new glass wool.

Perspectives for (preparing for) reuse

According to Rudjord (2018), reuse is not an option for glass wool waste, since the fibres are not of uniform size and the amount of organic content is too large. On the other hand, Väntsi & Kärki (2014) and Hendriks & Janssen (2001) report the possibility of using mineral wool as an artificial substrate to grow various plants in soilless cultures (e.g., stone wool is currently the most widely used soilless medium). However, this would rather be classified as a recycling or recovery pathway (not reuse) as the mineral wool reuse is not meant for the purpose for which the material was originally produced and marketed. For stone wool, similarly, no information on case studies documenting reuse were found in the technical and scientific literature. However, some companies claim that is suitable for reuse as thermal insulation at a new site, provided that the material can be extracted intact from its previous location.

3.1.10 Glass

Following conventional demolition, glass is crushed and landfilled with other waste materials or recovered for low-grade applications (e.g., using glass cullet in the production of RA for road construction). Via selective demolition, flat glass can be recycled into container glass or, more rarely, into new flat glass. Generally, glass has a relatively low reuse potential due to its fragility.

Recycling

Via conventional demolition, glass ends up in the mixed CDW and can be used to produce RA. In the recycling process producing RA from mineral CDW, the inclusion of fine waste glass aggregates such as glass powder in concrete mixtures is allowed under certain conditions. While the workability of concrete containing crushed glass waste in lieu of conventional fine aggregates is still under discussion, especially concerning its physical properties and associated functionalities, many studies have identified this type of management process as technically feasible (Abd-Allah et al., 2014; Batayneh et al., 2007; Chen et al., 2006; Ismail & AL-Hashmi, 2009). Glass powder is glass that is milled down into very small particles, with a typical median grain size between 30 μm down to as fine as 0.1 μm . In the recycling process producing RA several successive steps including transport, separation and milling to obtain more homogenous ready-to-use material without impurities are applied, while a minor fraction of residues is sent to landfill (Aslani et al., 2023; Mohajerani et al., 2017).

Perspectives for recycling

Via selective demolition, windows are dismantled so that the glass is separated from the frame. The resulting glass waste contains a reduced quantity of impurities and is therefore more likely to be usable in the production of new glass. The recycling process involves different activities such as manual selection, shredding, screening, magnetic and non-magnetic separation to remove impurities and inert materials (ceramics and gravels) and to obtain a proper size distribution. The glass cullet is then delivered to a glass manufacturing plant, where it is used in the production of new glass, together with ordinary virgin raw materials (silica, calcium carbonate, sodium hydroxide, additives) (Rigamonti et al., 2009). The presence of cullet, which is characterised by a lower melting temperature than virgin raw materials, allows the glass furnace to be operated at a lower temperature, thus leading to significant primary energy savings (up to 20% when 80% of cullet is utilised in the kiln feeding). Once the glass cullet has been produced, it can be used either to produce new flat glass, or other types of glass (especially hollow glass, also known as container or packaging glass) or fiberglass (also known as glass wool) (Hestin et al., 2016).

Perspectives for (preparing for) reuse

In terms of DfD strategies, the most common one consists of the use of dry connection methods between glass panel and window frame; this technology facilitates dismantling and can enable reuse. Repurposing is also an option, meaning that glass obtained during disassembly or renovation can be used for indoor applications, which do not require high thermal standards. As mentioned earlier, glass has a relatively low reuse potential due to its fragility. Consequently, recycling is expected to be the most common solution even when DfD is implemented.

3.1.11 Excavated soil

A recent review from Scialpi & Perrotti (2022) summarises the studies related to the sustainable management of excavated soils in urban areas. The excavated soil waste management options reported are the following: preparing for reuse, recycling into individual fractions or via stabilisation, and recovery via backfilling.

Recycling

The direct application of excavated soil (e.g., in dams or roadbeds) is usually difficult due to its poor strength and, thus it must be stabilised (Huang et al., 2022). Stabilisation is a technology for improving geotechnical properties in terms of increased strength, reduced permeability and compressibility of soil (Magnusson et al., 2015). This technique, considered herein as recycling, involves the use of blends of soil and binders and the most reported stabilisation methods in the literature are the ones using cement, lime, fly ash, and fibers (Firoozi et al., 2017). Other methods using different types of binders include rice husk ash, bituminous material, geotextiles and synthetic materials, and several recycled and waste products (Afrin, 2017). The application of different binders and the dosage of the blend depends on the type of soil (e.g., clay content) and the required physical and mechanical properties (e.g., strength and stiffness) of the blend. Namely, the stabilisation with lime is suitable for fine-grained soils, meanwhile the cement can be used for stabilising nearly all types of soils (whenever the organic content is limited to 2%) (Patel, 2019). There are other lesser-known technologies for soil modification such as fluidification that use fluidifiers and plasticisers to stabilise the soil (Michalcikova & Drochytka, 2018). It can be done on-site or off-site. For the former, excavation of the material is not needed. The off-site option involves the excavation of the material and additional transport of the excavated soil to the site where it is going to be used. The process includes the production and transport of the binder to the site and the mixing with the binder.

Excavated soil is recycled in various ways to replace traditional construction materials (N. Zhang et al., 2020). It can be done through on-site recycling plants (that normally function with diesel instead of electricity) or through stationary plants that require additional transport comparing to the on-site plants. The general recycling process (Huang et al., 2022) mainly consists of a screening and sieving phase to assure the adequate size of the soil. It includes an iron removal phase to collect any scrap steel that could cause damage to the separation equipment that extract the recycled sand from the soil and send it to the washer for further cleaning. The possible coarser aggregates are blasted to grind them into sand and washed. In the separation equipment, the other components of the soil (mainly clay and silt) are headed to the slurry tank where flocculating agents are used to precipitate them. Those are sent to the filter press to make the filter clay cakes. The filter cake can be either landfilled or further recycled mixing it with cement and curing agents (e.g., to produce RAC) (Xu et al., 2022). Other authors in literature reported recycling processes for excavated soil in line with the general one explained herein but extended to final products such as recycled bricks (baking free bricks or baked bricks) (N. Zhang et al., 2020), cement treated base materials (Xu et al., 2022), or concrete blocks (Luo et al., 2022). Note that the recycling to their individual components is rarely done due to economic constraints.

Preparing for reuse

A soil can be prepared for reuse and applied either on-site¹¹ or in other locations/projects, whenever allowed by legislation. Determining whether a material is suitable for reuse in an application depends on several practical and site-specific considerations and factors. Thus, to prepare for reuse and reuse excavation soils, different geotechnical properties (e.g., cohesion and friction angle, grain size distribution, swelling and loss of strength by wetting, organic matter content, hydraulic conductivity) of the receiving project (e.g., roadbeds, paving layers, vegetation cover replacement) have to be fulfilled requiring a characterisation of physical and mechanical properties (e.g., shear strength, dry density), as well as the compliance with environmental safety standards (Kataguirri et al., 2019). This management option includes the relocation of the soil within the receiving site using machinery and the compaction of the material. In the same line, the excavated soil can be used for backfilling either on-site or off-site depending on the geotechnical criteria documented and described in industrial standards (e.g., ASTM standards, AASTHO specifications).

Recovery

In the context of construction, backfilling is the practice of refilling the excavated pit with material to reinforce and maintain the foundation of a structure or any other structural part. It is important to highlight that complying with the recovery definition, the backfilling operation must replace other materials that are not waste,

¹¹ In case it is used on-site, they have to be declared previously as waste.

and in this sense the difference between reuse and backfilling for excavated soil is just semantic, acknowledging the difference in the waste hierarchy.

Finally, other applications have been explored in the literature, such as the possibility of using excavated soils for the creation of technosoils by mixing with compost (i.e., soils designed to mimic natural soil and suitable for vegetation growth) (Fabbri et al., 2021). Further innovative management options are also under development such as using such wastes for energy storage batteries. The EU project NewSETS, funded from the EU's Horizon 2020 programme¹², is focused on different technologies to store energy. Among them, the seasonal heat storage uses sand as storage medium. Excess electricity is used for heating up the sand to a high temperature (around 500 – 600 °C), later the stored energy can be used as heat for industrial steam production or district heating, and even back to electricity, thus working as a “battery”. Heat storage is not sensitive to sand grain size and might use grain sizes that are not suitable for the construction industry or were going to be landfilled (preferably high density, low-cost materials that are not from scarce sources).

3.1.12 Dredging spoils

When dredging spoils are non-toxic, they can be used on land for soil filling, construction purposes, coastal nourishment, and as an amendment in agriculture, horticulture, and forestry, as well as disposed directly in landfills or oceans whenever they comply with the pollutant-specific regulations (Crocetti et al., 2022). Thus, the dredging spoil waste management options vary depending on the level of contamination and local regulations. The reported ones in literature (Apitz, 2010; Maryland Department of the Environment, 2017) include the following: i) preparing for reuse, ii) recycling for use on land (either with or without aerobic composting), iii) recycling through stabilisation, iv) recovery through backfilling, and v) disposal. These management options require single treatment processes, or a combination of them, including: i) physical operations such as mechanical separation, dewatering, and washing; ii) chemical processes such as chemical oxidation, and solidification/stabilisation; iii) thermal processes such as desorption, thermal oxidation and immobilisation, and vitrification; and iv) biological processes (Crocetti et al., 2022). Note that most of those processes are commonly used to treat contaminated sediments, and that are typically not applied to non-contaminated dredging spoils.

Recycling

For the recycling and further use of the dredged material it requires some degree of drying or other processing. Minimal processing may consist of dewatering the material that is essential before land use due to the high-water content, and its negative influence on the subsequent transport and possible treatment/use. Different dewatering methods exist, from natural drainage and evaporation, also known as passive dewatering (Bates et al., 2015), that requires vast space and long retention times, to mechanical dewatering units such as filter presses and vacuum filters that increase performance and reduce land demand (Crocetti et al., 2022). The dewatering process can be accompanied by chemical conditioning using products such as iron and aluminium salts, or organic polymers like polyacrylamide (PAM), that helps releasing and removing the interstitial water (Crocetti et al., 2022; Zhou et al., 2021). The dewatered material is transported to the receiving site where it can be used in numerous potential beneficial uses including engineering (such as shoreline protection, reclamation and land formation (Bates et al., 2015), capping of contaminated dredged material in confined aquatic disposal or permanent cover of landfills, and agricultural use (either in agriculture for non-food crops, forestry, or horticulture) (Apitz, 2010). The recycling and further use on land includes the use as soil conditioner since the nutrients and organic matter content in these sediments could improve the chemical status of the soil, mainly as a potential source of phosphorus (Ferrans et al., 2022). The land use can be preceded by a biological process (i.e., aerobic composting) to degrade the organic carbon and nitrogen to create a stable end product (Zhou et al., 2021). However, their use as fertilisers in agriculture is still not allowed due to lack of permissive legislation and consolidated supply chains (Renella, 2021).

Through recycling, various products can be obtained from the dredging sediments in different forms such as individual fractions (i.e., sand, silt and clay), or as aggregated materials such as light weight aggregates (LWA) that are commonly classified as particles with very low density (i.e., clay and silt) (Crocetti et al., 2022). To obtain these products that later might be used for example in cement production, mineral processing techniques are used (Henry et al., 2023). Those can be dry techniques after the materials have been dehydrated, or wet

¹² The initiative has received funding from the European Union's Horizon 2020 research and innovation programme under grant agreements no. 646039 and no. 755970 - <https://www.newsets.eu/>

techniques to separate the low-density fraction. These includes operations such as sieving, crushing, flocculation, and filtering (Henry et al., 2023).

The recycling through stabilisation and solidification method is normally used to fixate and encapsulate the contaminants inside the sediment by adding binders, similarly to the process explained in the excavated soil section, lowering the permeability and reducing leaching, and enhancing the strength enough to be used in construction (Svensson et al., 2022). The binders that can be used include cement, lime, fly ash, slag, etc. According to Svensson et al. (2022). In a case study in Sweden, a mixture of binders (i.e., cement and ground-granulated blast-furnace slag) and sediments is used to build the port in Gothenburg.

Recovery

Recovery through backfill as structural and non-structural fill is also a possible use of dredging spoils. Engineered fill for uses such as roadway bed material, parking lot foundation or embankment fill are possible whenever requirements (type of material and gradation, plasticity, permeability, compaction, moisture content) of the engineering plans are fulfilled. To meet the physical and geotechnical requirements, processing might be needed through dewatering, blending or amending (Maryland Department of the Environment, 2017)

Preparing for reuse

The dredging spoil can be prepared for reuse unprocessed or with minimum processing and has been used typically for beneficial use options such as aquatic and wetland habitat development, environmental enhancement (in wildlife or fishery habitats) or beach nourishment (Maryland Department of the Environment, 2017).

CONFIDENTIAL – WORK IN PROGRESS

4. CDW management in the EU27

4.1 Mineral fraction

The mineral fraction of CDW (EWC code W12.1) includes concrete, bricks, ceramic and tiles, gypsum, insulation material (here assumed as inorganic, i.e., stone and glass wool), mixed construction waste, as well as track ballast and hydrocarbonised road-surfacing materials. Figure 4 shows the management of the mineral fraction of CDW in the analysed Member States in 2020. Based on Eurostat data (env_wastrt; European Commission, 2021c), the considered management options are disposal, incineration with energy recovery¹³, recycling and backfilling. Disposal is herein defined as landfill, incineration without energy recovery¹⁴ and other disposal, of which landfill is typically the dominant (> 99%) disposal method. Figure 4 shows that recycling as of 2020 is the predominant management form in most countries. Exceptions are countries where backfilling is the predominant management option e.g., Hungary, Denmark, Ireland, and Portugal where 88%, 71%, 73% and 63% of the mineral fraction of CDW, respectively, is reported to be used for backfilling purposes. Other countries such as Poland, France, Spain and Cyprus have waste disposal at higher than 20%. The Nordic countries are the only ones where incineration with energy recovery is practiced to some extent (more than 30% in Finland, around 9% in Sweden, and below 4% in Denmark). The official data reported do not provide further insights into the management of the individual fractions composing the mineral fraction, being the EU average 79% recycling, 10% backfilling, and 11% landfilling. In the attempt to close this knowledge gaps, we herein report insights from the literature to date. Summary may be found in Table 9.

For the case of bricks, grey literature reports cases of reuse occurring mainly in Denmark suggesting that about 3 million bricks per year are prepared for reuse (Santoro, 2020) (corresponding to 6 600 tons per year and 3% of the total brick waste in Denmark¹⁵). This, while currently at EU level is negligible (i.e., 0.08 %), is nevertheless important to be considered for the estimation of the reuse potential.

For the case of gypsum, the literature reports that ca. 10% of the gypsum waste generated in CDW is recycled (Deloitte, 2017). The remaining is assumed to be landfilled. As for mineral insulation materials, stakeholders pointed out that this fraction should not be assumed as part of the 'mineral fraction of CDW', as this would overestimate recycling of mineral wool. For these material fractions, data reported for 2015 by Wiprächtiger et al. (2020) for Switzerland, acknowledging the geographic restriction of the case study, shows a 2% recycling (mineral wool to mineral wool, calculated after the results presented in their material flow analysis), and since mineral wools should not be incinerated given the negligible calorific value, the remaining 98% is here assumed to be landfilled. This estimation is also supported by other evidence, for example from the Flanders where less than 1% recycling is reported (Debacker et al., 2021).


Box 1 shows the share of the management options for the mineral fraction of CDW in the 27 Member States in 2016 and 2018 based on Eurostat data (European Commission, 2021b). Notice that the data reported in Eurostat do not provide further insights into the management of the individual fractions composing the mineral fraction. Additionally, Box 1 includes a summary of the findings from the critical review of the recovery rates of CDW in the EU performed by Moschen-Schimek et al. (2023) concerning quality data and influencing factors. The authors conclude that changes in the definition of the waste management options over time, notably for backfilling, are a key factor to explain the inconsistencies in the reported quantities of recycling, backfilling and disposal. The Commission is already aware of the problems concerning backfilling data reporting and a study was published to support the definition of backfilling enabling a uniform application across Member states (European Commission, 2020c). Figures in Box 1 (year 2016 and 2018) can be compared directly and can be compared also to Figure 4 (year 2020).

¹³ "Incineration with energy recovery" represents waste incineration processes classified as R1 according to 2008/98/EC, Annex II.

¹⁴ "Incineration without energy recovery" represents waste incineration processes classified as D10 according to 2008/98/EC, Annex I.

¹⁵ Calculated using a weigh of a brick of 2.2 kg, and considering the waste brick quantity in Denmark of 212 000 t according to Damgaard et al. (2022).

Figure 4. Treatment of the mineral fraction of CDW in the analysed EU Member States in 2020. Disposal is defined as landfill, incineration without energy recovery and other disposal. Note that data for Ireland 2020 is not available and data from 2018 has been used.

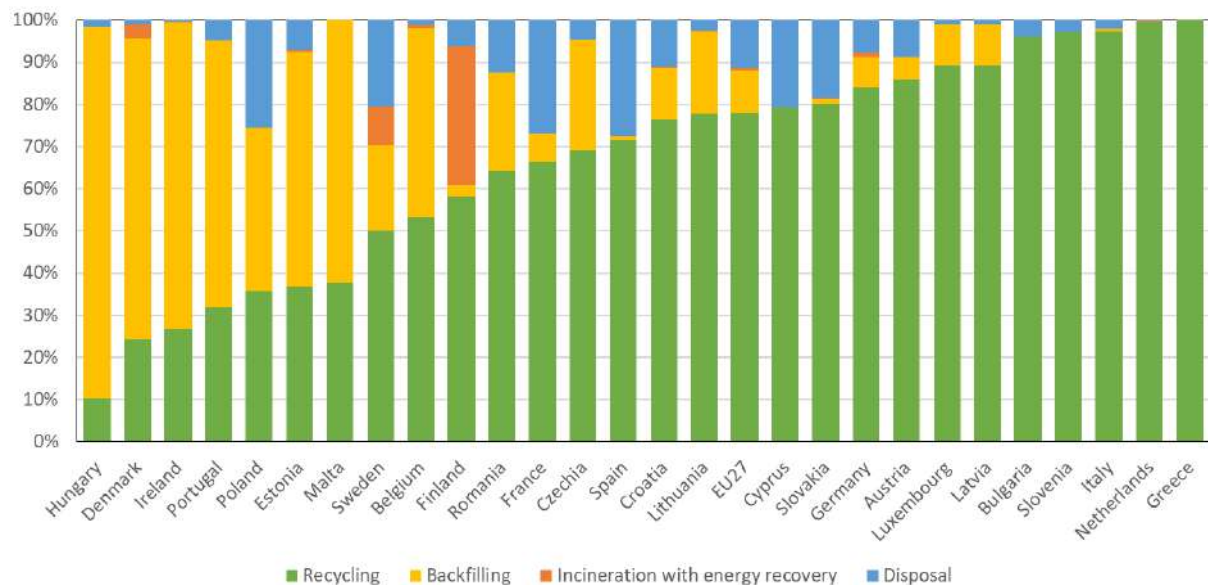

Source: Own elaboration based on data from Eurostat (env_wastrt).

Box 1. Treatment of the CDW mineral fraction: changes observed following the update of the definition of backfilling


Similarly, to 2020 (Figure 4), the predominant management option as an average in EU in 2016 (Figure B1) and 2018 (Figure B2) was recycling (80% and 79%, respectively).

Several countries already reported backfilling as a management option in 2016, thereby complying with Commission Decision 2011/753/EU establishing rules and calculation methods for verifying compliance with the WFD target¹⁶ for CDW. The Commission decision obliged Member States to report the amount of CDW used for backfilling operations separately from the amount of waste prepared for reuse, recycled or used for other material recovery operations. As described earlier the definition of backfilling in Commission Decision 2011/753/EU has been revised in the WFD as of 2018 (2018/851/EU). The revised definition might have been the cause for a decrease in the recycling rates of some Member States as more focus is put on the distinction between recycling and backfilling, and thus more mineral waste could be reported as being backfilled. Such shift in reporting should, however, not interfere with the overall recovery rate, as backfilling is still considered a recovery operation if the criteria of the definition are fulfilled. This might be the case for **Denmark**, that in 2016 reported 0% backfilling and in 2018 reported 66% of mineral CDW backfilled at the expense of recycling that decreased from 89% in 2016 to 30% in 2018. Similar changes happened for other Member States, even if delayed in time, not due to an actual shift in treatment methods, but rather because of the revised definition of backfilling in the 2018 amendment of the WFD, which forced Member States to thoroughly re-consider how CDW is reported. For example, **Hungary** reported a recycling rate of 89% and 92% in 2016 and 2018, respectively, but in 2020 that quantity was reduced to 10%, increasing the reported backfilling from 7% in 2018 to 88% in 2020.

¹⁶ The target set in Article 11(2)(b) of Directive 2008/98/EC reads: “by 2020, the preparing for reuse, recycling and other material recovery, including backfilling operations using waste to substitute other materials, of non-hazardous construction and demolition waste excluding naturally occurring material defined in category 17 05 04 in the list of waste shall be increased to a minimum of 70 % by weight.”


In addition, more clarification on the definitions and instructions on the reporting are still needed. It is observed from the data that some countries changed the reported quantities dramatically from one reporting year to the other between the different management options (including recycling, backfilling and disposal). For example, **Bulgaria** reported in 2016 recycling rates and disposal rates of 89% and 11%, respectively. But in 2018, the rates shift to the opposite (recycling rates of 24% and disposal rates of 76%), just to shift back in 2020 to similar figures as 2016 (recycling rates of 96% and disposal rates of 4%). Greece reported in 2016 recycling rates and disposal rates of 88% and 12%, respectively. But in 2018, the recycling rates were null shifting all to backfilling (97%), just to shift back in 2020 to recycling rates of 100%. Slovakia reported in 2018 recycling rates and disposal rates of 37% and 50%, respectively. But in 2020, the recycling rates increased to 80% and the disposal rates decreased to 19%.

Figure B1. Treatment of the mineral fraction of CDW in the analysed Member States in 2018. Disposal is defined as landfill, incineration without energy recovery and other disposal.

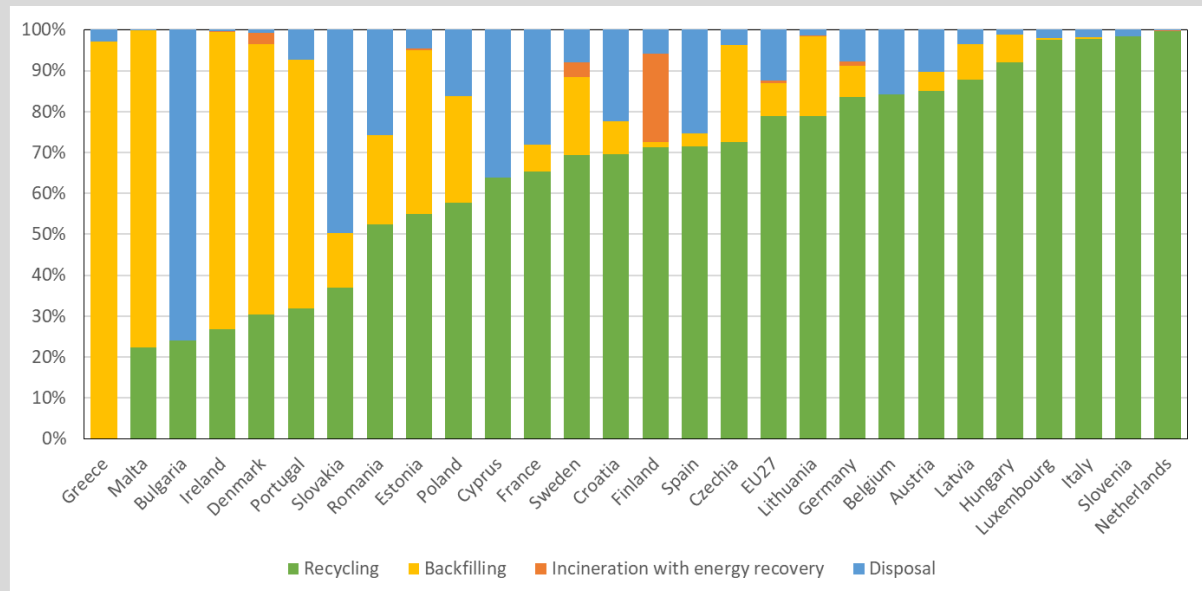

Source: Own elaboration based on data from Eurostat (env_wasrt).

Figure B2. Treatment of the mineral fraction of CDW in the analysed Member States in 2016. Disposal is defined as landfill, incineration without energy recovery and other disposal.

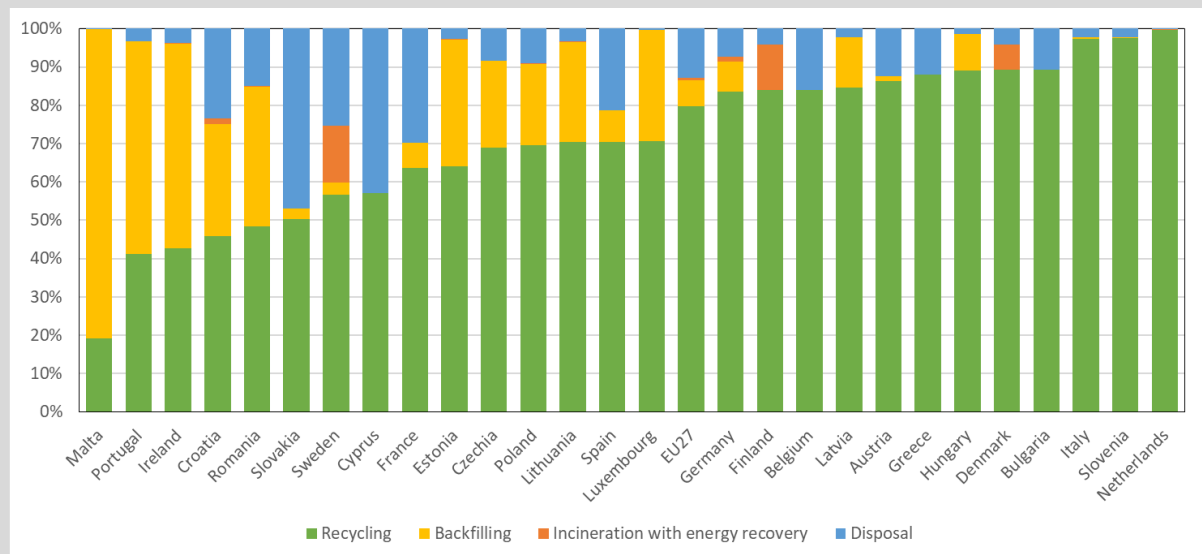

Source: Own elaboration based on data from Eurostat (env_wasrt).

In a critical review on the recovery rates of CDW in the EU from (Moschen-Schimek et al. (2023), the authors investigate, for 12 countries, whether they have achieved a real increase in CDW recovery rate based on technological and legal changes, or whether the increase was due to methodological changes in data reporting, and analyse three potential influencing/limiting factors: a) not harmonized data collection methods in the analysed countries, b) differences in national waste code systems, and c) not harmonized application and insufficient definition of backfilling activities. The study is grounded on the evaluation of the quality reports (between 2012 and 2016) that according to the authors present good quality and can be regarded as a reliable database. The authors conclude that two of the three influencing factors, namely a) and c), are relevant for the meaningfulness in the interpretation of the CDW recovery rates published on Eurostat. Misallocation of waste types to waste codes or treatment activities to treatment operations codes hampers comparisons both inter-European and within one country over time. High growth rates of the recovery rates can be linked to the change of treatment codes (from disposal to backfilling codes), the change of data collection methods and the adjusted allocation of waste streams to the correct waste code.

4.2 Metals, plastic, wood and glass

CDW also contains other fractions besides those listed under the mineral fraction (EWC code W12.1), notably metals, plastic, wood, and glass. As for aluminium management, a study by Delft University of Technology (2004) suggests that aluminium is already largely separated and recycled from CDW (the study suggests that ca. 95% of the aluminium available in CDW was collected for recycling, as of 2004). As for steel, the high market value of steel scrap relative to other materials, make this fraction also being largely separated and recovered from mixed CDW – either during demolition or at subsequent sorting plants treating mixed CDW, in a similar fashion as aluminium. Besides, for both aluminium and steel, a quantity between 5 and 15% is prepared for reuse. Diyamandoglu & Fortuna (2015) reported current practice at EU level as 10% preparing for reuse, 84% recycling and 6% landfill.

As for wood waste, a study by Ramboll (2018) (mainly on wooden windows and doors) reports eight country's specific estimations of the treatment for 2018. There are great variations among them, for example Austria incinerate 100%, Sweden and Germany incinerate 95% with 5% recycled, Italy present 80% recycled and 20% incinerated. Landfill is estimated as 25% for France (40% recycled and 35% incinerated) and 5% for Czechia (40% recycled and 55% incinerated). To calculate an EU average, based on the construction wood waste reported in Eurostat for 2018 and based on the eight country estimations from Ramboll (2018), we perform a weighted average resulting in 73% incinerated, 21% recycled (mainly to particleboard), and 6% landfilled. The recycled quantity is then corrected to 30% following the indications of Deloitte (2017) that has a broader EU27 scope than Ramboll's study (however, estimates are ultimately comparable). Even if some wood could in practice be prepared for reuse, there is no data available for this management option.

Deloitte (2017) further estimates recycling rate of glass waste (to new glass) at 6%, validated by GlassEurope, while not reporting the end treatment of the remaining 94%. A report from Ramboll (2018) provides rough estimates for the treatment of glass waste from windows, suggesting that landfilling is the main management pathway (70%) complemented by recycling (30%). On this basis, we here assumed that 6% is sent to closed loop recycling (glass-to-glass) while the remaining glass waste is split between landfilling (70%) and ending up as foreign material in the production of RA for backfilling (24%). Note that this is an assumption due to lack of specific data, as the RA containing glass could as well be used for road construction and thus reported as recycled.

As for plastic waste, PVC and EPS are by far the main plastic fractions in CDW representing altogether about 80% of the total plastic waste found typically in CDW¹⁷. Concerning EPS, according to 2019 estimates by EUMEPS¹⁸, about 10% was recycled, 66% incinerated and the remaining 24% landfilled. As for PVC, the material flow analysis of the EU PVC cycle by Ciacci et al. (2017) concludes that, for the period 1960-2012, ca. 30% of the PVC waste (from all origins, i.e., construction, packaging, and other sectors) has been collected for recycling, 12% sent directly to incineration and 58% to landfill. Notably, out of the amount collected and sent to recycling, a substantial share is rejected in the recycling process and then sent to incineration or landfill (ca. 30-50% of

¹⁷ These shares are taken from Plastic Europe and used also in the previous JRC report on CDW by (Damgaard et al., 2022).


¹⁸ Data provided to JRC by EUMEPS during an expert workshop held in 2023. Similar data are reported in a presentation power point of a study by BASF (available at <https://www.psloop.eu/wp-content/uploads/2021/01/Conversion-study.pdf>)

the PVC entering recycling) as suggested in the studies from Damgaard et al. (2022) and Ciacci et al. (2017). An overview of the management pathways for all fractions may be found in Table 9.

4.3 Soil waste

For excavated soils, treatment data from Eurostat is also used (env_wastrt; European Commission, 2021c). For 2020, Figure 5 shows the management of the excavated soil fraction (non-hazardous) of CDW in the analysed Member States. It is clear that there is no predominant management option at EU level. Some countries report shares of recycling higher than 80% such as Denmark, Bulgaria, Cyprus, Italy, Lithuania and Netherlands. On the other hand, other countries report negligible recycling shares with either 100% disposal (Malta) or 100% backfilling (Latvia, Slovenia, Ireland). Other countries present high disposal shares for this fraction such as Finland (93%), Austria (66%), and Croatia (46%). As an average, for the EU27 in 2020, the recovery rate of soils (not included in the official recovery rate published by Eurostat) equals about 76%, even if there is no mandatory target for this fraction. However, the quality of this data needs to be further assessed and probably the limiting factors referenced in Box 1 might also apply. According to Moschen-Schimek et al. (2023), some countries such as Bulgaria and Belgium do not report any backfilling activities of soil waste even if those take place. Thus, these amounts are either reported as recovered amounts, are not classified as waste (i.e., they reach an end-of-waste (EoW) status) or they are not reported at all. This is somehow reflected in the validation report of the Eurostat data (Noel et al., 2021) for 2018 that highlights for Bulgaria that there is a significant difference between excavated soil waste generations (74 kt - see Table 2) and reported as treated (only 9%, i.e., 6.4 kt). Other countries, apart from Bulgaria, that reported in 2018 less than 50% of the generated excavated soil waste as treated are Malta (0%), Belgium (25%), Cyprus (44%) and Lithuania (46%).

Figure 5. Treatment of the excavated soil fraction of CDW in the analysed Member States in 2020. Disposal is defined as landfill, incineration without energy recovery and other disposal. Note that data for Ireland 2020 is not available and data from 2018 has been used.

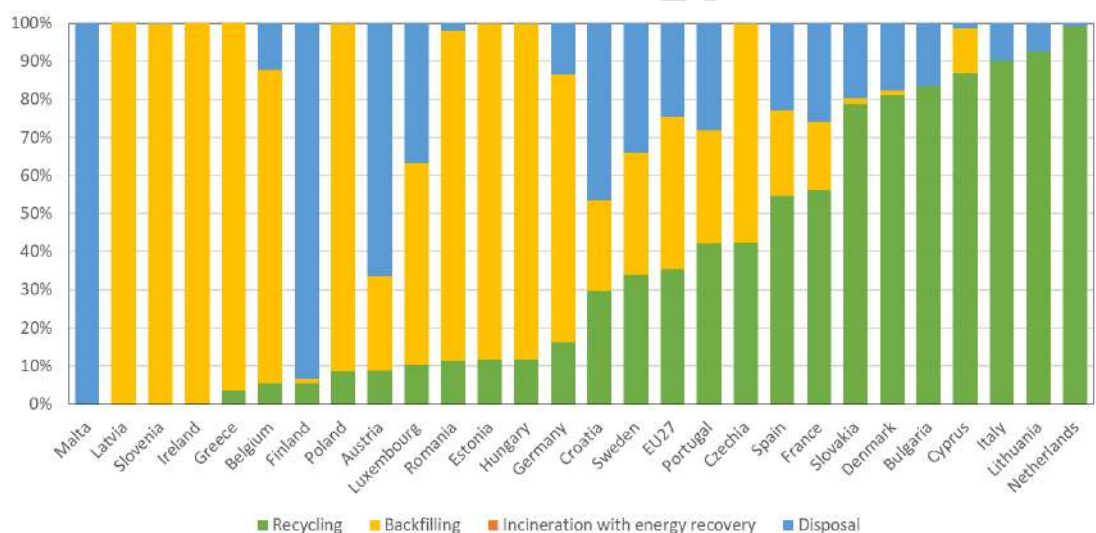


Source: Own elaboration based on data from Eurostat (env_wastrt).

4.4 Dredging spoils

Similarly, for dredging spoil, Figure 6 shows the management data for that fraction of (non-hazardous) CDW in the analysed Member States in 2020. According to the data, there are three countries that recycle 100% of dredging spoils (Bulgaria, Lithuania, and Poland), and Slovakia recycles more than 80%. However, the EU average shows that recycling accounts only for 8%, disposal for 88%, and backfilling for 4%. This is due to the weight of Netherlands where 85% of dredging spoils within the EU are generated and the treatment followed within this country is mainly disposal (98%). The limiting factors referenced in Box 1 might also apply herein. Note that six countries reported no data for this fraction (i.e., Austria, Cyprus, Latvia, Luxembourg, Portugal and Romania). The validation report of the Eurostat data (Noel et al., 2021) for 2018 points out that, in the case of the Netherlands, for some disposal methods such as disposal of dredging spoils at sea (code D6), treatment capacities are less straightforward to determine and thus they have not been determined.

Figure 6. Treatment of the dredging spoil fraction of CDW in the analysed Member States in 2020. Disposal is defined as landfill, incineration without energy recovery and other disposal. Note that data for Ireland and Czechia 2020 is not available and data from 2018 has been used.

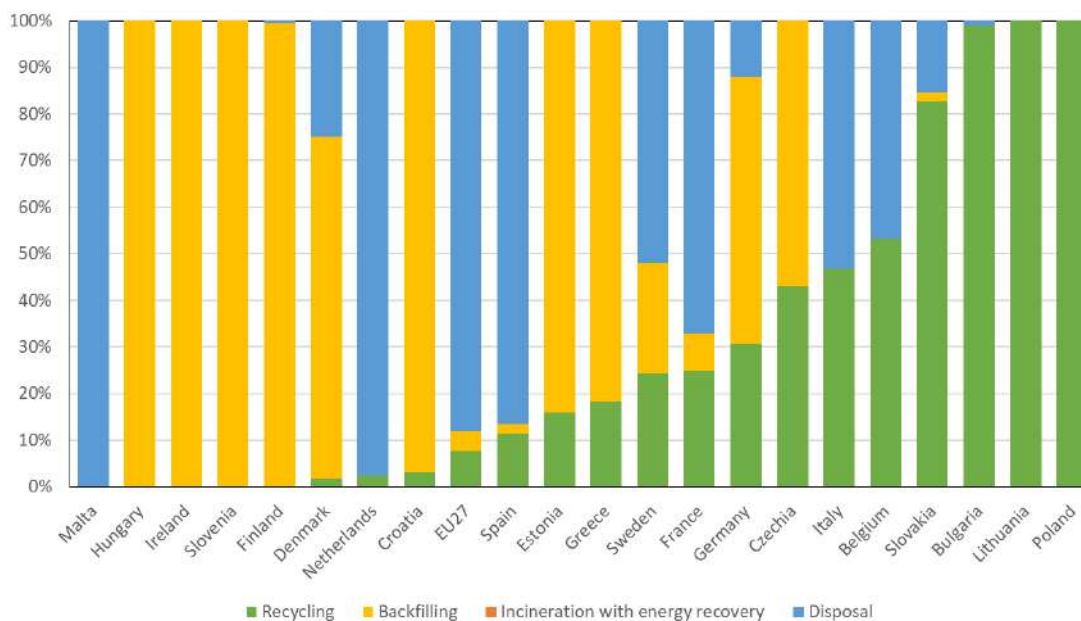

Source: Own elaboration based on data from Eurostat (env_wastrt).

4.5 Overview of current CDW management pathways and recovery rates in EU27

Based on the details provided per each individual material fraction along the whole Section 4, Table 9 summarises the current management pathways in the EU. The overall recovery rate for CDW (based on the mineral waste fraction) as reported to Eurostat (env_wastrt) for the attainment of the WFD CDW recovery target is shown in Table 10. It varies from 63% for Finland to 100% for Malta, Greece and the Netherlands, and equals on average 89% for the EU27 in 2020.

Table 9. Overview of the management pathways for individual material fractions of CDW in the EU estimated for the current situation based on data reported by Member States and on the available techno-scientific literature. Values are rounded.

Material fraction	Preparation for reuse	Recycling	Backfilling	Incineration	Landfilling
Mineral fraction					
Concrete		79%	10%		11%
Bricks		79%	10%		11%
Ceramics and tiles		79%	10%		11%
Insulation material		2%			98%
Gypsum		10%			90%
Metals					
Aluminium	10%	84%			6%
Steel	10%	84%			6%
Plastic					
PVC		30%		12%	58%
EPS		10%		66%	24%

Wood		30%		64%	6%
Glass		6% ⁽¹⁾	24% ⁽²⁾		70%
Soil waste		35%	40%		25%
Dredging spoils		8%	4%		88%

(1) 6% only is estimated to be glass to glass recycling (https://ec.europa.eu/environment/pdf/waste/studies/CDW_Final_Report.pdf).

(2) This is an assumption due to lack of specific data as the RA containing glass could be used for road construction and reported as recycled

Source: Own elaboration – see detailed description and references in section 4.1-to-4.4.

Table 10. Overall recovery rate for CDW across the EU Member States (in %).

	2010	2012	2014	2016	2018	2020
European Union - 27 countries (from 2020)	:	:	87	87	88	89
Belgium	17	18	32	95	97	99
Bulgaria	62	12	96	90	24	96
Czechia	91	91	90	92	:	96
Denmark	:	91	92	90	97	97
Germany	95	94	:	:	93	94
Estonia	96	96	98	97	95	93
Ireland	97	100	100	96	100	:
Greece	0	0	0	88	97	100
Spain	65	84	70	79	75	73
France	66	66	71	71	73	74
Croatia	2	51	69	76	78	89
Italy	97	97	97	98	98	98
Cyprus	0	60	38	57	64	79
Latvia	:	:	92	98	97	99
Lithuania	73	88	92	97	99	98
Luxembourg	98	99	98	100	98	99
Hungary	61	75	86	99	99	98
Malta	16	100	100	100	100	100
Netherlands	100	100	100	100	100	100
Austria	92	92	94	88	90	91

Poland	93	92	96	91	84	74
Portugal	58	84	95	97	93	95
Romania	47	67	65	85	74	88
Slovenia	94	92	98	98	98	97
Slovakia	:	:	54	54	51	81
Finland	5	12	83	87	74	63
Sweden	78	81	55	61	90	74

Source: (Eurostat; env_wastr; CEI, "Circular Economy Indicator WM_040"; accessed May 2023).

CONFIDENTIAL – WORK IN PROGRESS

5. Assessment of environmental and economic impacts of CDW management

5.1 Material and Methods

5.1.1 Goal, scope and functional unit


LCA methodology is applied in accordance with ISO 14040/14044 standards. Besides, ELCC methodology presented in Martinez-Sanchez et al. (2015) is applied to perform both the conventional and societal LCC, the former consisting in a traditional financial assessment and the latter also known as “welfare-economic” assessment that includes marketed goods along with the effects on the welfare of the society caused by externalities (here we only include external cost of the environmental emissions to air, water, and soil). The goal of the study is to assess the environmental and economic impacts of alternative management options for the different fractions of CDW, focusing on preparing for reuse and recycling. To this aim, the functional unit (FU) is the management of one tonne of each individual fraction from CDW. Based on this FU, for each individual waste material fraction we compare alternative waste management pathways; these management and technology pathways do not necessarily produce the same end-products. This is obvious for the case of recycling and landfill or incineration pathways. To credit the reuse or recovery of materials and energy via the alternative EoL management pathways, system expansion is applied as commonly done in waste management LCAs (Ekvall, 2002) and in accordance with ISO 14040/14044 and EF methodology. In line with that method, to quantify the impacts related to the use of a reused product or material (i.e., multi-cycle product or material), the approach put forward in the European standard EN 15804+A2 that set the rules for the product category of construction products, includes an additional phase (module D – benefits and loads beyond the system boundaries) that can be used to assess and express the potential benefits and loads of future loops. This method assumes that the savings from reusing a material are equal to the impact related to the production of the original material (assumed herein coming from virgin sources) minus the impact of the processes required to prepare the product for reuse (e.g., cleaning) (Etienne et al., 2022). This method builds on the assumption that benefits associated to the use of a reused product are more important than benefits associated to the use of a reusable product (i.e., avoiding the production related impact is more relevant than limiting the EoL impact by using a reusable product.). It is necessary to keep in mind that the reusability of a product is hypothetical and cannot be guaranteed when using a product (the benefit is “potential”) while for a reused product, the benefit is certain. Note that system expansion only avoids reuse or recycling from the second cycle: any further cycles are neglected (Malabi Eberhardt et al., 2020). It does not account for topics such as the reference service life, maximum number of reuses, or the impact allocation from the final disposal of the material. Other methods are available in the literature as shown by Allacker et al. (2017) and De Wolf et al. (2020) but no consensus exists.

5.1.2 System boundaries

The general system boundaries of the study are shown in Figure 7. Light-blue dash-dotted squares denote life cycle stages that depending on the scenario might not be needed, dark-blue solid squares are life cycle stages that occur in all scenarios and green dotted squares represent substitution processes that might occur depending on the final output produced. The **generation** stage includes demolition processes that can be either conventional or selective demolition, excavation processes, or dredging processes. The **conditioning** stage includes all processes needed to adequate the wastes generated before the transport or the processing (eg, dewatering processes for dredging spoils). The **transport** stage includes the handling of the material as well as the transport of the input-waste from the generation site to the receiving site or treatment facilities comprising different transport vessels such as lorry, train or barge. Note that this stage is very dependent on the distance, as well as depending on the scenario it might not be needed (e.g., on-site treatment of wastes), and this will be analysed in the sensitivity analysis. The **processing** stage includes preparing for reuse, recycling and recovery operations (depending on the scenario) needed to transform the waste material into a re-usable product or a recyclate and emissions. This stage also includes the landfilling process. Consecutive (subsequent or multiple) use of the reused materials and recyclates has not been taken into consideration in this study. The processing stage also considers further treatment of any non-targeted material fractions separated/recovered during recycling (e.g., metals, when included in the input-waste), as well as the handling of separated non-recyclable material fractions, residues and losses from recycling. Residues and losses from recycling were assumed to be landfilled. The input-waste was assumed to carry no environmental burdens from the respective upstream life cycle stages (that according to the EN 15978 would be from A1 to B7 covering the product stage,

the construction process stage and the use stage), following the common "zero-burden" assumption applied in waste management LCA as the impact of the production are the same across the alternative management scenarios. The assessment was facilitated with the EASETECH software (Clavreul et al., 2014).

Figure 7. General system boundaries of the life cycle assessment and costing. Waste is assumed to be generated burden-free as the upstream impacts of the production would be the same across all management scenarios. All operations involving generation are included (e.g., demolition and conditioning) (blue continuous boxes). System expansion is applied to credit material and energy recovery (green dashed boxes).

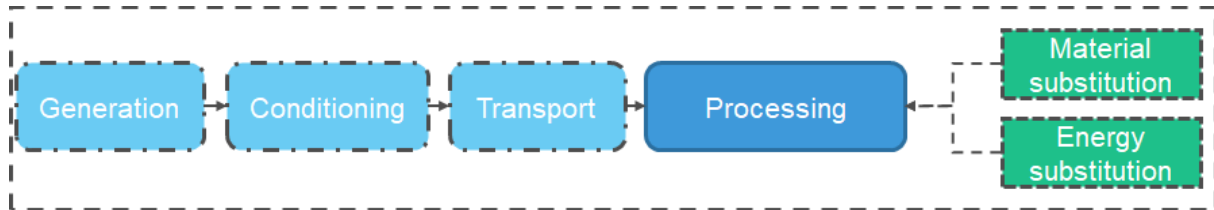

Source: Own elaboration.

5.1.3 Impact categories

The impact assessment was performed for the 16 impact categories included in the product environmental footprint method (Zampori & Pant, 2019). Herein, only **climate change** results are explicitly shown and discussed. The results for the remaining environmental impact categories are summarized in Annex 1 and further reported in Caro et al. (2023) and Cristóbal et al. (forthcoming). Besides, economic impacts were also assessed through ELCC using three main indicators, namely: financial cost that accounts for the annualised cost of capital along with operational expenditures and revenues, external cost that represents the monetisation of environmental emissions (external costs of emissions to air, water, soil; e.g., CO₂ costs), and societal costs that are the sum of financial costs (expressed as shadow prices, i.e., removing taxes and subsidies) and external costs (also expressed as shadow prices).

5.1.4 Scenario definition

The assessment considered five classes of waste management options possible for the different fractions: preparing for reuse (REU), recycling (REC), recovery-backfill (RCB), landfill (LAN), and incineration (INC). Note that for the modelling of some fractions such as excavated soils and dredging spoils, backfilling is similar modelling-wise to preparing for reuse and recycling, respectively, because both pathways substitute materials other than waste (e.g., natural material). The selected scenarios relying on alternative pathways and technologies for treatment of individual CDW material fractions are shown in Table 11. Landfill was considered for all CDW waste fractions, and incineration was considered only for those fractions having positive calorific value. Notice that Table 11 also presents the substitutability factor applied to account for the replacement of primary material via secondary material (reused or recycled) in the market. Substitutability factors are taken from literature and reported in Table 11. This factor considers both the quality of the material and the market demand (Borghi et al., 2018). The former considers the quality of the material in terms of "clean composition" and presence of impurities (through a coefficient named Q_1), as well as the technical characteristics compared to those of the substituted material in relation to the specific application (through a coefficient named Q_2). The market demand considers the ratio between the amount of material sold and produced at the preparing for reuse/recycling/recovery process in a time period (through a coefficient named M). Thus, the substitutability factor is calculated by multiplying the three coefficients (i.e., $Q_1 * Q_2 * M$).

Table 11. Description of the scenarios modelled in this study for the different fractions with details on the life cycle stages and the product substitutability factors (when applicable).

Fraction	Details of the life cycle stage				Substitutability factor	Scenario Code ⁽¹⁾
	Generation	Processing	Products & Outputs	Products substituted		
Concrete (CON)	Selective demolition	Preparing for reuse	Concrete	Concrete	1	REU
	Selective demolition	Recycling	Cementitious material Recycled aggregates	Cement Natural aggregates	0.71 0.85	REC-CEM
	Selective demolition	Recycling	Recycled aggregates	Natural aggregates	0.85	REC-RA
	Conventional demolition	Landfill	-	-	-	LAN
Wood (WOD)	Selective demolition	Preparing for reuse	Wood	Timber	1	REU
	Selective demolition	Recycling	Particleboard	Particle board	1	REC-PBD
	Conventional demolition	Landfill	-	-	-	LAN
	Conventional demolition	Incineration	Electricity & heat	Electricity & heat	1	INC
Steel (STE)	Selective demolition	Preparing for reuse	Steel	Steel	1	REU
	Selective demolition	Recycling	Iron scrap	Iron scrap	0.75	REC-STE
	Conventional demolition ⁽²⁾	Landfill	-	-	-	LAN
Aluminium (ALU)	Selective demolition	Preparing for reuse	Aluminium	Aluminium	1	REU
	Selective demolition	Recycling	Aluminium ingot	Aluminium ingot	0.85	REC-ALU
	Conventional demolition ⁽²⁾	Landfill	-	-	-	LAN
Plastic PVC (PVC)	Selective demolition	Recycling	Polyvinylchloride	Polyvinylchloride	0.69	REC-PVC
	Conventional demolition	Landfill	-	-	-	LAN
	Conventional demolition	Incineration	Electricity & heat	Electricity & heat	1	INC

Plastic EPS (EPS)	Selective demolition	Recycling	Polystyrene	Polystyrene	0.69	REC-EPS
	Conventional demolition	Landfill	-	-	-	LAN
	Conventional demolition	Incineration	Electricity & heat	Electricity & heat	1	INC
Gypsum (GYP)	Conventional demolition	Recycling	Plasterboard	Plasterboard	0.88	REC-GYP
	Conventional demolition	Landfill	-	-	-	LAN
Ceramics&t iles (C&T)	Selective demolition	Preparing for reuse	Ceramic	Ceramic	1	REU
	Selective demolition	Recycling	Cementitious material	Cement	0.71	REC-CEM
	Selective demolition	Recycling	Recycled aggregates	Natural aggregates	0.83	REC-RA
	Conventional demolition	Landfill	-	-	-	LAN
Glass wool (GLW)	Selective demolition	Recycling	Glass wool fibres	Virgin rock	0.83	REC-GLW
	Conventional demolition	Landfill	-	-	-	LAN
Stone wool (STW)	Selective demolition	Recycling	Stone wool fibres	Virgin rock	0.83	REC-STW
	Conventional demolition	Landfill	-	-	-	LAN
Bricks (BRK)	Selective demolition	Preparing for reuse	Brick	Brick	1	REU
	Selective demolition	Recycling	Cementitious material	Cement	0.71	REC-CEM
	Selective demolition	Recycling	Alkali activated blocks	Concrete	0.65	REC-CON
	Selective demolition	Recycling	Recycled aggregates	Natural aggregates	0.83	REC-RA
	Conventional demolition	Landfill	-	-	-	LAN
Glass (GLA)	Selective demolition	Preparing for reuse	Glass	Glass	1	REU
	Selective demolition	Recycling	Flat glass	Flat glass	1	REC-GLA

	Selective demolition	Recycling	Recycled aggregates	Natural aggregates	0.83	REC-RA
	Conventional demolition	Landfill	-	-	-	LAN
Excavated soil and rocks (ESR)	Excavation	Preparing for reuse	Soil	Natural aggregates	0.65	REU-RCB ⁽⁵⁾
	Excavation	Recovery backfill				
	Excavation	Recycling – stabilisation (with lime)	Stabilised soil	Concrete	1	REC-LIM
	Excavation	Recycling – stabilisation (with cement)	Stabilised soil	Concrete	1	REC-CEM
	Excavation	Recycling	Individual components (sand, clay)	Natural sand Natural clay	1	REC-IND
	Excavation	Landfill	-	-	-	LAN
Dredging spoil (DDS)	Dredging	Preparing for Reuse	Dredged sediments	Natural aggregates	1	REU
	Dredging	Recycling (use on land)	Dredged sediments	Natural aggregates	0.75	REC-RCB ⁽³⁾
	Dredging	Recovery backfill				
	Dredging	Recycling – stabilisation (with cement)	Stabilised sediments	Concrete	1	REC-CEM
	Dredging	Recycling	Individual components (sand, clay)	Natural sand Natural clay	1	REC-IND
	Dredging	Landfill (Upland)	-	-	-	LAN

(1) The code is composed of a first set of letters referring to the treatment (e.g. REC=recycling; LAN=landfilling; INC=incineration) and a second set of letters referring to either the eventual material produced in case of recycling (e.g., RA=recycled aggregates; CEM=cement; PBD=particle board; STE=steel; ALU=aluminium) or the used as binder in case of stabilization technique (LIM=lime; CEM=cement).

(2) While the landfilling scenario for metals has been modelled for illustration in the present study, it does not reflect today's reality as metals are mostly recycled.

(3) Complying with the recovery definition in the WFD, the backfilling operation must replace other materials that are not waste. In this sense, for excavated soils, backfill is modelled equally as preparing for reuse (Iacovidou et al, 2020), and for dredging spoils it is modelled as recycling (use on land).

Note: Transport process is included in all scenarios (road transport) while conditioning (dewatering) is only considered for dredging spoils.

Source: Own elaboration.

5.1.5 Inventory

To describe the foreground system, we use the data obtained from the techno-scientific literature on i) waste characterisation (CDW composition and flows), and ii) technologies and processes inventory (energy, electricity, material, fuels and resource provision). For more information about the data used for each scenario listed in Table 11, the reader is referred to Caro et al. (2023) and Cristóbal et al. (forthcoming). Complementary background data for modelling waste treatment technologies were taken from Ecoinvent centre 3.7.1 (Ecoinvent, 2023).

Transport distances from generation site to preparing for reuse/recovering/recycling sites or landfills were assumed to be 50 km (Magnusson et al., 2015; N. Zhang et al., 2020). For other transport processes, for example the transport of soil components (e.g., sand) after recycling, a lower distance of 20 km was assumed following the assumptions of Magnusson et al. (2015). For transport of materials required for management options, e.g., lime or cement for stabilisation, 10 km is used. While shorter or longer distances may occur with different treatment options across the 27 Member States, the same distance was assumed for all scenarios to capture the differences in the performance of individual management technologies rather than focusing on specific regional contexts. However, these assumptions on the distances are tested in a sensitivity analysis. Notice that we considered the volume-limiting factor for transport of voluminous and light material such as EPS using the utilisation rate of the cargo, following the approach explained in Lu et al. (2021) (considering the bulk density of the material and the weight and volume of the cargo). We assumed that conventional demolition preceded incineration, landfill or any recovery operation, while selective demolition was a prerequisite for recycling. The modelling of the two types of demolition involved different energy consumptions and costs (Caro et al.; 2023).

For all scenarios, one or more reference studies were used to model the technologies (see Table 8). Detailed (life cycle) inventories for technologies and processes may be found in separate documents complementing this study (Caro et al.; 2023 and Cristóbal et al.; forthcoming).

5.1.6 Uncertainty propagation analysis

Parameter uncertainty was addressed using uncertainty propagation following the approach suggested in Bisinella et al. (2016). The total uncertainty of a parameter (i.e., of a single data point that is input to the model) is obtained considering both the uncertainty related to the intrinsic variation of the value (e.g., the electricity recovery efficiency at incinerators in EU has a certain range of variation around a mean or likely value) and an additional uncertainty related to the quality of the data itself. The first is assigned to all parameters following a uniform distribution (except for incineration that is triangular) and the range assigned to the parameters is either based on literature, when available, or assumed to be +/- 20%. The additional uncertainty on quality is quantified by means of the Pedigree Matrix using the approach suggested by Ciroth et al. (2016). For the Pedigree Matrix calculation, parameters are grouped in clusters and valued according to five indicators based on the scope of the study: reliability, completeness, temporal correlation, geographical correlation, and further technological correlation.

5.1.7 Sensitivity analyses

On top of the uncertainty propagation analysis, we perform **four sensitivity analyses** specifically on different groups of parameters varying such key parameters *one-at-the-time* to see their effect on the results. The **first** group of parameters is related to transport. Since the key parameter here is the **distance**, three different assumptions are taken. The first one is the base case in which the distance to treatment is assumed to be 50 km (except for dredging spoils where the distance is 10 km for landfilling and 20 km to recovery/recycling). The second is treating the waste in-situ (i.e., transport distance null whenever possible). Note that this in-situ treatment assumes that the treatment plant functions with diesel instead of electricity, and in some cases the generation process is not needed. The third is an increase in the distance of the transport to subsequent treatment/disposal set to 100 km (double the base case). Transport distances for all remaining products (e.g., used for processing) are maintained as in the base case. The **second** group of parameters tested is the **substitutability factors** in the model. These have been halved relative to the value used in the base case (see Table 10). The **third** group is on the use of a **low-carbon energy mix** in line with the upcoming political framework (i.e., year 2050) as reported by (Keramidas et al., 2021). Finally, a specific sensitivity analysis is performed for the **wood waste fraction** introducing the **cascading principle** to see the effects on the results. This sensitivity is performed following the approach of Faraca, Tonini, et al. (2019) that studied the cascade of wood waste. For this analysis, we assume that only high-quality wood waste (Q1 and Q2 of the German classification, see Faraca, Tonini, et al. (2019)) can be used for subsequent cascading applications in


particleboard production. This constitutes ca. 60% of the wood waste generated at each cycle, the rest being sent to incineration for energy recovery. We assume no impacts from use phase and transport in the subsequent life cycles (2nd, 3rd, 4th) considered as we are only interested in the net difference between the incineration and recycling scenario (we assume that both scenarios have same transport and use impacts). We stop at the 4th life cycle, as in Faraca, Tonini, et al. (2019).


5.2 Assessment results

5.2.1 Life cycle assessment results

Figure 8 shows the results for the category climate change for all the scenarios analysed. The contribution breakdown presents the following aggregation: i) generation of the waste (including demolition, excavation, dredging); ii) conditioning processes; iii) transport; iv) processing; v) material recovery; vi) energy recovery.

Figure 8. Characterised climate change results per tonne of CDW fraction managed with breakdown of the contributions in 2020. Values above zero represent burdens, while values below zero represent savings. The final net impact, per each individual category, is the sum of burdens and savings and is represented with a black dot. The error bars represent the standard deviation around the net result. For the abbreviations used please refer to Table 11.

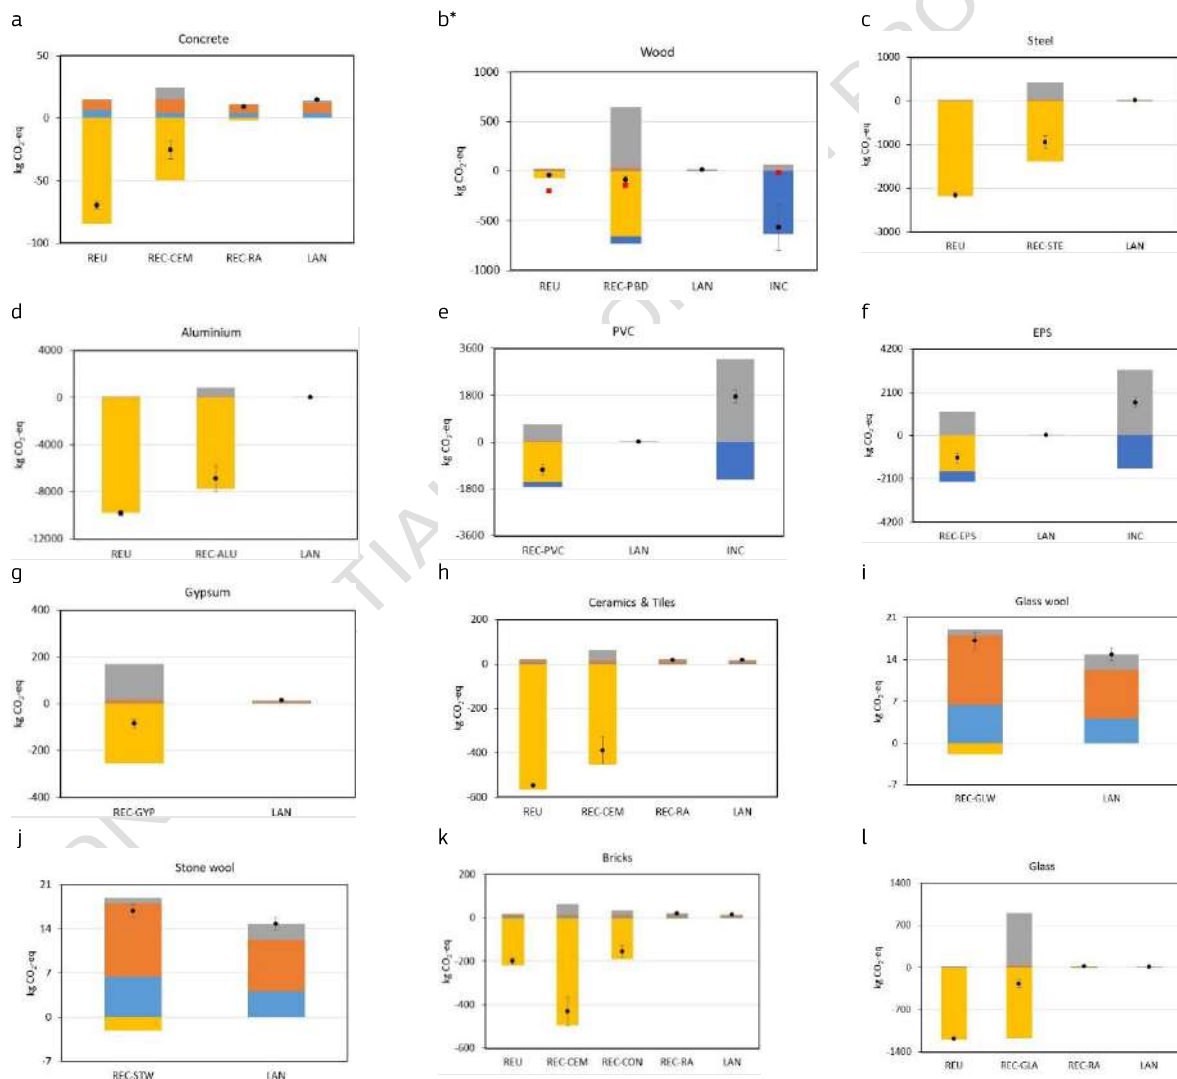

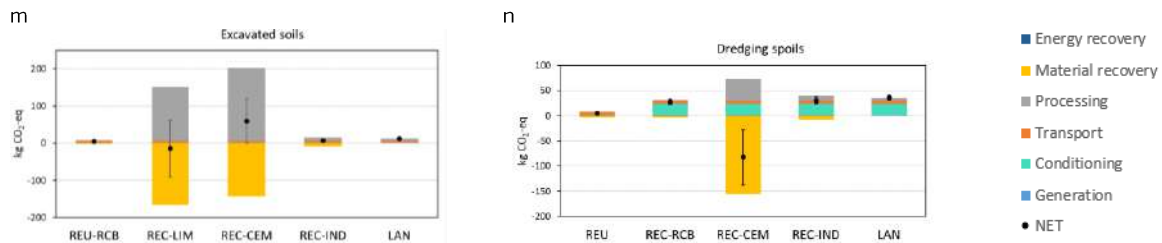

*Note that for wood, it is also represented with a red square (■) the results for the cascading calculation for four cycles.

Source: Own elaboration

On **climate change**, the waste hierarchy is fully respected for nine CDW material fractions, and partially respected for the three fractions that present the incineration option (i.e., PVC and EPS where landfilling performs better than incineration, and wood where incineration performs better than reuse and recycling (only if the cascading is not considered because otherwise the hierarchy is fully respected)). The two fractions that do not follow the waste hierarchy are glass wool and stone wool where landfilling performs better than recycling (see below). Thus, preparing for reuse is the best performing option for almost all fractions that present the option, capitalizing on the low processing impacts and/or on the high savings from material recovery (e.g, 9 770 kg CO₂ eq. t⁻¹ and 2 166 kg CO₂ eq. t⁻¹ for aluminium and steel, respectively). Only for bricks and dredging spoils, a recycling option performs better than preparing for reuse, with the latter the second best performing option.

Thus, for wood (Figure 8b), incineration performs better than preparing for reuse and recycling owing to high energy recovery and low GHG emissions following the carbon neutrality assumption for carbon-biogenic in wood. However, Figure 8b shows that when calculation for cascading is performed, wood results significantly change with preparing for reuse becoming the best option followed by recycling and finally incineration. Although results showed in Figure 8b are calculated by using four cycles of cascading, an inversion of the trend is already observed with only two cycles (see Annex 2 for further info). For stone wool (Figure 8j) and glass wool (Figure 8i), the recycling scenarios offer limited GHG savings. This result can be extended in general to the other material fractions where scenarios producing RA are considered. We observe that recycling to RA is comparable to landfilling, i.e., credits from material recovery are not sufficient to compensate for the burdens of collection, sorting, transport and recycling operations. For instance, recycling of concrete waste to cement (Figure 8a) records a total net GHG saving of 26 kg CO₂ eq. t⁻¹ that is substantially higher than the net burden achieved through recycling concrete to RA (9 kg CO₂ eq. t⁻¹). Another example, the closed-loop recycling producing flat glass from glass waste achieves a total net saving of 272 kg CO₂ eq. t⁻¹ (Figure 8l) substantially higher than the net burden achieved through recycling glass to RA (23 kg CO₂ eq. t⁻¹). The same results are revealed for ceramics/tiles (Figure 8h) and bricks (Figure 8k) where recycling to RA does not result in substantial savings relative to landfilling or incineration.

The highest GHG savings are achieved recycling metals Figure 8c for steel and Figure 8d for aluminium. While this is expected, due to the carbon-intensive production process of these materials and the consequent substantial savings in recycling them, aluminium and steel are already separated and recycled to a large extent owing to their market value. Recycling of EPS (Figure 8f) and PVC (Figure 8e) save 1 088 and 1 058 kg CO₂ eq. t⁻¹, respectively, resulting in a significant reduction of GHG emissions relative to the net burden incurred by landfilling (15 kg CO₂ eq. t⁻¹) and incineration (1605 and 1 747 kg CO₂ eq. t⁻¹ respectively). Recycling gypsum to plasterboard (saving 85 kg CO₂ eq. t⁻¹) performs better than landfilling (net burden of 15 kg CO₂ eq. t⁻¹; Figure 8g). Recycling bricks or concrete to cement also generates important net GHG savings (431 kg CO₂ eq. t⁻¹ and 26 kg CO₂ eq. t⁻¹, respectively) relative to the net burden from landfilling (15 kg CO₂ eq. t⁻¹). However, these scenarios are based on experimental set ups with low TRL and are thus very uncertain.

Across all scenarios investigated, the most important contribution to the climate burdens from recycling is the recycling process (processing) itself, while the most important contribution to the savings is the substitution of materials with a substantial difference between substituting natural aggregates (low savings) and substituting concrete or materials in a closed loop (high savings). However, in scenarios with recycling to RA the contribution of the processing is minor and, in many cases, lower than transport (see concrete, ceramics/tiles, bricks and glass), which becomes the most impacting parameter in the management. In selected recycling pathways also substitution of energy via energy recovery becomes important when CDW is diverted to incineration. This is the case for fractions with high calorific value, i.e., wood, EPS and PVC. For PVC and EPS, however, notwithstanding the energy recovery savings, the overall GHG balance is a net burden (GHG emissions are higher than GHG savings). For incineration, the most important contribution to the burdens is the process itself (combustion and

related emissions), as well as for landfilling (on site operations). The GHG contribution of demolition is negligible compared to the others.

With respect to excavated soils (Figure 8m), the scenario leading to the highest climate benefits was recycling through stabilization with lime that was the only one contributing with net savings (14 kg CO₂ eq. t⁻¹), followed by preparing for reuse/backfilling (burden of 4 kg CO₂ eq. t⁻¹), recycling (burden of 6 kg CO₂ eq. t⁻¹), landfilling (burden of 12 kg CO₂ eq. t⁻¹), and finally recycling through stabilization with cement (burden of 60 kg CO₂ eq. t⁻¹), all of them net burdens. It is important to note that both recycling through stabilization scenarios present very high uncertainty, mainly due to the excavated soil density parameter that influences the quantities of binder added and thus the whole modelling. Across all scenarios, processing (including landfilling) contributes the most to the net impact except for reuse/backfilling where the main contribution is the transport. Specifically, the burdens from recycling through stabilization were driven by the carbon dioxide in the production of the hydrated lime and the cement added as a binder. On the other hand, the main contribution to the savings was the material recovery due to the displacement of natural aggregates and concrete for reuse/backfilling and stabilization with lime scenarios, respectively. The contributions from transport were important for reuse/backfilling and recycling. For the remaining scenarios, albeit not negligible, they were nevertheless small relative to the others. In the same line, contributions from excavation are small comparing to the other processes.


For dredging spoils (Figure 8n), almost all scenarios lead to climate burdens, except for recycling through stabilization with cement with savings of 82 kg CO₂ eq. t⁻¹, followed by preparing for reuse (burden 5 kg CO₂ eq. t⁻¹), backfill (burden 27 kg CO₂ eq. t⁻¹), recycling (burden 30 kg CO₂ eq. t⁻¹) and landfilling (burden 36 kg CO₂ eq. t⁻¹). The main contributions are from conditioning except for the case of stabilization with cement where the main contributions are from the material recovery and processing, being processing contribution also important for landfilling and recycling. The contribution of transport and generation processes are small relative to the others.


Detailed results for the other key impact categories analysed on top of the climate change can be found in Annex 1. The impacts on the other categories, except for ozone depletion, land use and resource use, follow a similar trend to that of climate change with respect to the ranking of the scenarios and the impact contributions.

5.2.2 Environmental life cycle cost results

Figure 9 shows the environmental life cycle conventional (financial) cost results for the scenarios analysed. The contribution breakdown is the same as for the LCA results: i) generation of the waste (including demolition, excavation, dredging); ii) conditioning processes; iii) transport; iv) processing; v) material recovery; vi) energy recovery.

Figure 9. Environmental life cycle cost results per tonne of CDW fraction managed with breakdown of the contributions. Values above zero represent costs, while values below zero represent revenues. The final net impact, per each individual category, is the sum of costs and revenues and is represented with a black dot. The error bars represent the standard deviation around the net result. For the abbreviations used please refer to Table 11.

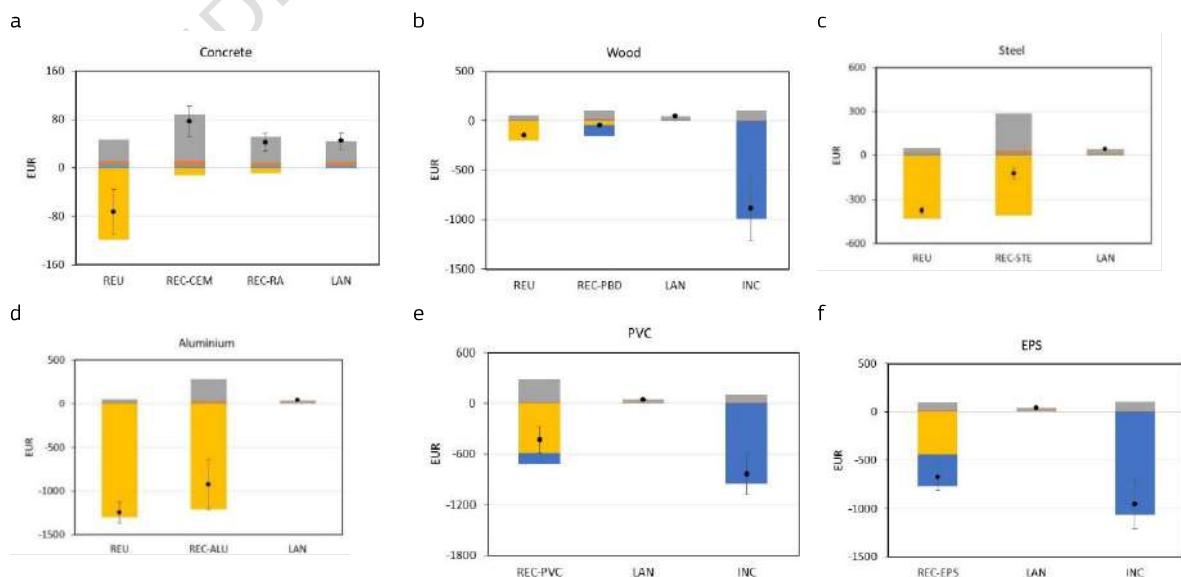

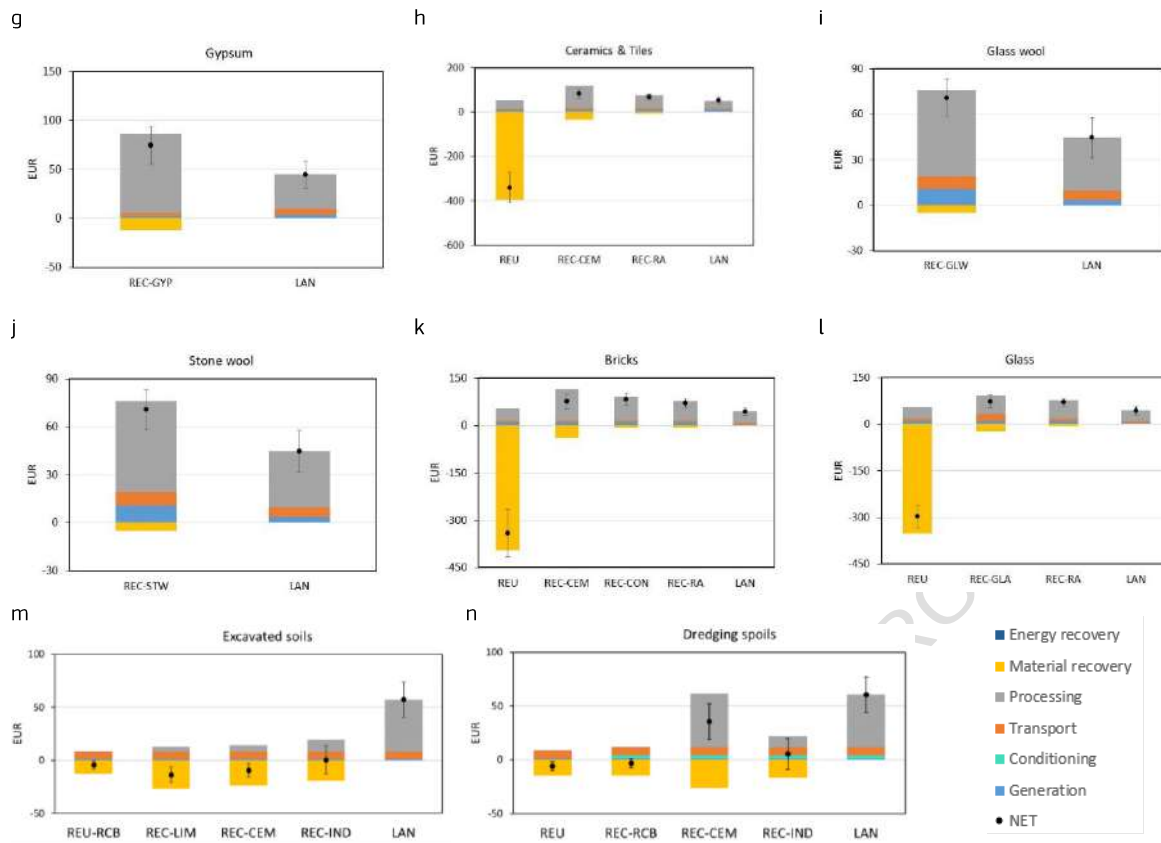

Source: Own elaboration

For the financial costs, preparing for reuse is the best option for almost all fractions that present this option, similarly to the climate change impact, capitalizing on the low processing costs and/or on the high revenues from material recovery (e.g., 1 246 EUR t⁻¹ and 376 ERU t⁻¹ for aluminium and steel, respectively). Only for excavated soils, the recycling through stabilization options performs better than preparing for reuse, being the latter the second-best performing option.

We find that recycling of concrete (Figure 9a), ceramics/tiles (Figure 9h) and bricks (Figure 9k) to cement is more expensive than landfilling (notice that a landfill tax of 19 EUR t⁻¹ is included), as well as for the cost of closed-loop recycling of gypsum to plasterboard and glass to flat glass comparing to landfilling (Figure 9g and Figure 9l, respectively). Recycling of steel (Figure 9c) and aluminium (Figure 9d) expectedly stand out as clearly economically favourable. For plastics, recycling of PVC (net income of 431 EUR t⁻¹) is less costly than landfilling (45 EUR t⁻¹) but more expensive than incineration (net income of 839 EUR t⁻¹). Although an incineration tax is here included (21 EUR t⁻¹), this result is mainly due to the higher revenues obtained from energy recovery via incineration (Figure 9e). Recycling of EPS (net income of 674 EUR t⁻¹) is preferred to landfilling (45 EUR t⁻¹) but still more costly than incineration (net income of 956 EUR t⁻¹; notice that a part of the revenues of recycling comes from energy recovery because of the significant amount of recycling residues incinerated) (Figure 9f). Recycling of stone wool (Figure 9j) and glass wool (Figure 9i) is more expensive than landfilling. Across all scenarios investigated, the most important contribution to the costs is the recycling process itself (processing). Similarly for landfilling and incineration the process is the most expansive stage. The revenues come from the sale of materials and energy.

The scenario with the lowest financial costs for excavated soils (Figure 9m) are recycling through stabilization with lime (net revenues of 14 EUR t⁻¹) and with cement (net revenues of 9 EUR t⁻¹), followed by preparing for reuse/backfilling with net revenues of 0.4 EUR t⁻¹. The recycling scenario presents a net cost of 0.5 EUR t⁻¹, and for the landfilling scenario the net cost equals 57 EUR t⁻¹. The main contribution to the landfilling scenario is the processing (that accounts for the CAPEX and OPEX), as well as the landfill tax mentioned before. For the remaining scenarios, processing contributes to a lower extent, being almost negligible in preparing for reuse/backfilling. Transport processes present a high contribution in preparing for reuse/backfilling scenario and moderated contribution in the rest of them. Contributions from excavation are very low in all scenarios. Finally, revenues come from material recovery.

For dredging spoils (Figure 9n), the lowest financial costs is for preparing for reuse with net income of 6 EUR t⁻¹, followed by recycling for use on land/backfilling with net income of 3 EUR t⁻¹, recycling with net costs of 5 EUR t⁻¹, recycling through stabilization with net costs of 36 EUR t⁻¹, and finally landfilling with costs of 61 EUR t⁻¹. In line with the excavated soils, the main contribution to the landfilling scenario is the processing that accounts for the CAPEX and OPEX, as well as the landfill tax. The main contribution for recycling through stabilization is processing, meanwhile, the material recovery is the main contributor to the total financial cost for recycling for use on land/backfilling, as well as for the recycling scenario. The rest of stages (i.e., generation, conditioning and transport), even if not negligible, their summed contribution is small comparing to the other processes.

Findings reveal that a trade-off between environmental (Figure 8) and economic (Figure 9) impacts seems currently to exist at EU level, since, leaving aside the preparing for reuse, the worst environmental performance often coincides with the cheapest management pathway, for at least concrete, gypsum, ceramic and tiles, bricks, and glass (see Table 12). The results for the societal costs may be consulted at Annex 1. Overall, the societal cost follows a similar trend to that of the financial costs. Recycling pathways significantly reduce the societal costs relative to landfilling.

Table 12. Combination of the results obtained in Figure 8 and Figure 9 reporting the outcome of the net impact on climate change (CC) category and the conventional (financial) environmental life cycle costs (Costs), per each individual fraction and associated management.

Material	Preparing for reuse		Recycling		Landfill		Incineration	
	CC	Costs	CC	Costs	CC	Costs	CC	Costs
Concrete	(1)☺	(1)☺	(2)☹	(3)☹	(3)☹	(2)☹	-	-
Wood	(2)☹	(2)☹	(3)☹	(3)☹	(4)☹	(4)☹	(1)☺	(1)☺
Wood*	(1)☺	(1)☺	(2)☹	(2)☹	(4)☹	(4)☹	(3)☹	(3)☹
Steel	(1)☺	(1)☺	(2)☹	(2)☹	(3)☹	(3)☹	-	-
Aluminium	(1)☺	(1)☺	(2)☹	(2)☹	(3)☹	(3)☹	-	-
Plastic PVC	-	-	(1)☺	(2)☹	(2)☹	(3)☹	(3)☹	(1)☺
Plastic EPS	-	-	(1)☺	(2)☹	(2)☹	(3)☹	(3)☹	(1)☺
Gypsum	-	-	(1)☺	(2)☹	(2)☹	(1)☺	-	-
Ceramics&Tiles	(1)☺	(1)☺	(2)☹	(3)☹	(3)☹	(2)☹	-	-
Glass wool	-	-	(2)☹	(2)☹	(1)☺	(1)☺	-	-
Stone wool	-	-	(2)☹	(2)☹	(1)☺	(1)☺	-	-
Bricks	(2)☹	(1)☺	(1)☺	(3)☹	(3)☹	(2)☹	-	-
Glass	(1)☺	(1)☺	(2)☹	(2)☹	(3)☹	(3)☹	-	-
Excavated soil	(1)☺	(1)☺	(2)☹	(2)☹	(3)☹	(3)☹	-	-
Dredged spoil	(1)☺	(1)☺	(2)☹	(2)☹	(3)☹	(3)☹	-	-

Note: Symbol ☺ along with (1) represents the best performance from a Climate Change and conventional environmental life cycle costs perspective. Symbol ☹ along with (2) represents the second-best performance from a Climate Change or conventional environmental life cycle cost perspective. Finally symbol ☹ along with (3) represents the worst performing management scenario.

*These consider cascading and/or a cleaner energy mix (see sensitivity analysis in section **Error! Reference source not found.**).

Source: Own elaboration

5.2.3 Sensitivity analysis results

This section presents the results of the sensitivity analysis for each of the aspects mentioned before. This is done by comparing impacts of the sensitivity scenario(s) with those of the base case assessment. First, doubling **the distance** to treatment or disposal does not affect the ranking of the scenarios, across all the material fractions investigated. However, it is important to highlight that pathways producing recycled aggregates (REC-RA) are more sensitive to the distance. This is due to a lower relevance of other parameters such as material substitution and processing for this specific recycling pathway. Similarly, applying **in-situ treatments** (only tested on to the excavated soils fraction) does not affect the ranking on climate change and cost.

Regarding the sensitivity on the **substitution factors**, results for climate change impact show that most of the CDW fractions are extremely sensitive to the substitutability factor. However, pathways leading to recycled aggregates (REC-RA), are less sensitive to the substitution factor. This is due to a lower relevance of this parameter for this specific recycling pathway, as the saving contribution from substitution of natural aggregate is indeed limited, making processing and transport relatively more important. For the excavated soils halving the substitution factor leads to a change in the ranking of the scenarios making preparing for reuse/backfill and recycling the best options and recycling through stabilization worse than landfilling. Results on costs show that

halving the substitutability parameters have limited influence on the results and does not affect to the ranking of options.

The sensitivity analysis focusing on a **low-carbon EU energy mix** (i.e., year 2050; based on electricity and heat with higher presence of renewable energies compared to the one of 2020) shows that the influence on the climate change for the scenarios consuming high quantities of electricity (e.g., recycling) or leading to energy recovery (e.g., incineration) is paramount. In general, the performance of energy recovery scenarios is drastically reduced in 2050 because less credits are achieved substituting energy (being this cleaner). Contrarily, the performance of recycling is only partly affected as, while it is true that the impact of the virgin production (substituted via recycling) is reduced, processing impacts associated with recycling technologies also decrease (greener energy used). This is evident for the case of wood waste. For excavated soils, the use of a greener energy mix can foster recycling that would be the best option performing better than preparing for reuse. Since no change in the price of the electricity has been modelled, this aspect would not influence the cost. The results of this sensitivity analysis may be consulted at Annex 2 (Figure A1). Finally, the results on the sensitivity analysis on **wood waste including further cascading** uses have been shown in Figure 8b and commented on section 5.2.1. Further details on the results can be found in Annex 2 - Table A15. We included the analysis of the possible effect of a low-carbon EU energy mix on treating wood waste including further cascading uses as previously commented (see Annex 2 – Table A16).

CONFIDENTIAL – WORK IN PROGRESS

6. Potential for preparing for reuse and recycling in the EU27

Section 6.1 and 6.2 summarize the information available in the techno-scientific literature in respect to recycling and reuse potential for the individual fractions of CDW. The information detailed in these sections is the basis for the assumptions taken to quantify GHG savings and costs associated with increased recycling (scenario named MRP) and increased preparing for reuse and recycling (scenario named MPP) in section 6.3.

6.1 Potential for recycling

The recycle potential of several material fractions has been estimated on the basis of a literature review and stakeholder consultations. The resulting values are collected in Table 13. Below, the assumptions made for each material fraction are explained.

For concrete waste, 100% recycling potential (into RA and/or cementitious materials) appears possible as suggested in Wahlström et al. (2014). We apply this value for further calculations. For wood waste, the literature flags that recycling is possible only for certain types of wood waste (often referred to as high-quality wood waste) and the recycling potential varies therefore between 60% for a case study in Denmark (Faraca, Tonini, et al., 2019) and 44% for a case study in Germany (Höglmeier et al., 2017) out of the total wood waste generated. We apply the latter for further calculations. For steel and aluminium, a total of 99% is suggested from stakeholders (i.e., Metals in Buildings and European Aluminium) as feasible to be collected and sent for preparing for reuse/recycling. For gypsum, recovery rates of up to 95% are reported by Vrancken & Laethem (2000). Similar to concrete, for bricks and ceramic and tiles, a maximum recycling potential of 100% is possible. For glass and insulation materials (i.e., glass wool and stone wool), Mulders (2013) and C. Zhang et al. (2021) report that 100% was sent to recycling in selected case studies in the Netherlands. For PVC waste, Lase et al. (2023 - Table S5) report recycling potential of ca. 90%¹⁹. For EPS waste, while the same authors suggest that 14% recycling is realistically achievable, another study by Conversio reports that in some EU countries EPS recycling from CDW is already happening at rates around 20-27% (e.g., Czechia 27%, Austria 20%; Lindner et al., 2020). We thus assume that this figure is realistically achievable based on best practices/performing countries; therefore, we apply it to our calculations. For excavated soils and dredging spoils, the literature information suggests that 100% recycling is possible. Table 14 summarizes the assumptions on the recycling rates taken for the quantification of GHG savings and costs associated with increased recycling in section 6.3.

6.2 Potential for preparing for reuse

The reuse potential of several material fractions has been estimated on the basis of a literature review and stakeholder consultations. The resulting values are collected in Table 13. Below, the assumptions made for each material fraction are explained; for further details, refer to Pristerà et al. (forthcoming).

Concrete: based on the literature review, it is assumed that only precast concrete can be reused. The amount of precast concrete has therefore been estimated and multiplied by the reuse potential of precast concrete, which, according to Iacovidou & Purnell (2016), is around 50%. Further details on the calculation are available in Table 13.

Wood: as timber can perform a variety of functions within a building, estimating its reuse potential is particularly complex. Even within the context of one specific building element, reuse potential values can sometimes vary from one source to another. Wooden flooring, for instance, has a reuse potential that ranges between around 50% and 85% (Gorgolewski & Ergun, 2013; Iacovidou & Purnell, 2016; Sassi, 2002). Doors have a reuse potential of around 50%, while the number is lower for window frames (<50%) (Gorgolewski & Ergun, 2013). As structural timber represents the highest share of wood in buildings, it has been used in the present report as a proxy to estimate the reuse potential of construction timber as a whole. Several values are available in literature: Höglmeier et al. (2017) estimate a 25% reuse potential based on a 2011 German case study; ARUP (2021) states that a survey conducted in 1998 the UK showed a 30% salvaged wood rate; the Institute for Local Self-Reliance (2006) assumes a reuse potential of 39% in buildings in fair condition and 59% in buildings in good conditions (data relative to the US); finally, Iacovidou & Purnell (2016) estimate reuse potential to

¹⁹ Calculated with the Max transfer coefficients of collection and on-site sorting.

amount to >50%. The study from Höglmeier et al. (2017) was used in the present report, as it provides a precise number, refers to a European country, and is relatively recent.

Steel and aluminium: according to Cooper & Allwood (2012), structural steel alone has a reuse potential of 79% on a global level; however, that value decreases to 38% when considering the total steel content in buildings, and to 29% when taking into account the construction sector as a whole. According to the same source, aluminium has a reuse potential of 50%. These values, which have been used in the present work, are largely in line with the 40% overall reuse potential estimated by way of a stakeholder survey by Hartwell et al. (2021) for building frame materials (i.e., steel and aluminium).

PVC: on the basis of the literature review in general, and Iacovidou & Purnell (2016) in particular, PVC has been assumed to have no potential for reuse, being better suited to recycling.

EPS: based on the literature review, it has been assumed that EPS has not potential for reuse.

Gypsum: as a category, gypsum includes both plaster and plasterboard. The former has no reuse potential. Information on the latter is less well defined. According to Gorgolewski & Ergun (2013) and Iacovidou & Purnell (2016), its reuse potential is “weak” (<50%). Given a variety of other sources indicating that reusing gypsum plasterboard is either not an option, or theoretically but not practically feasible (Klinge et al., 2022; Monier et al., 2011; Pristerà et al., forthcoming; Sandin et al., 2021; Thormark, 2000), the assumption in the present work is that the material has a reuse potential of 0%.

Ceramics & Tiles: there is a distinction to be made between roof and floor tiles. Roof tiles seem to have a higher reuse potential (>50%, according to Iacovidou & Purnell (2016); 60% according to (Blomaard, 2020), though it should be noted that the latter includes both cement and clay tiles), while this value is much lower for ceramic floor tiles (2%, according to Sassi (2002)). However, the share of each of these elements in the corresponding waste fraction is not known. Using stakeholder consultations as a basis, an overall 10% reuse potential has been estimated for this category (further details available in Table 13).

Glass wool and mineral wool: based on the literature review, it has been assumed that glass wool has no potential for reuse. According to Gorgolewski & Ergun (2013) and Iacovidou & Purnell (2016), stone wool has low reuse potential (<50%). However, a variety of other sources indicate that stone wool, and mineral wool in general, has no potential for reuse and is better suited for recycling (Domonkos et al., 2022; NFDC, 2023; Thormark, 2000; WOOL2LOOP, 2020); it has therefore been assumed that the reuse potential of stone wool is also equal to 0%.

Bricks: according to Iacovidou & Purnell (2016), clay bricks bonded with cement mortar have a 0% reuse potential, while those bonded with lime mortar have a high reuse potential (>50%). However, other factors are also to be taken into account in this analysis, such as the size and technical characteristics of the bricks. In order to develop a valid estimate of the reuse potential of bricks at the EU level, stakeholders have been consulted, leading to establishing values for Denmark in particular. These values have then been scaled up as detailed in Table 13.

Glass: according to Gorgolewski & Ergun (2013) and Iacovidou & Purnell (2016), glass has a low reuse potential (<50%); Rota et al. (2023) estimated the reuse potential of insulated glass units at 33%, while according to Hartwell et al. (2021), glazing glass has an average reuse potential of 20%. The latter value has been used in the current work, as it refers to the overall glass content in buildings and is rather recent.

Table 13. Estimation of the share of waste material fraction that can be potentially sent for ‘preparing for reuse’. In column #2, in brackets, we report the percent of material available for reuse preparing for reuse i.e., corrected for process losses.

Material fraction	Potential sent to recycling (% waste recycled)	Reference	Potential sent to preparing for reuse (% waste reused)	Reference
Concrete	100% (100%)	For concrete waste, 100% recycling	13% (13%)	It is assumed that only precast concrete can potentially be reused based on the review of

		potential (into RA and/or cementitious materials) appears possible as suggested in Wahlström et al. (2014).		(Pristerà et al., forthcoming). The precast concrete is calculated based on Business Market Insight ²⁰ that estimate the EU ready mix concrete market value in 2022 as 113 140 million US\$ and the precast concrete market value in 2022 as 29 799 million US\$ (i.e., the share would be equal to ca. 26%). Iacovidou & Purnell (2016) estimate that precast concrete has a reuse potential of around 50%; the overall reuse potential of concrete in buildings is therefore estimated at 13%.
Wood	44% (37%)	For wood waste, the literature flags that recycling is possible only for certain types of wood waste (often referred to as high-quality wood waste) and the recycling potential varies therefore between 60% for a case study in Denmark (Faraca, Tonini, et al., 2019) and 44% for a case study in Germany (Höglmeier et al., 2017) out of the total wood waste generated. We apply the latter for further calculations.	25% (25%)	It is assumed 25% based on the findings of a case study in Germany proposed by Höglmeier et al. (2017).
Steel	99% (83%)	For steel, a total of 99% is suggested from stakeholders (i.e., Metals in Buildings and European Aluminium) as feasible to be collected and sent for recycling.	29% (29%)	Value based on Cooper & Allwood (2012).
Aluminium	99% (92%)	For aluminium, a total of 99% is suggested from stakeholders (i.e., Metals in Buildings and European Aluminium) as	50% (50%)	Value based on Cooper & Allwood (2012), who assessed the potential reuse of aluminium in the construction sector on a global level. As construction technologies do not undergo

²⁰ <https://www.businessmarketinsights.com/reports/europe-precast-concrete-market>

		feasible to be collected and sent for recycling.		significant regional variations with regards to aluminium, it is assumed that the same reuse potential can be applied at the global and European level.
Plastic PVC	90% (78%)	For PVC waste, Lase et al. (2023) report recycling potential of ca. 90%.	0%	It is assumed that reuse is not feasible, based on data from Iacovidou & Purnell (2016).
Plastic EPS	27% (18%)	For EPS waste, while Lase et al. (2023) suggest that 14% recycling is realistically achievable, another study by Conversio reports that in some EU countries EPS recycling from CDW is already happening at rates around 20-27% (e.g., Czechia 27%, Austria 20%; Lindner et al., 2020). We thus assume that this figure is realistically achievable based on best practices/performing countries; therefore, we apply it to our calculations.	0%	It is assumed that reuse is not feasible, based on the analysed literature.
Gypsum	95% (94%)	For gypsum, recovery rates of up to 95% are reported by Vrancken & Laethem (2000).	0%	It is assumed that reuse is not feasible, based on the analysed literature.
Ceramics & Tiles	100% (93%)	Similar to concrete, for ceramic and tiles, a maximum recycling potential of 100% is possible.	10% (7%)	Stakeholders pointed to some niche businesses collecting and preparing for reuse roof tiles. On this basis, knowing the market for ceramics, we calculated that about 10% of the total generated C&T waste consist of roof tiles and be potentially available for preparation for reuse. As for the reuse process itself and related losses, in the absence of specific data, we assume the same process losses as for bricks.
Glass wool	100% (80%)	For insulation materials (i.e., glass wool and stone wool), Mulders (2013) and C.	0%	It is assumed that reuse is not feasible, based on the analysed literature.

		Zhang et al. (2021) report that 100% was sent to recycling in selected case studies in the Netherlands.		
Stone wool	100% (80%)	For insulation materials (i.e., glass wool and stone wool), Mulders (2013) and C. Zhang et al. (2021) report that 100% was sent to recycling in selected case studies in the Netherlands.	0%	It is assumed that reuse is not feasible, based on the analysed literature.
Bricks	100% (93%)	Similar to concrete, for bricks, a maximum recycling potential of 100% is possible.	59% (40%)	To estimate the preparing for reuse potential at EU level, we assume that, similarly to Denmark, solid bricks (in contrast to engineering bricks for non-visual purposes) can be reused in countries with similar building practices as Denmark ²¹ . Relying on the figures from Damgaard et al. (2022; Table F25), the waste brick quantity in EU27 amounts to ca. 8.5 million t from which 53 million t are from the abovementioned countries (i.e., Western Europe), leading to an estimated rate of preparing for reuse . Notice that, out of the total amount that could be sent for preparation for reuse, only a portion is reused. According to stakeholders, after demolition ca. 95% is recovered and sent for preparing for reuse (due to some material breaking), and of this, about 57-65% could be reused as suggested by Douguet & Wagner (2021) and Kancheva & Zaharieva (2023), while 15% of the material sent to preparation for reuse constitute RA of low quality for replacement of natural aggregates (no structural applications) and ca. 20% is mortar for use as RA. Thus, the potential preparing for reuse is 59%.

²¹ Denmark is grouped with Western Europe (including Austria, Belgium, Denmark, France, Germany, Ireland, Luxembourg, the Netherlands) since Danish building practice is considered similar to that of other western EU countries, rather than to that of Nordic countries, based on the observed share of wood waste in the CDW data (according to Damgaard et al. (2022)).

Glass	100% (97%)	For glass, Mulders (2013) and C. Zhang et al. (2021) report that 100% was sent to recycling in selected case studies in the Netherlands.	20% (20%)	Assumption based on Hartwell et al. (2021).
Excavated soil	100% (100%)	For excavated soils and dredging spoils, the literature information suggests that 100% recycling is possible.	100% (100%)	For excavated soils and dredging spoils, it is assumed that 100% could be sent to preparing for reuse with no losses. A demonstration experiment in Høje-Taastrup (Denmark) within the project CityLoops reports that more than 90% of excavated soil is prepared for reuse when developing the area (CityLoops, 2020).
Dredged spoil	100% (100%)		100% (100%)	
Total CDW (weighted average)	96.4% (96%)	Weighted average using data from Table 2 and data within this table.	83% (82.7%)	Weighted average using data from Table 2 and data within this table.
Total CDW (weighted av. – excl excavated soil and dredging spoil)	82% (80%)		15.5% (14%)	

Source: Own elaboration

6.3 GHG savings and costs in increased recycling and preparing for-reuse scenarios

This section explores two scenarios that represent the maximum recycling potential (MRP) and the maximum preparing for reuse potential (MPP) at EU27 level. Both scenarios build on the idea of assessing the maximum potential benefits from increased recycling and preparing for reuse at EU27 level. Thus, in the maximum recycling potential scenario a maximum of recycling is assumed. In the maximum preparing for reuse potential scenario (MPP), the maximum potential for preparing for reuse is assumed whenever this option has been identified as possible for the selected material fraction. When for a selected material preparing for reuse is not a feasible option, it is assumed that a maximum of recycling applies to the same extent as in the MRP scenario (Table 14). In both scenarios, landfilling (of mineral waste) and incineration (of waste with calorific value) are set to a minimum rate to close the mass balance. Backfill operations are also reduced to the minimum possible acknowledging the lower position in the waste hierarchy. To model recycling technologies, both scenarios assume the implementation of the best performing pathways based on the results of the LCA. Financial constraints are not considered.

The potential rates of recycling and preparing for reuse applied in the calculations are summarized in Table 14. Notice that the shares refer to the input to the individual management options (e.g., % sent to preparing for reuse or % sent to recycling). These are then corrected accounting for technical inefficiencies represented by material losses at sorting and recycling stage in the LCA model. The scenarios MRP and MPP are then compared against the baseline (BSL) representing the *status quo* of the CDW management in EU27 in 2020 for each material fraction (the information for the baseline is reported in Table 14, taken from Table 9). By comparing, we can quantify impacts and costs of moving from BSL to MRP and from BSL to MPP, for illustrative purposes.

In order to estimate the environmental impact and cost of shifting from BSL to either MRP or MPP in the EU27, the material flows reported in Table 2 are multiplied by the treatment shares reported for each fraction in the BSL, the MRP and the MPP scenarios (Table 14) and by the climate change impacts calculated in section 5.2.1 and the costs calculated in section 5.2.2 (in kg CO₂-eq. per tonne of managed waste and Euros per tonne of managed waste, respectively). A delta between the impacts or costs of BSL and MRP or MPP is then calculated. Notice that for this estimation we assume that in the scenarios MRP and MPP **only the best performing recycling processes are employed**²² (for concrete, bricks, ceramics and tiles), and for wood the results in the sensitivity analysis considering the cascading effect are used. Instead, in the BSL the current recycling processes aiming at producing only RA are used. Figure 10 and Figure 11 show the marginal abatement cost curve (MACC) for the MRP and the MPP scenarios, respectively. Notice that the impacts and costs of the baseline are accounted for as avoided.

Table 14. Partitioning of the generated CDW across management pathways in the two scenarios analysed (MRP and MPP). The percentage reflects the share of the CDW generated sent to the treatment (e.g., sent to 'preparing for reuse') and not what is considered reused or recycled in practice. However, losses are duly considered in the LCA calculation. CON: concrete; ALU: aluminium; BRK: bricks; C&T: ceramic and tiles; DDS: dredging spoils; EPS: expanded polystyrene; ESR: excavated soil; GLA: glass; GLW: glass wool; GYP: gypsum; INC: incineration; LN: landfilling; PVC: poly vinyl chloride; REC: recycling; RBB: recovery/backfilling; STE: steel; STW: stone wool; WOD: wood.

Fraction	Baseline (BSL)					Maximum Recycling Potential (MRP)					Maximum Preparing for Reuse Potential (MPP)				
	Management pathways %					Management pathways %					Management pathways %				
	REU	REC	RBB	INC	LAN	REU	REC	RBB	INC	LAN	REU	REC	RBB	INC	LAN
CON	0	79	10	0	11	0	100	0	0	0	13	87	0	0	0
WOD	0	30	0	64	6	0	44	0	56	0	25	19	0	56	0
STE	10	84	0	0	6	10	89	0	0	1	29	70	0	0	1
ALU	10	84	0	0	6	10	89	0	0	1	50	49	0	0	1
PVC	0	30	0	12	58	0	90	0	10	0	0	90	0	10	0
EPS	0	10	0	66	24	0	27	0	73	0	0	27	0	73	0
GYP	0	10	0	0	90	0	95	0	0	5	0	95	0	0	5
C&T	0	79	10	0	11	0	100	0	0	0	10	90	0	0	0
GLW	0	2	0	0	98	0	100	0	0	0	0	100	0	0	0
STW	0	2	0	0	98	0	100	0	0	0	0	100	0	0	0
BRK	0	79	10	0	11	0	100	0	0	0	59	41	0	0	0
GLA	0	6	24	0	70	0	100	0	0	0	20	80	0	0	0
ESR	0	35	40	0	25	0	100	0	0	0	100	0	0	0	0
DDS	0	8	4	0	88	0	100	0	0	0	100	0	0	0	0
Total*	0	37	29	0	30	0	96	0	0	0	83	13	0	0	0

²² In the case of excavated soils and dredging spoils, the recycling process to individual materials is selected.


Total (exc. ESR & DDS)*	1	61	8	2	13	1	82	0	2	0	16	67	0	2	0
-------------------------	---	----	---	---	----	---	----	---	---	---	----	----	---	---	---

*Total calculated as weighted average based on the share of each individual material fraction in the total CDW. Note that the partitioning between the management pathways does not sum to 100% because there are some fractions of CDW that have been excluded from the analysis (mainly mixed inert, representing ca. 14%, but also minor fractions such as cardboard, electronics, paint and glue that represent ca. 1% of the total CDW).

Source: Own elaboration

The MACCs represent the quantity of potential savings of GHGs at EU27 level (in Mt) per each fraction and the marginal cost assumed to be constant (EUR per kg of CO₂ eq.). Notice that selected unit-costs are negative because the cost of the baseline is avoided (thus subtracted), which leads to financial savings when shifting from the BL to the MRP and MPP scenarios. Boxes in the x axis represent the different fractions analysed, and the ones above the x axis indicate that there is a net cost of the actions – the higher the box, the higher the cost. For instance, in the MACC of MRP for concrete (see Figure 10), a cost of 1 EUR per t of CO₂ eq. reduced is shown. On the other hand, boxes below the x axis indicate a net saving from that action – this time the lower the box, the greater the saving. For instance, in the MACC of MRP for aluminium (see Figure 10), a saving of 0.14 EUR per kg of CO₂ eq. reduced is observed. This information is then combined with the width of the boxes indicating the action's potential volume of reduction, expressed as Mt of CO₂ eq.

Figure 10. Marginal abatement cost curve for the maximum recycling potential (MRP) scenario. Notice that the impacts and costs of the baseline are accounted for as avoided. DDS: dredging spoils; EPS: expanded polystyrene; ESR: excavated soil; PVC: poly vinyl chloride.

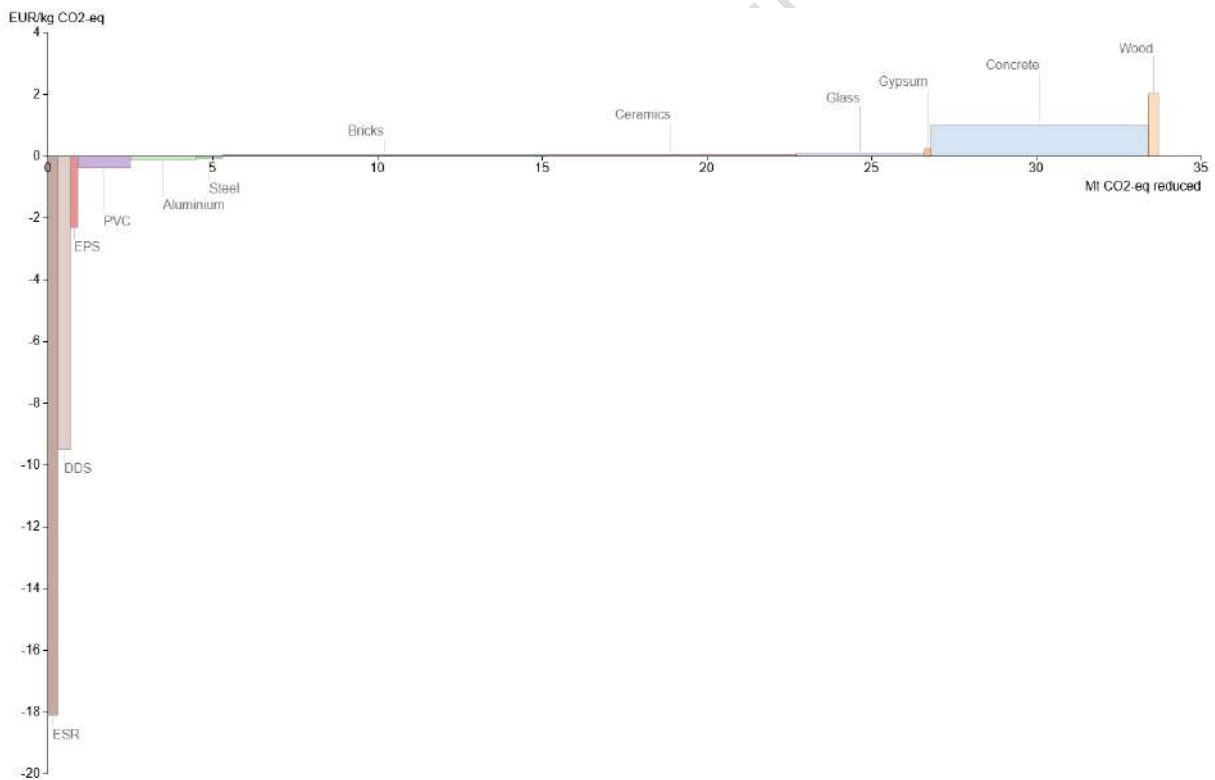


Note that for wood the results for the cascading calculation for four cycles are here considered.

Source: Own elaboration

As shown in Figure 10 for the MRP scenario, the fractions with the highest GHG emission saving potential are the summed inert (bricks, ceramics and tiles, glass, concrete) totalling 27.9 Mt of CO₂ eq.. Concrete could contribute with 6.6 Mt CO₂ eq. at a total cost of 6.5 billion EUR (marginal cost of 1 EUR kg⁻¹ CO₂ eq.). The lowest marginal costs (negative, i.e., a saving) is associated with dredging spoils and excavated soils (leading to total savings of 3.8 and 5.4 billion EUR, respectively), which recycling however incur limited GHG emission saving (i.e., 0.4 and 0.3 Mt of CO₂ eq. in 2020, respectively). Plastics (EPS and PVC) could contribute with 0.2 and 1.6 Mt CO₂ eq. savings respectively, while metals with 2.8 Mt CO₂ eq. (2.0 Mt CO₂ eq. for aluminium and 0.8 Mt CO₂ eq. for steel, both largely recycled already). Overall, accounting for the total (non-hazardous) CDW from buildings,

soil and dredging spoil generation (131 Mt, 444 Mt, and 79 Mt, respectively, totalling 652 Mt), the MRP scenario could lead to a total reduction of ca. 33.7 Mt CO₂ eq. using 2020 waste generation figures and a net cost saving of ca. 2.55 billion EUR. Excluding soil and dredging spoils, for which cost savings are considered highly uncertain, the GHG saving potential is ca. 33 Mt CO₂ eq. at a cost of 6.67 billion EUR (detailed information in Table 15).

Figure 11. Marginal abatement cost curve for the maximum preparing for reuse potential (MPP) scenario. Notice that the impacts and costs of the baseline are accounted for as avoided. DDS: dredging spoils; EPS: expanded polystyrene; ESR: excavated soil; PVC: poly vinyl chloride.

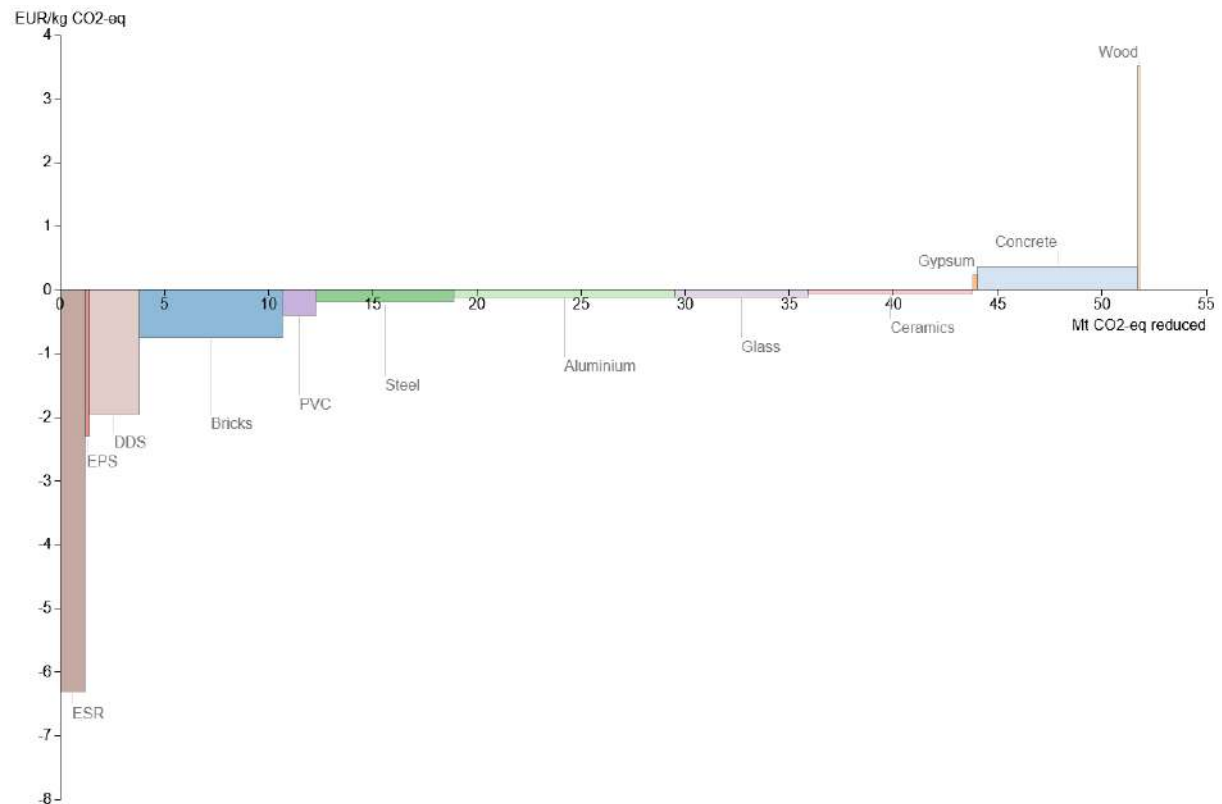

Source: Own elaboration

As shown in Figure 11, for the MPP scenario, the fractions with the highest GHG emission saving potential are the summed inert (bricks, ceramics and tiles, glass, concrete) totalling 28.9 Mt of CO₂ eq.. Concrete could contribute with 7.7 Mt CO₂ eq. at a net cost of 2.8 billion EUR (marginal cost of 0.37 EUR kg⁻¹ CO₂ eq.). The lowest marginal costs (negative, i.e., a saving) is associated with dredging spoils and excavated soils (leading to total savings of 4.7 and 7.6 billion EUR, respectively), which however incur limited GHG emission saving (i.e., 2.4 and 1.2 Mt of CO₂ eq. in 2020, respectively). Plastics (EPS and PVC) could contribute with 0.2 and 1.6 Mt CO₂ eq. savings respectively, while metals with 17.2 Mt CO₂ eq. (10.6 Mt CO₂ eq. for aluminium and 6.6 Mt CO₂ eq. for steel). Overall, accounting for the total (non-hazardous) CDW from buildings, soil and dredging spoil generation (131 Mt, 444 Mt, and 79 Mt, respectively, totalling 652 Mt), the MPP scenario would lead to a total reduction at EU level of ca. 51.5 Mt CO₂ eq. using 2020 waste generation figures and a net cost saving of approximately 19 billion EUR. Excluding soil and dredging spoils, for which cost savings are considered highly uncertain, the GHG saving potential is 47.9 Mt CO₂ eq. leading to savings of 6.76 billion EUR (more detailed information on Table 15).

Table 15. Marginal cost, total GHG emission reductions and total cost for the MPR and MPP scenarios by material fraction.

Fraction	MRP scenario			MPP scenario		
	Marginal cost (EUR kg ⁻¹ CO ₂ eq.)	Total GHG reduction (Mt CO ₂ eq.)	Total cost (M EUR)	Marginal cost (EUR kg ⁻¹ CO ₂ eq.)	Total GHG reduction (Mt CO ₂ eq.)	Total cost (M EUR)
CON	0.98	6.6	6495	0.37	7.7	2840
WOD	2.34	0.3	603	3.51	0.1	352
STE	-0.08	0.8	-61	-0.20	6.6	-1297
ALU	-0.14	2.0	-286	-0.12	10.6	-1239
PVC	-0.39	1.6	-637	-0.39	1.6	-637
EPS	-2.53	0.2	-462	-2.53	0.2	-462
GYP	0.30	0.2	48	0.3	0.2	48
C&T	0.04	7.6	311	-0.06	7.9	-486
GLW	-13.0	-0.002	28	-13.0	-0.002	28
STW	-11.4	-0.002	28	-11.4	-0.002	28
BRK	0.03	9.8	341	-0.76	6.9	-5207
GLA	0.07	3.9	271	-0.11	6.4	-733
ESR	-18.1	0.3	-5434	-6.4	1.2	-7568
DDS	-9.5	0.4	-3800	-2	2.4	-4702
TOTAL	-	33.7	-2557	-	51.5	-19036
TOTAL excl. ESR/DDS	-	33.0	6677	-	47.9	-6766

Note: The totals are calculated assuming the total generation of building CDW (131 Mt), soil (444 Mt) and dredging spoil (79 Mt). CON: concrete; ALU: aluminium; BRK: bricks; C&T: ceramic and tiles; DDS: dredging spoils; EPS: expanded polystyrene; ESR: excavated soil; GLA: glass; GLW: glass wool; GYP: gypsum; PVC: poly vinyl chloride; STE: steel; STW: stone wool; WOD: wood.

Source: Own elaboration.

7. Economic and non-economic market barriers

There are several studies documenting economic and non-economic market barriers for CDW that are potential drivers of market inefficiencies in the literature (Bakas et al., 2019; Di Maria et al., 2020; Ghisellini et al., 2018; López Ruiz et al., 2020; Luciano et al., 2022; Oluleye et al., 2022; Villoria Sáez & Osmani, 2019). The literature review presented in Ghisellini et al. (2018) grouped CDW market barriers into five groups: economic; political; legislative; informative; and managerial. Bakas et al. (2019) explored the Danish market for secondary building materials. Most recently, the European Environment Agency (2022) developed a rubric for measuring well-functioning secondary material markets and applied it to specific waste fractions. These sources and others provide an overview of potential market inefficiencies impacting the private sector uptake of CDW and the expansion of secondary material markets for CDW.

In general, the literature identifies potential market inefficiencies driven by the following widely accepted principles:

- **There is little or no difference between several CDW fractions and their primary material counterparts. Without differentiation, products compete on price and recycled products are often more expensive.** For example, most CDW recycling results in low-value aggregates that compete with low-cost primary raw materials also used as aggregates. The next step of this argument is that prices of primary raw material products do not reflect the full lifecycle costs of pollution generated due to the production and disposal phases of the same products. As recycled products include the cost of recycling, they are disadvantaged.
- **However, doubts remain about the quality of recycled products in comparison to products from primary materials amongst some stakeholders** (Luciano et al., 2022).
- **There is often a disconnection between supply and demand in local markets for specific wastes.** Due to low demand in local markets, firms find it difficult to find customers. The nature of CDW is bulky and heavy. As a result, markets for recycled construction products depend on local or regional factors such as housing and infrastructure growth and local regulation (C. Zhang et al., 2022). Regional and local factors may limit potential customer demand.
- **A lack of information on building composition,** meaning that reuse and recycling strategies may not be apparent until demolition is underway. Without detailed information on the components of the building it is difficult to plan for optimal removal for reuse and recycling (Lederer et al., 2020).
- **A lack of financing needed to employ recycling or advanced recycling.** CDW recycling capacity growth depends on high upfront investment costs. Investment in new capacity is slowed by perceived risk of demand (price signals) (Bakas et al., 2019). Investment risks stem from uncertainty of regulatory framework and uncertainty of supply.
- **Cultural barriers and lack of knowledge on reuse and recycling techniques and capacity to implement** (Bertozzi, 2022; European Environment Agency, 2022). Construction is a profession with entrenched practices that may not include reuse and recycling techniques for demolition. Also, knowledge of and/or perception of low quality for reused and recycling products during the design phase may limit market demand (Oyedele et al., 2014).

However, the literature does not agree on all potential market barriers. Notably, the effect of landfill taxes on CDW management has been studied extensively yet remains contested. The impact of landfill taxes is contested because some researchers find that landfill taxes are drivers of CDW treatment choices and others find that it is not a strong driver of CDW treatment. Villoria Sáez & Osmani (2019) reported that their analysis and several other studies concluded that “there was no correlation between the percentage of CDW landfilled and landfill taxation”. However, regional and municipal studies show that high landfill taxes reduce CDW waste to landfill. In general, the principal that low-cost landfilling disposal options displace recycling options holds. According to several review articles, landfill taxes are an important economic incentive to encourage recycling (Di Maria et al., 2020; López Ruiz et al., 2020; Luciano et al., 2022; Oluleye et al., 2022). Landfill taxes and disposal fees are a driver of recycling, if set appropriately, as well as a potential barrier to recycling if the cost is too low.

Markets for secondary materials depend upon the own-price elasticity of secondary materials. The literature points to low own-price elasticity of demand for many CDW fractions. For example, if own-price elasticity is low, when the price of aluminium goes up the quantity of aluminium would not immediately go

down because it takes time for consumers to find alternatives. In general, in the short run, firms could pass on the cost of investments to consumers.

Is the CDW market well-functioning? It is important to remember that each fraction of CDW has its own related but differentiated market in Europe. These markets have different actors, technologies, barriers and histories. Therefore, it is difficult to generalize findings to all CDW fractions. Longstanding industries such as scrap metal have built-up networks, and management over time that have created a well-functioning market. The EEA's 2022 report, "Investigating Europe's secondary raw material (SRM) markets" illustrates the variation in CDW recycling markets.

"SRM markets exist for many materials (metals, paper, wood, plastics, construction and demolition materials, biomaterials, etc.). Each of these markets is different in terms of its operational characteristics, historical and current developments, degree of closure of its material cycle, business and economic importance. While some markets have been well-established for a long time and are rather successful in providing a stable and relevant contribution to the circular economy, others still suffer from barriers to their further development. This remains the case even when they are targeted by strong waste and recycling policies at the EU and national levels."

(European Environment Agency, 2022)

The EEA's report (European Environment Agency, 2022) establishes that CDW markets have diverse levels of success. For example, aluminium, wood, and aggregates:

- According to the EEA, aluminium has a well-functioning, mature market in Europe today. "Aluminium recycling rates are among the highest compared with those of other materials: in Europe, recycling rates are over 90% in the automotive and building sectors, and 75% for aluminium cans".
- At the same time, wood and aggregates do not currently have well-functioning markets. EEA concludes that the market for wood, "has the potential to be well-functioning. However, wood waste for recycling does not fully meet the criteria for a well-functioning SRM market in terms of the quantities (e.g, the share of SRM with respect to the total market) and the industrial capacity for producing SRM".
- EEA concludes that "the market for aggregate from C&D waste generally does not meet the criteria to be well-functioning... The markets for aggregates exist, the recycling is under-used and varies among Member States".

The results of the recent JRC stakeholder survey by Pacheco et al. (2023) reinforces two themes described in the literature. First, local/regional aspect of CDW markets is relevant to outcomes. Second, stakeholders' perception of quality (fit for use) will influence market outcomes. Pacheco et al. (2023) surveyed stakeholders on the use of recycled aggregates in concrete. They found that stakeholders "strongly support the idea that a major obstacle to the increased market uptake of recycled aggregate concrete is the scarce availability of recycled aggregates fit for use in concrete" (*emphasis added*) (Pacheco et al., 2023). The authors state that, "In countries where recycled aggregate concrete is not produced, the procurement of recycled aggregates adequate for concrete will encounter strong difficulties. - In countries where recycled aggregate concrete is produced (sometimes): attempts to increase the uptake of recycled aggregates by the concrete industry will also face strong challenges in procurement." (Pacheco et al., 2023). The results emphasize the diversity of stakeholder views on a single waste fraction's non-economic market barriers. We may draw from these results that stakeholders of other waste fractions may be similarly diverse.

In summary, enabling measures are important to foster reuse and prevention and improving collection for recycling. Not all CDW fractions currently have well-functioning markets. The economic barriers include inefficient pricing that does not include environmental costs as shown in the ELCC above. The non-economic barriers include the cultural bias against secondary materials and lack of information about the technical qualities slows down demand for secondary materials. As is described in the potential for preparing for reuse and recycling in the EU27 section, both scenarios, MRP and MPP, have the potential to reduce the marginal abatement cost of CO₂ (EUR per kg of CO₂ eq.). The potential environmental benefits cannot be achieved without addressing the economic and non-economic barriers that continue to prevent CDW secondary material markets from becoming well-functioning and scaling up.

8. Limitations of the study and further research

8.1 Limitations related to the quantification of CDW generation and treatment

This study is based on the quantities reported to Eurostat complemented with literature, as detailed in the background study by Damgaard et al. (2022). There are some reporting issues concerning waste generation, notably for soil waste. There are also some reporting issues concerning treatment categories due to the different interpretation of backfilling among Member States. There is need for clarity on basic definitions such as backfilling (see inconsistencies in reporting by the same member state over the years, Box 1). Even if preparing for reuse is a recognised waste treatment category, there is no data within Eurostat. Specific data on the amounts sent for preparing for reuse is needed to compare the *status quo* of this management option against its full potential.

8.2 Limitations related to excavated soils and dredging spoils

Excavated soils and dredging spoils are usually excluded from CDW studies since they do not count for the recovery rate imposed on the WFD. One of the main limitations of this study is the lack of data and the uncertainty associated with these two fractions. Concerning the modelling, the composition of natural constituents and possible contaminants of excavated soil waste and dredging spoils is variable and case dependent. General values have been used within this study and the uncertainty has been solved herein through uncertainty analysis to account for it, but it should be considered case-by-case. For soils, at European level, the European Soil Data Centre (ESDAC) hosted by the European Commission's Joint Research Centre (JRC), is the focal point for soil data, and within the Land Use and Cover Survey (LUCAS) soil module datasets are available including particle size distribution at EU level, as well as coarse fragments (Panagos et al., 2022). Thus, soil coarse-, sand-, silt- and clay content is measured (in %) in the samples of topsoil (0-20 cm) of the LUCAS database in 2009 for 23 Member States (one of them is the UK, no longer a Member State) and then extrapolated to the full extent of the EU. Samples from Bulgaria and Romania were in 2012 sampled and included in the database (Tóth et al., 2013). In this study it is assumed that the subsoil has the same characteristics as the topsoil. A possible option to estimate data for the subsoil would be identify the type of soil (e.g., Cambisol, Histosol) from LUCAS and estimate the grain distribution based on that, as well as for the bulk density. For dredging spoils, there is no data at EU level of material composition that can differ from soils being usually dominated by silt and clay fractions (accounting for 60-90% of the solid content). In this study data from a case study in Sweden (Ferrans et al., 2019) is used to characterize EU dredging spoils.

Possible storage, as well as administrative and operational cost for material analysis has not been considered herein, thus maybe underestimating the real cost of management options. For all soil waste removals, a soil classification test to accurately assess contamination levels is needed. If the management option selected is landfill, probably a Waste Acceptance Criteria test is carried out to determine which type of landfill. On the other hand, for reuse, recovery and recycle options to achieve the EoW criteria, different analysis on the technical criteria of the final use must be conducted.

The savings and burdens associated with the recycling through stabilization for soils and dredging spoils (either using cement or lime) are based on recipes from literature that calculates the quantity of binder depending on the characteristics of the soil or dredged spoils. As mentioned already in this section, this is very uncertain and has been somehow captured with the uncertainty analysis performed, but due to the great variability of the results, those options have not been considered in the calculation of the potential at EU level. More clarity is needed concerning this management pathway since it is not clear if it is commonly applied (a specific question on the survey to stakeholders was done concerning that and half of the respondents said that it is not commonly applied), as well as on how to report these quantities of treated soil to Eurostat. Furthermore, some stakeholders rose the attention to a possible long-term impact on the soil that should be further assessed.

For the potential for preparing for reuse and recycling in the EU27, since no data for excavated soils and dredging spoils was available, it is assumed 100% potential in both cases, something not fully realistic but somehow showing the full potential of these two, usually, undervalued fractions. The recycling option to individual fractions is the selected option for the potential scenarios, even if as stated by the stakeholders this option is rarely done due to economic constraints. Within the scenarios, small increases in quantities treated through preparing for reuse and recycling lead to big differences in the marginal costs (acknowledging the probable underestimation of those cost treatments comparing to landfilling as mentioned before) and thus to great savings in the total costs. For that reason, the total numbers for both scenarios MRP and MPP concerning excavated soils and dredging spoils should therefore be taken with care.

8.3 Limitations related to the environmental and economic assessment

The savings associated with the recycling of concrete into recycled aggregate (RA) of high-quality (e.g., for use in structural concrete) and of low-quality (e.g., for road sub-base or backfilling) are the same as in both cases we assume the replacement of natural gravel (no specific data available). While this should be improved, it is anticipated not to change significantly the overall environmental savings due to the very low impact of the extraction and processing of natural aggregates.

The savings associated with the recycling of bricks and ceramics/tiles into cementitious materials (scenarios named REC-CEM for each fraction) are uncertain as they are based on the process described in a single publication (Fořt & Černý, 2020). We could not prove the existence of a proven technology and market for this pathway. The related environmental savings of this recycling pathway are based on the assumptions taken following the study abovementioned and should therefore be taken with care.

The estimation of the potential share of waste material that could be subject to 'preparing for reuse' is highly uncertain (Table 13) as it is based on few sources, notably case studies, or authors' estimates. The same likewise applies to the environmental and economic savings associated with 'preparing for reuse' scenarios. The 'preparing for reuse' scenarios that were included in this study following a specific request of the stakeholders' consultation, are to be considered as illustrative and should be used with care. The only preparing for reuse scenarios for which the authors could prove the existence of established processing technologies and market is the case of metal (stakeholders suggested that 5-15% of the waste generated is currently sent to preparing for reuse) and solid bricks in Denmark. For the latter, ca. 3 million bricks are estimated to be currently processed annually for reuse while the total potential for reuse was estimated at 47 million bricks in previous studies²³.

The data used to represent the costs of recycling and the price of recycled materials were taken from literature, except for the case of reused bricks, and are thus subject to significant uncertainties. While we transparently reported sources (see Supplementary Information of Caro et al., 2023 for details) and strived to address uncertainties using state-the-art techniques, the specific magnitude of the (environmental life cycle costing) results should be used with care. Nevertheless, we believe that the resulting costs of the scenarios investigated are robust enough to show tendencies and ranking between the different management scenarios (incineration, landfilling and the multiple recycling pathways assessed), e.g., to flag whether a selected recycling pathway is not competitive economically under given costs and prices.

²³Based on feedback from the stakeholder consultations (specific meetings with Danish companies operating in the business of solid bricks reuse were held to get further insights into the reuse operations and market in Denmark and the potential at the EU27 level).

9. Stakeholder Consultation

This section provides an overview of the stakeholder consultation process and results. In the course of preparation of this report, JRC actively sought stakeholder feedback through three channels:

- 1) Stakeholder review of the draft report;
- 2) Stakeholder workshop on the techno-economic and environmental assessment of construction and demolition waste management on July 21, 2023; and
- 3) Stakeholder survey, open for more than thirty days, until July 28, 2023.

The stakeholders were invited to participate in these communication channels via direct emails based on a list of stakeholders maintained by the JRC Circular Economy and Industrial Leadership Unit.

The following sections summarise the results and impact of the stakeholder consultation.

9.1 Dialogue on the techno-economic and environmental assessment report and workshop with stakeholders

Self-declared stakeholders were provided a draft of the report and a new survey before the workshop. Stakeholders had the opportunity to comment on the report directly through the survey app, during the workshop, or through direct email. Several stakeholders flagged new data sources and provided their own data to the Commission.

Also, the literature review by Damgaard et al. (2022), which informed the characterisation of CDW in the report, includes country-specific data from a separate stakeholder consultation.

The workshop with stakeholders on June 21, 2023, attracted approximately 60 stakeholders. Stakeholders who participated in the workshop called for coordination between Commission initiatives, including waste prevention, end of waste, and the EU Taxonomy. In addition, clarification was sought on specific scenarios, for example EoL scenarios (notably stakeholders asked to add 'reuse' for selected fractions), increasing demand for low carbon products and closed-loop recycling options rather than downcycling. Further, questions were asked about the greenhouse gas emissions calculated for wood. There were three overall threads that ran through the stakeholder's discussion.

- The lack of well-functioning markets for CDW products at prices that support uptake of CDW at scale for all fractions. The need to address economic and non-economic market barriers. Consumer information that highlights specifications and benefits of recycled and primary material products was noted by stakeholders.
- The need to distinguish between quality of CDW for recycling as high quality (with the meaning of meeting specifications of non-recycled products to be substituted) versus low quality (with the meaning of downcycling) in future work.
- The need for regulatory coordination at the MS and EU level was mentioned, with examples of new MS initiatives on CDW in Denmark, Spain, and Austria.

Finally, stakeholders linked the waste discussion to products from primary and secondary resources. In summary, stakeholders would like to see the Commission present a holistic perspective across the value chain that incorporates product design of the products on the market such that secondary materials and primary materials are on an equal footing.

9.2 Stakeholder Survey Results

The survey received 24 respondents of whom 88% were industry organisations, 4% were non-governmental organisations, 4% were research organisations, and 4% non-profit organisations.

The survey comprised five yes/no questions on the techno-economic assessment (see Table 16). The questions focused on topics that were not fully described in the literature, or the authors suspect that current practice is different than the literature indicated. Specifically, the questions concerned the composition of excavated soils, dredging spoils, and infrastructure waste, recycling technologies for CDW, relationships between excavated soils/dredging spoils, their recovery via stabilisation, and their use in agriculture, environmental impacts from the recycling life cycle stage. The average percentage of respondents that answered individual questions was 69%.

Although the percentage of respondents for every question was not above 50 percent, the survey tool was successful in eliciting additional data. Stakeholders provided additional data for four out of five questions. Question number 2, “Is the description in section 4 of the background document covering the main recycling technologies for CDW or are there any additional innovative or emerging technologies that could play a role in the near future (2023-2035)?” elicited the most feedback. Stakeholders contributed data for recycling technologies of concrete, bricks, ceramics, mineral wool, glass, gypsum, metals, and plastics and the preparing for reuse of CDW.

Most survey respondents (100% response) were interested in the generation and composition of excavated soils, dredging spoils and infrastructure waste while the relationship between agriculture and excavated and dredging spoil was the topic with less answers (33%) since respondents focused on areas where they felt most comfortable with their knowledge.

The survey results are informative for the current study; however, given the small number of survey respondents, the results are not statistically significant for the entire EU. Rather, the results reflect expert industry and municipal knowledge on the topic.

Table 16. Template for questions within the survey and the statistics of the results obtained.

Questions	Percentage of Survey Respondents that answered the question	Percentage of Question Respondents that answered Yes	Percentage of Question Respondents that answered No	Did Respondents provide additional data? Yes or No
1. Are you aware of any (additional) data on the generation and composition of excavated soils, dredging spoils and infrastructure waste	100%	17%	83%	Y
2. Is the description in section 4 of the background document covering the main recycling technologies for CDW or are there any additional innovative or emerging technologies that could play a role in the near future (2023-2035)?	88%	48%	52%	Y
3. Based on your knowledge, is recovery via stabilization (with lime or cement) a commonly applied pathway for excavated soils and dredging spoils?	38%	55%	45%	N
4. Based on your knowledge, is use in agriculture a commonly applied pathway for excavated soils and dredging spoil?	33%	50%	50%	Y
5. Would you be able to provide additional data to update the environmental impacts from the recycling stage in the life cycle assessment models used, and if so, would you be available to be contacted by JRC to form part of a technical working subgroup on LCA/ELCC?	88%	52%	48%	Y

Source: Own elaboration

9.3 Stakeholder impact on final report

As a result of the workshop and survey, additional dialogues were initiated between the authors and stakeholders with expertise to share with JRC (see Table 17). These meetings were held on a rolling basis from spring 2023 until closing the final report. Follow-ups actions resulted in changes in the report, particularly for the waste characterisation and life cycle inventory data. JRC follow ups to Stakeholders led to the reviewing of Sections 2, 3 and 5. The impact of stakeholder's comments is summarised in Table 17. The authors are thankful for the data and information provided by the stakeholders that improved the final report.

Table 17. Bilateral dialogues between JRC and stakeholders.

Date of Meeting / Contact / Visit	Stakeholder's Name and Organisation	Topic	Did follow-up meeting result in changes in the report (data, or facts)?
07/07/2023 (Possible visit to their premises in Fall 2023)	HERCAL	CDW – mineral fraction. Treatment routes focused on concrete recycling and products obtained.	Refinement of information on the technologies and processes for concrete waste management.
04/08/2023	Concrete Europe	Infrastructure waste	Refinement of information on the generation and composition of infrastructure waste.
07/09/2023	DTI	Preparation for reuse of construction products.	Provided an overview of preparing for reuse of CDW materials and provided a contact with companies preparing for reuse bricks within Denmark. Expanded the reuse section in the final report.
17/09/2023	ECOS	CDW – insulation materials. Recycling quantities.	Refinement of information concerning the management of insulation material at EU level.
20/09/2023	Euro Panels	CDW - wood fraction. Carbon neutrality assumption and cascading principle.	Inclusion of sensitivity analyses on wood CDW accounting for the cascade cycle and future cleaner energy mix.
29/09/2023	Gamle Musler	CDW – brick fraction. Preparing for reuse of bricks in Denmark.	Refinement of information on the technologies and processes for bricks waste management and the reuse potential.

Source: Own elaboration.

10. Conclusions

EU waste legislation is driving improvements towards environmentally sound management of waste and spurring its contribution to the circular economy. As CDW represents more than one third of the waste generated in the EU27, this study focuses on the current management and related environmental and economic implications of CDW. We do this by identifying current and potential management options for all individual fractions of CDW (preparing for reuse, recycling, recovery, incineration and landfilling) and performing an in-depth techno-economic and environmental assessment of these management options. The study further provides an outlook of the potential for preparing for reuse and recycling at the material fraction level and summarizes the main economic and market barriers based on the available literature. In conclusion, this study lays the scientific groundwork for the European Commission's consideration of possible objectives and other measures designed to improve the management of CDW in the EU27.

The **life cycle assessment** results for the impact category **climate change** indicate that recycling is the option incurring the highest GHG savings, when assuming the use of best-performing recycling technologies. Landfilling (or incineration when applicable) incurs the highest GHG burdens for all individual material fractions except for wood and mineral wool waste. When assuming the use of recycling processes that produce only recycled aggregates, savings from recycling are often comparable to (or only slightly better than) landfilling. The reason is that the GHG savings connected to avoiding natural material extraction and processing (gravel, sand) are limited. For the material fractions, mineral wool and wood waste, the results are different. Specifically, for glass wool and stone wool waste, landfilling performs comparable to recycling due to the limited GHG savings associated with the replacement of natural materials otherwise used in the mineral wool production process. For wood waste, incineration incurs higher GHG savings than recycling when cascading cycles are not accounted for and when considering the current EU energy mix for the calculations. These results are heavily affected by the following: i) biogenic CO₂ released from wood waste incineration is considered neutral with respect to climate change (i.e., no impact); ii) we only accounted for a single life cycle (i.e., no cascading cycles); and iii) we assumed the current EU energy mix. A sensitivity analysis on the wood case including cascading cycles shows that wood waste recycling (same for reuse) is preferable to incineration when a second cascading loop is included. Also, when accounting for a future cleaner EU energy mix, this gap further increases in favour of recycling (or reuse). These results highlight the importance of considering multiple cycles for the case of wood and the future EU energy mix. While one could also take a detailed look at the benefits from biogenic carbon storage (delayed emissions) and avoiding land use changes connected with the timber demand, this was out of the scope of the present analysis. It is understood that more data on biogenic carbon storage and land use change would further favour wood recycling over energy recovery options. For plastic waste (PVC and EPS), while recycling is the preferred option from a GHG reduction perspective, landfilling performs better than incineration due to the release of GHG upon incinerating the plastic, which is not compensated by the GHG savings from energy recovery²⁴. For excavated soils and dredging spoils, preparing for reuse, recycling and recovery (backfilling) management options perform better than landfilling albeit overall GHG savings are limited for the same reasons as explained earlier for natural aggregates replacement. Notice that the remaining impact categories generally follow a similar trend to that of climate change with respect to the ranking of the management scenarios.

The **conventional** (i.e., financial) **environmental life cycle costing** results indicate that landfilling, when including landfill tax, is the worst economic option for half of the waste material fractions considered. For the other half, the financial cost of landfilling is simply cheaper. More advanced recycling pathways for concrete, ceramic and tiles, and bricks (to cement and aggregates) are (with data currently available) clearly more expensive than landfilling, mainly due to the processing costs albeit also the cost increase due to selective demolition is relevant. However, even simpler recycling processing producing only recycled aggregates appear to have comparable costs to landfilling overall and are thus in close competition with landfilling economically. Incineration, whenever applicable, is the most convenient option economically (with net income) due to the significant revenues from energy recovery. This is the case for plastic and wood waste owing to the high calorific value. It is important to note that when external costs are accounted for via **societal life cycle costing** recycling pathways significantly reduce the societal costs relative to landfilling and incineration (plastics, notably, due to the CO₂ emission cost). In conclusion, although the financial cost of recycling is higher than landfilling for concrete, gypsum, ceramic and tiles, glass wool, stone wool, brick and glass and higher than

²⁴ Given the assumptions in terms of average electricity and heat recovery in EU incinerators (15% and 40%, respectively) and without considering Carbon Capture and Storage.

incineration for wood, PVC, and EPS, the societal cost is lower when including externalities (for plastic waste always; for wood waste when cascading uses are considered). This means that landfilling and incineration are more costly options for society and should be further discouraged. It should be noted that our results in terms of conventional (financial) costs are based on average figures and, therefore, should not be considered representative of the situation in all member states. In particular, we apply a landfill tax for inert waste of 19 EUR t⁻¹, the average for EU27 based on the data available from a current report of the European Environment Agency. However, some member states apply much higher rates (up to 100 EUR t⁻¹ or more, e.g. see the Netherlands) and this has been proven to have important implications in terms of waste diversion from landfill and increased recycling.

The study further explores the potential for recycling and preparation for reuse for each individual material fraction of CDW. The figures are based on a review of the available literature complemented with information collected from stakeholders. Overall, we found that the **preparing for reuse and recycling rate potential could be in the range of 27%-100%** across the individual material fractions of CDW investigated, **averaging 83% for the whole CDW** (the values should be interpreted as the proportion of waste that can be 'sent for preparing for re-use and recycling'). Notice that this figure is calculated excluding the mixed inert waste fraction (ca. 14%) and soil and dredging spoils (excluded from the recovery rate target of the EU Waste Framework Directive). When considering the recovery of the mixed inert fraction as recycling in the equation, the total recycling rate of CDW would rise to as much as 97%²⁵. As for the **potential for preparing for reuse alone**, we estimated that this could vary between **0-50%** depending on the material fraction, **averaging 16% for the whole CDW** (to be interpreted as 'sent for preparing reuse'; 14% when considering preparing for re-use losses). These should be considered as preliminary estimates, based on literature and specific case studies, especially for the case of preparing for reuse. Based on these figures, two scenarios are analysed reflecting a maximum recycling rate scenario and a maximum preparation for reuse and recycling rate scenario. The first scenario is reduces landfilling and incineration to the minimum and assumes implementation of the best performing recycling processes following a best available methods approach; reuse rate is kept at the same levels as today. The second scenario follows the same exact assumptions as the first but prioritises preparing for reuse whenever applicable and to the maximum extent technically possible. The cost savings in the latter simulation are due to the theoretical savings gained by reusing in place of processing the waste via incineration, landfilling and recycling (as in the baseline for year 2020) and should be considered as a theoretical tendency rather than an accurate cost estimate. The results of the assessment show that, compared to the baseline (*status quo* management of CDW in the EU27; and using 2020 waste generation figures) and excluding soil and dredging spoils, a total annual reduction of ca. 33 Mt CO₂ eq. at a net cost of approximately 6.7 billion EUR would be achieved with the maximum recycling potential scenario and a total reduction of ca. 48 Mt CO₂ eq. with a net cost saving of approximately 6.8 billion EUR would be achieved with the maximum preparation for reuse and recycling scenario.

²⁵ Our estimate of 83% is thus not directly comparable with the current EU27 recovery rate of CDW of 79%, as estimated by Eurostat because the latter includes mixed inert waste (which we did not include in the calculation leading to 83%). If a comparison should be made, the value of 97% should be used instead (assuming that all mixed inert waste fraction can be recycled as recycled aggregates).

References

- Abd-Allah, M. N., Salah, A., & El-Beltagy, S. R. (2014). Enhanced customer churn prediction using social network analysis. *International Conference on Information and Knowledge Management, Proceedings, 2014-Novem*(November), 11–12. <https://doi.org/10.1145/2665994.2665997>
- Afrin, H. (2017). A Review on Different Types Soil Stabilization Techniques. *International Journal of Transportation Engineering and Technology*, 3(2), 19. <https://doi.org/10.11648/j.ijtet.20170302.12>
- Ali, H., & Rojali, A. (2023). Recycling Asphalt Pavements: The State of Practice. *Recycling Strategy and Challenges Associated with Waste Management Towards Sustaining the World*, 1–18. <https://doi.org/10.5772/intechopen.106235>
- Allacker, K., Mathieux, F., Pennington, D., & Pant, R. (2017). The search for an appropriate end-of-life formula for the purpose of the European Commission Environmental Footprint initiative. *International Journal of Life Cycle Assessment*, 22(9), 1441–1458. <https://doi.org/10.1007/s11367-016-1244-0>
- Apitz, S. E. (2010). Waste or resource? Classifying and scoring dredged material management strategies in terms of the waste hierarchy. *Journal of Soils and Sediments*, 10(8), 1657–1668. <https://doi.org/10.1007/s11368-010-0300-9>
- Arm, M., Wik, O., Engelsen, C. J., Erlandsson, M., Sundqvist, J.-O., Oberender, A., Hjelmar, O., & Wahlström, M. (2014). ENCORT-CDW: Evaluation of the European recovery target for construction and demolition waste. In *Nordic Council of Ministers*. <https://doi.org/10.6027/NA2014-916>
- Arm, Maria, Wik, O., Engelsen, C. J., Erlandsson, M., Hjelmar, O., & Wahlström, M. (2017). How Does the European Recovery Target for Construction & Demolition Waste Affect Resource Management? *Waste and Biomass Valorization*, 8(5), 1491–1504. <https://doi.org/10.1007/s12649-016-9661-7>
- ARUP. (2021). *Evaluating re-use potential: Material profiles and vision for project workflow*. <https://www.arup.com/perspectives/publications/research/section/evaluating-re-use-potential-materials-profiles>
- Aslani, A., Hachem-Vermette, C., & Zahedi, R. (2023). Environmental impact assessment and potentials of material efficiency using by-products and waste materials. *Construction and Building Materials*, 378(February), 131197. <https://doi.org/10.1016/j.conbuildmat.2023.131197>
- Bakas, I., Kampmann, C. E., & Andersen, G. (2019). Establishing effective markets for secondary building materials. In *The Danish Environmental Protection Agency* (Issue 2076).
- Barry, K., Daniel, J. S., Foxlow, J., & Gray, K. (2014). An evaluation of reclaimed asphalt shingles in hot mix asphalt by varying sources and quantity of reclaimed asphalt shingles. *Road Materials and Pavement Design*, 15(2), 259–271. <https://doi.org/10.1080/14680629.2013.861765>
- Batayneh, M., Marie, I., & Asi, I. (2007). Use of selected waste materials in concrete mixes. *Waste Management*, 27(12), 1870–1876. <https://doi.org/10.1016/j.wasman.2006.07.026>
- Bates, M. E., Fox-Lent, C., Seymour, L., Wender, B. A., & Linkov, I. (2015). Life cycle assessment for dredged sediment placement strategies. *Science of the Total Environment*, 511, 309–318. <https://doi.org/10.1016/j.scitotenv.2014.11.003>
- Bertozzi, C. (2022). How is the construction sector perceiving and integrating the circular economy paradigm? Insights from the Brussels experience. *City, Culture and Society*, 29(May 2021), 100446. <https://doi.org/10.1016/j.ccs.2022.100446>
- BIO by Deloitte. (2015a). *Construction and Demolition Waste Management in Austria* (Issue September). https://environment.ec.europa.eu/topics/waste-and-recycling/construction-and-demolition-waste_en
- BIO by Deloitte. (2015b). *Construction and Demolition Waste Management in Germany* (Issue September). https://environment.ec.europa.eu/topics/waste-and-recycling/construction-and-demolition-waste_en
- BIO by Deloitte. (2015c). *Construction and Demolition Waste Management in Sweden* (Issue September). https://environment.ec.europa.eu/topics/waste-and-recycling/construction-and-demolition-waste_en
- Bisinella, V., Albizzati, P., Federica, Astrup, T., Fruergaard, & Damgaard, A. (2018). *Life Cycle Assessment of management options for beverage packaging waste*. Danish Ministry of Environment and Food.

<http://mfvm.dk/footermenu/publikationer/publikation/pub/hent-fil/publication/udvidelse-af-pant-og-retursystemet/>. <http://mfvm.dk/footermenu/publikationer/publikation/pub/hent-fil/publication/udvidelse-af-pant-og-retursystemet/>

- Bisinella, V., Conradsen, K., Christensen, T. H., & Astrup, T. F. (2016). A global approach for sparse representation of uncertainty in Life Cycle Assessments of waste management systems. *International Journal of Life Cycle Assessment*, 21(3), 378–394. <https://doi.org/10.1007/s11367-015-1014-4>
- Borghi, G., Pantini, S., & Rigamonti, L. (2018). Life cycle assessment of non-hazardous Construction and Demolition Waste (CDW) management in Lombardy Region (Italy). *Journal of Cleaner Production*, 184, 815–825. <https://doi.org/10.1016/j.jclepro.2018.02.287>
- Caro, D., Lodato, C., Astrup, T. F., Cristóbal, J., Forster, G., Flachenecker, F., & Tonini, D. (2023). Environmental and socio-economic effects of building construction and demolition waste recycling in the EU. *In Process*.
- Chen, C. H., Huang, R., Wu, J. K., & Yang, C. C. (2006). Waste E-glass particles used in cementitious mixtures. *Cement and Concrete Research*, 36(3), 449–456. <https://doi.org/10.1016/j.cemconres.2005.12.010>
- Ciacci, L., Passarini, F., & Vassura, I. (2017a). The European PVC cycle: In-use stock and flows. *Resources, Conservation and Recycling*, 123, 108–116. <https://doi.org/10.1016/j.resconrec.2016.08.008>
- Ciacci, L., Passarini, F., & Vassura, I. (2017b). The European PVC cycle: In-use stock and flows. *Resources, Conservation and Recycling*, 123, 108–116. <https://doi.org/10.1016/j.resconrec.2016.08.008>
- Ciroth, A., Muller, S., Weidema, B., & Lesage, P. (2016). Empirically based uncertainty factors for the pedigree matrix in ecoinvent. *International Journal of Life Cycle Assessment*, 21(9), 1338–1348. <https://doi.org/10.1007/s11367-013-0670-5>
- CityLoops. (2020). *Circular soil handling in Høje-Taastrup - Extract from the Demonstration Report* <https://cityloops.eu/construction-demolition-waste/circular-soil-handling>
- Clavreul, J., Baumeister, H., Christensen, T. H., & Damgaard, A. (2014). An environmental assessment system for environmental technologies. *Environmental Modelling and Software*, 60, 18–30. <https://doi.org/10.1016/j.envsoft.2014.06.007>
- Coelho, A. M. G., Pimentel, R., Ungureanu, V., Hradil, P., & Kesti, J. (2020). *European Recommendations for Reuse of Steel Products in Single-Storey Buildings*. ECCS – European Convention for Constructional Steelwork. www.steelconstruct.com
- Cristiano, S., Ghisellini, P., D’Ambrosio, G., Xue, J., Nesticò, A., Gonella, F., & Ulgiati, S. (2021). Construction and demolition waste in the Metropolitan City of Naples, Italy: State of the art, circular design, and sustainable planning opportunities. *Journal of Cleaner Production*, 293. <https://doi.org/10.1016/j.jclepro.2021.125856>
- Cristóbal, J., Foster, G., Caro, D., Manfredi, S., & Tonini, D. (forthcoming). Assessment of excavated soil waste management within the EU: towards a recycling target?.
- Crocetti, P., González-Camejo, J., Li, K., Foglia, A., Eusebi, A. L., & Fatone, F. (2022). An overview of operations and processes for circular management of dredged sediments. *Waste Management*, 146(February), 20–35. <https://doi.org/10.1016/j.wasman.2022.04.040>
- Damgaard, A., Lodato, C., Butera, S., Fruergaard Astrup, T., Kamps, M., Corbin, L., Tonini, D., & Astrup, T. F. (2022). *Background data collection and life cycle assessment for construction and demolition (CDW) waste management*. May. <https://doi.org/10.2760/772724>
- De Melo, A. B., Goncalves, A. F., & Martins, I. M. (2011). Construction and demolition waste generation and management in Lisbon (Portugal). *Resources, Conservation and Recycling*, 55(12), 1252–1264. <https://doi.org/10.1016/j.resconrec.2011.06.010>
- De Wolf, C., Hoxha, E., & Fivet, C. (2020). Comparison of environmental assessment methods when reusing building components: A case study. *Sustainable Cities and Society*, 61(June), 102322. <https://doi.org/10.1016/j.scs.2020.102322>
- Debacker, W., Vrijders, J., Voorter, J., Vergauwen, A., Bergmans, J., & Stouthuysen, P. (2021). *Urban Mining van gebouwen. Rapportage Uitgewerkt in het kader van de Proeftuin Circulair Bouwen*.
- Delft University of Technology. (2004). *Collection of Aluminium from Buildings in Europe, A Study by Delft University of Technology*. <https://european-aluminium.eu/media/1628/collection-of-aluminium-from-buildings-in-europe.pdf>

- Deloitte. (2017). *Study on Resource Efficient Use of Mixed Wastes - Improving management of construction and demolition waste - Final Report. Prepared for the European Commission, DG ENV.* (Issue October).
- Denyer, D., & Tranfield, D. (2009). Producing a Systematic Review. In *The SAGE handbook of organizational research methods* (p. 39).
- Di Maria, A., Eyckmans, J., & Van Acker, K. (2020). Use of LCA and LCC to help decision-making between downcycling versus recycling of construction and demolition waste. In *Advances in Construction and Demolition Waste Recycling: Management, Processing and Environmental Assessment* (Vol. 2010). Elsevier Ltd. <https://doi.org/10.1016/B978-0-12-819055-5.00026-7>
- Diyamandoglu, V., & Fortuna, L. M. (2015). Deconstruction of wood-framed houses: Material recovery and environmental impact. *Resources, Conservation and Recycling*, 100, 21–30. <https://doi.org/10.1016/j.resconrec.2015.04.006>
- Douguet, E., & Wagner, F. (2021). *FutuREuse. The environmental impact of reuse in the construction sector.* <http://www.nweurope.eu/fcrbe>
- EAPA. (2023). *Asphalt in Figures - Provisional figures 2021.* <https://eapa.org/asphalt-in-figures-2021/>
- Ecoinvent. (2023). *Database.* <https://ecoinvent.org/>
- Ekvall, T. (2002). Cleaner production tools: LCA and beyond. *Journal of Cleaner Production*, 10(5), 403–406. [https://doi.org/10.1016/S0959-6526\(02\)00026-4](https://doi.org/10.1016/S0959-6526(02)00026-4)
- El-Haggar, S. M. (2007). Sustainability of Construction and Demolition Waste Management. *Sustainable Industrial Design and Waste Management*, 261–292. <https://doi.org/10.1016/b978-012373623-9/50010-1>
- Etienne, D., Lisa, W., & Laetitia, D. (2022). Evaluating “reuse” in the current LCA framework - Impact of reuse and reusability in different life cycle stages. *IOP Conference Series: Earth and Environmental Science*, 1078(1), 0–9. <https://doi.org/10.1088/1755-1315/1078/1/012015>
- European Commission. (2008). Directive 2008/98/EC of the European Parliament and of the Council of 19 November 2008 on waste and repealing certain Directives. In *Official Journal of European Union* (Vol. L312). <http://eur-lex.europa.eu/LexUriServ/LexUriServ.do?uri=OJ:L:2008:312:0003:01:ES:HTML>
- European Commission. (2011). Commission Decision of 18 November 2011 establishing rules and calculation methods for verifying compliance with the targets set in Article 11(2) of Directive 2008/98/EC of the European Parliament and of the Council. In *Official Journal of the European Union* (Vol. 310). <https://eur-lex.europa.eu/legal-content/EN/TXT/PDF/?uri=CELEX:32011D0753&from=EN>
- European Commission. (2016). *EU Construction and Demolition Waste Management Protocol.* https://single-market-economy.ec.europa.eu/news/eu-construction-and-demolition-waste-protocol-2018-09-18_en
- European Commission. (2018a). Directive (EU) 2018/851 of the European Parliament and of the Council of 30 May 2018 amending Directive 2008/98/EC on waste. In *Official Journal of the European Union* (Issue 1907). <https://eur-lex.europa.eu/legal-content/EN/TXT/?uri=CELEX:32018L0851>
- European Commission. (2018b). *Guidelines for the waste audits before demolition and renovation works of buildings.* <https://ec.europa.eu/docsroom/documents/31521/>
- European Commission. (2019). COMMISSION IMPLEMENTING DECISION (EU) 2019/1004 of 7 June 2019 laying down rules for the calculation, verification and reporting of data on waste in accordance with Directive 2008/98/EC of the European Parliament and of the Council and repealing Commission. In *Official Journal of European Union: Vol. L 163/66.*
- European Commission. (2020a). *Circular Economy - Principles for Buildings Design* (pp. 1–30). <https://ec.europa.eu/docsroom/documents/39984>
- European Commission. (2020b). *Communication from the Commission to the European Parliament, the Council, the European Economic and Social Committee and the Committee of the regions - A new Circular Economy Action Plan For a cleaner and more competitive Europe - COM(2020) 98 Final* (p. 249). <https://eur-lex.europa.eu/legal-content/EN/TXT/PDF/?uri=CELEX:52020DC0098&from=EN>
- European Commission. (2020c). *Study to support the preparation of Commission guidelines on the definition of backfilling* (Issue January). Publications Office of the European Union. <https://op.europa.eu/en/publication-detail/-/publication/f82900fe-9fc2-11ea-9d2d-01aa75ed71a1/language-en>

- European Commission. (2021a). *Communication from the Commission to the European Parliament, the Council, the European economic and social committee and the committee of the regions - EU Soil Strategy for 2030 - Reaping the benefits of the healthy soils for people, food, nature and clim.* <https://eur-lex.europa.eu/legal-content/EN/TXT/?uri=CELEX%3A52021DC0699>
- European Commission. (2021b). *Treatment of waste by waste category, hazardousness and waste management operations (env_wastrt) for 2018.* Eurostat.
- European Commission. (2022a). *Reporting on material recovery of C&D waste - Guidance for the reporting of the data according to Commission Decision 2011/753/EU and Commission Implementing Decision (EU) 2019/1004.*
- European Commission. (2022b). *Study on Measuring the Application of Circular Approaches in the Construction Industry Ecosystem.* https://eisma.ec.europa.eu/news/study-measuring-application-circular-approaches-construction-industry-ecosystem-2022-07-19_en
- European Commission. (2023a). *Environmental and Economic Assessment of Plastic Waste Recycling, Joint Research Centre* (Issue September). <https://doi.org/10.2760/0472>
- European Commission. (2023b). *Eurocodes: Building the future - About the EN Eurocodes.* <https://eurocodes.jrc.ec.europa.eu/showpage.php?id=1>
- European Commission. (2023c). *Transition pathway for Construction* (pp. 1–74). <https://ec.europa.eu/docsroom/documents/53854>
- European Environment Agency. (2022). *Investigating Europe's Secondary Raw Material Markets* (Issue 12). Luxembourg: Publications Office of the European Union. <https://doi.org/10.2800/48962>
- European Parliament and the Council. (2020). Regulation (EU) 2020/852 of the European Parliament and of the Council of 18 June 2020 on the establishment of a framework to facilitate sustainable investment, and amending Regulation (EU) 2019/2088. *Official Journal of the European Union*, 198(22.06.2020), 13–43.
- Fabbri, D., Pizzol, R., Calza, P., Malandrino, M., Gaggero, E., Padoan, E., & Ajmone-Marsan, F. (2021). Constructed technosols: A strategy toward a circular economy. *Applied Sciences (Switzerland)*, 11(8). <https://doi.org/10.3390/app11083432>
- Faraca, G., Martinez-Sanchez, V., & Astrup, T. F. (2019). Environmental life cycle cost assessment: Recycling of hard plastic waste collected at Danish recycling centres. *Resources, Conservation and Recycling*, 143(June 2018), 299–309. <https://doi.org/10.1016/j.resconrec.2019.01.014>
- Faraca, G., Tonini, D., & Astrup, T. F. (2019). Dynamic accounting of greenhouse gas emissions from cascading utilisation of wood waste. *Science of the Total Environment*, 651, 2689–2700. <https://doi.org/10.1016/j.scitotenv.2018.10.136>
- Fatta, D., Papadopoulos, A., Avramikos, E., Sgourou, E., Moustakas, K., Kourmoussis, F., Mentzias, A., & Loizidou, M. (2003). Generation and management of construction and demolition waste in Greece - An existing challenge. *Resources, Conservation and Recycling*, 40(1), 81–91. [https://doi.org/10.1016/S0921-3449\(03\)00035-1](https://doi.org/10.1016/S0921-3449(03)00035-1)
- Ferrans, L., Jani, Y., Gao, L., & Hogland, W. (2019). Characterization of dredged sediments: a first guide to define potentially valuable compounds - the case of Malmfjorden Bay, Sweden. *Advances in Geosciences*, 49, 137–147. <https://doi.org/10.5194/adgeo-49-137-2019>
- Ferrans, L., Nilsson, A., Schmieder, F., Pal, D., Rahmati-Abkenar, M., Marques, M., & Hogland, W. (2022). Life Cycle Assessment of Management Scenarios for Dredged Sediments: Environmental Impacts Caused during Landfilling and Soil Conditioning. *Sustainability (Switzerland)*, 14(20). <https://doi.org/10.3390/su142013139>
- Firoozi, A. A., Guney Olgun, C., Firoozi, A. A., & Baghini, M. S. (2017). Fundamentals of soil stabilization. *International Journal of Geo-Engineering*, 8(1). <https://doi.org/10.1186/s40703-017-0064-9>
- Fořt, J., & Černý, R. (2020). Transition to circular economy in the construction industry: Environmental aspects of waste brick recycling scenarios. *Waste Management*, 118, 510–520. <https://doi.org/10.1016/j.wasman.2020.09.004>
- Fruergaard, T., Hyks, J., & Astrup, T. (2010). Life-cycle assessment of selected management options for air pollution control residues from waste incineration. *Science of the Total Environment*, 408(20), 4672–4680.

<https://doi.org/10.1016/j.scitotenv.2010.05.029>

- Gálvez-Martos, J. L., & Istrate, I. R. (2020). Construction and demolition waste management. In *Advances in Construction and Demolition Waste Recycling: Management, Processing and Environmental Assessment* (Issue 2018). Elsevier Ltd. <https://doi.org/10.1016/B978-0-12-819055-5.00004-8>
- Gebremariam, A. T., Di Maio, F., Vahidi, A., & Rem, P. (2020). Innovative technologies for recycling End-of-Life concrete waste in the built environment. *Resources, Conservation and Recycling*, 163(April), 104911. <https://doi.org/10.1016/j.resconrec.2020.104911>
- Ghisellini, P., Ripa, M., & Ulgiati, S. (2018). Exploring environmental and economic costs and benefits of a circular economy approach to the construction and demolition sector. A literature review. *Journal of Cleaner Production*, 178, 618–643. <https://doi.org/https://doi.org/10.1016/j.jclepro.2017.11.207>
- Gorgolewski, M., & Ergun, D. (2013). Closed-loop materials systems. In R. Soetanto, N. Tsang, & A. Ahmed (Eds.), *Sustainable Building Conference 2013* (pp. 235–243). Coventry University. https://www.irbnet.de/daten/iconda/CIB_DC26438.pdf
- Guyer, J. P. (2012). *Introduction to Fill and Backfill for Structures*. [https://www.cedengineering.com/userfiles/An Introduction to Fill and Backfill for Structures R1.pdf](https://www.cedengineering.com/userfiles/An%20Introduction%20to%20Fill%20and%20Backfill%20for%20Structures%20R1.pdf)
- Haas, M., Galler, R., Scibile, L., & Benedikt, M. (2020). Waste or valuable resource – a critical European review on re-using and managing tunnel excavation material. *Resources, Conservation and Recycling*, 162(June), 105048. <https://doi.org/10.1016/j.resconrec.2020.105048>
- Hale, S. E., Roque, A. J., Okkenhaug, G., Sørmo, E., Lenoir, T., Carlsson, C., Kupryianchyk, D., Flyhammar, P., & Žlender, B. (2021). The reuse of excavated soils from construction and demolition projects: Limitations and possibilities. *Sustainability (Switzerland)*, 13(11), 1–15. <https://doi.org/10.3390/su13116083>
- Hendriks, C. F., & Janssen, G. M. T. (2001). Application of construction and demolition waste. *Heron*, 46(2), 95–108.
- Henry, M., Haouche, L., & Lemièrre, B. (2023). Mineral Processing Techniques Dedicated to the Recycling of River Sediments to Produce Raw Materials for Construction Sector. *Mining*, 3(1), 54–76. <https://doi.org/10.3390/mining3010003>
- Hestin, M., de Veron, S., & Burgos, S. (2016). Economic study on recycling of building glass in Europe. *Economic Study on Recycling of Building Glass in Europe, April*, 141. <https://www.glassforeurope.com/wp-content/uploads/2018/04/Economic-study-on-recycling-of-building-glass-in-Europe-Deloitte.pdf>
- Höglmeier, K., Weber-Blaschke, G., & Richter, K. (2017). Potentials for cascading of recovered wood from building deconstruction—A case study for south-east Germany. *Resources, Conservation and Recycling*, 117, 304–314. <https://doi.org/10.1016/j.resconrec.2015.10.030>
- Huang, T., Kou, S., Liu, D., Li, D., & Xing, F. (2022). Evaluation of the Techno-Economic Feasibility for Excavated Soil Recycling in Shenzhen, China. *Sustainability (Switzerland)*, 14(5), 1–16. <https://doi.org/10.3390/su14053028>
- Iacovidou, E., Martin, O. V., & Gerasimidou, S. (2020). *Environmental Life Cycle Impacts of Inert / Less Reactive Waste Materials*. Brunel University London.
- Iacovidou, E., & Purnell, P. (2016). Mining the physical infrastructure: Opportunities, barriers and interventions in promoting structural components reuse. *Science of the Total Environment*, 557–558, 791–807. <https://doi.org/10.1016/j.scitotenv.2016.03.098>
- Ismail, Z. Z., & AL-Hashmi, E. A. (2009). Recycling of waste glass as a partial replacement for fine aggregate in concrete. *Waste Management*, 29(2), 655–659. <https://doi.org/10.1016/j.wasman.2008.08.012>
- Kancheva, Y. D., & Zaharieva, R. A. (2023). End-of-life options for ceramic masonry units – environmental and performance-based perspective. *IOP Conference Series: Materials Science and Engineering*, 1276(1), 012002. <https://doi.org/10.1088/1757-899x/1276/1/012002>
- Katagiri, K., Boscov, M. E. G., Teixeira, C. E., & Angulo, S. C. (2019). Characterization flowchart for assessing the potential reuse of excavation soils in Sao Paulo city. *Journal of Cleaner Production*, 240. <https://doi.org/10.1016/j.jclepro.2019.118215>
- Keramidas, K., Fosse, F., Diaz-Vazques, A., Schade, B., Tchung-Ming, S., Weitzel, M., Vandyck, T., & Wojtowicz, K. (2021). Global Energy and Climate Outlook 2020: A New Normal Beyond Covid-19. In *Publications Office*

- of the European Union. <https://doi.org/10.2760/608429>
- Kreislaufwirtschaft Bau. (2023). *Mineralische Bauabfälle Monitoring 2020 (in German)*. <https://kreislaufwirtschaft-bau.de/Download/Bericht-13.pdf>
- Lase, I. S., Tonini, D., Caro, D., Albizzati, P. F., Cristóbal, J., Roosen, M., Kusenber, M., Ragaert, K., Van Geem, K. M., Dewulf, J., & De Meester, S. (2023). How much can chemical recycling contribute to plastic waste recycling in Europe? An assessment using material flow analysis modeling. *Resources, Conservation and Recycling*, 192(November 2022). <https://doi.org/10.1016/j.resconrec.2023.106916>
- Lederer, J., Gassner, A., Kleemann, F., & Fellner, J. (2020). Potentials for a circular economy of mineral construction materials and demolition waste in urban areas: a case study from Vienna. *Resources, Conservation and Recycling*, 161(June), 104942. <https://doi.org/10.1016/j.resconrec.2020.104942>
- Lindner, C., Hein, J., & Fischer, E. (2020). *Waste generation, waste streams and recycling potentials of HBCD-containing EPS/XPS waste in Europe and forecast model up to 2050* (Issue April). Elaborated for BASF.
- López Ruiz, L. A., Roca Ramón, X., & Gassó Domingo, S. (2020). The circular economy in the construction and demolition waste sector – A review and an integrative model approach. *Journal of Cleaner Production*, 248. <https://doi.org/10.1016/j.jclepro.2019.119238>
- Lu, W., Yuan, L., & Xue, F. (2021). Investigating the bulk density of construction waste: A big data-driven approach. *Resources, Conservation and Recycling*, 169(105480).
- Luciano, A., Cutaia, L., Altamura, P., & Penalvo, E. (2022). Critical issues hindering a widespread construction and demolition waste (CDW) recycling practice in EU countries and actions to undertake: The stakeholder's perspective. *Sustainable Chemistry and Pharmacy*, 29(June), 100745. <https://doi.org/10.1016/j.scp.2022.100745>
- Luo, W., Liu, S., Hu, Y., Hu, D., Kow, K. W., Pang, C., & Li, B. (2022). Sustainable reuse of excavated soil and recycled concrete aggregate in manufacturing concrete blocks. *Construction and Building Materials*, 342(February). <https://doi.org/10.1016/j.conbuildmat.2022.127917>
- Magnusson, S., Lundberg, K., Svedberg, B., & Knutsson, S. (2015). Sustainable management of excavated soil and rock in urban areas - A literature review. *Journal of Cleaner Production*, 93, 18–25. <https://doi.org/10.1016/j.jclepro.2015.01.010>
- Malabi Eberhardt, L. C., Stijn, A. Van, Rasmussen, F. N., Birkved, M., & Birgisdottir, H. (2020). Towards circular life cycle assessment for the built environment: A comparison of allocation approaches. *IOP Conference Series: Earth and Environmental Science*, 588(3), 0–8. <https://doi.org/10.1088/1755-1315/588/3/032026>
- Marsh, A. T. M., Velenturf, A. P. M., & Bernal, S. A. (2022). Circular Economy strategies for concrete implementation and integration. *Journal of Cleaner Production*, 362(May), 132486. <https://doi.org/10.1016/j.jclepro.2022.132486>
- Martinez-Sanchez, V., Kromann, M. A., & Astrup, T. F. (2015). Life cycle costing of waste management systems: Overview, calculation principles and case studies. *Waste Management*, 36, 343–355. <https://doi.org/10.1016/j.wasman.2014.10.033>
- Maryland Department of the Environment. (2017). *Innovative Reuse and Beneficial Use of Dredged Material Guidance Document* (Issue August). https://mde.maryland.gov/programs/marylander/Documents/Dredging/FINAL_IBR_GUIDANCE_8.30.2017_MDE.pdf
- Menegaki, M., & Damigos, D. (2018). A review on current situation and challenges of construction and demolition waste management. *Current Opinion in Green and Sustainable Chemistry*, 13, 8–15. <https://doi.org/10.1016/j.cogsc.2018.02.010>
- Mhatre, P., Gedam, V. V., & Unnikrishnan, S. (2021). Material circularity potential for construction materials – The case of transportation infrastructure in India. *Resources Policy*, 74(October), 102446. <https://doi.org/10.1016/j.resourpol.2021.102446>
- Michalcikova, M., & Drochytka, R. (2018). Techniques of soil modification for re-use in construction. *IOP Conference Series: Materials Science and Engineering*, 385(1). <https://doi.org/10.1088/1757-899X/385/1/012036>
- Mohajerani, A., Vajna, J., Cheung, T. H. H., Kurmus, H., Arulrajah, A., & Horpibulsuk, S. (2017). Practical recycling

- applications of crushed waste glass in construction materials: A review. *Construction and Building Materials*, 156, 443–467. <https://doi.org/10.1016/j.conbuildmat.2017.09.005>
- Moschen-Schimek, J., Kasper, T., & Huber-Humer, M. (2023). Critical review of the recovery rates of construction and demolition waste in the European Union – An analysis of influencing factors in selected EU countries. *Waste Management*, 167(December 2022), 150–164. <https://doi.org/10.1016/j.wasman.2023.05.020>
- Mulders, L. (2013). *Master thesis High quality recycling of construction and demolition waste in the Netherlands Lisanne Mulders*. [https://studenttheses.uu.nl/bitstream/handle/20.500.12932/13837/Master thesis - Lisanne Mulders - High quality C%26D waste recycling.pdf?sequence=1&isAllowed=y](https://studenttheses.uu.nl/bitstream/handle/20.500.12932/13837/Master%20thesis%20-%20Lisanne%20Mulders%20-%20High%20quality%20waste%20recycling.pdf?sequence=1&isAllowed=y)
- Noel, L., Kuchen, V., & Gonser, J. (2021). *In depth validation of waste statistics data – reference year 2018. Data validation description and country fact sheets* (Issue July). Institut de Conseil et d'Etudes en Développement Durable asbl.
- Oluleye, B. I., Chan, D. W. M., Saka, A. B., & Olawumi, T. O. (2022). Circular economy research on building construction and demolition waste: A review of current trends and future research directions. *Journal of Cleaner Production*, 357, 131927. <https://doi.org/10.1016/j.jclepro.2022.131927>
- Oyedele, L. O., Ajayi, S. O., & Kadiri, K. O. (2014). Use of recycled products in UK construction industry: An empirical investigation into critical impediments and strategies for improvement. *Resources, Conservation and Recycling*, 93, 23–31. <https://doi.org/10.1016/j.resconrec.2014.09.011>
- Pacheco, J., de Brito, J., & Lamperti Tornaghi, M. (2023). *Use of recycled aggregates in concrete - Opportunities for upscaling in Europe*.
- Panagos, P., Van Liedekerke, M., Borrelli, P., Königer, J., Ballabio, C., Orgiazzi, A., Lugato, E., Liakos, L., Hervas, J., Jones, A., & Montanarella, L. (2022). European Soil Data Centre 2.0: Soil data and knowledge in support of the EU policies. *European Journal of Soil Science*, 73(6), 1–18. <https://doi.org/10.1111/ejss.13315>
- Pantini, S., Giurato, M., & Rigamonti, L. (2019). A LCA study to investigate resource-efficient strategies for managing post-consumer gypsum waste in Lombardy region (Italy). *Resources, Conservation and Recycling*, 147(December 2018), 157–168. <https://doi.org/10.1016/j.resconrec.2019.04.019>
- Patel, A. (2019). Soil stabilization. In *Geotechnical Investigations and Improvement of Ground Conditions* (pp. 19–27). Woodhead Publishing. <https://doi.org/10.1016/C2018-0-01307-9>
- Pristerà, G., Tonini, D., Lamperti Tornaghi, M., & Sala, S. (forthcoming). *Taxonomy of Design for Deconstruction Options to Enable Circular Economy in Buildings*.
- Ramboll. (2018). *Screening Study on End of Life Treatment of Wood From Doors and Windows*.
- REBRICK. (2013). *REBRICK project*. <http://www.gamlemursten.eu/>
- Renella, G. (2021). Recycling and reuse of sediments in agriculture: Where is the problem? *Sustainability (Switzerland)*, 13(4), 1–12. <https://doi.org/10.3390/su13041648>
- Rigamonti, L., Grosso, M., & Giugliano, M. (2009). Life cycle assessment for optimising the level of separated collection in integrated MSW management systems. *Waste Management*, 29(2), 934–944. <https://doi.org/10.1016/j.wasman.2008.06.005>
- Rivela, B., Moreira, M. T., Muñoz, I., Rieradevall, J., & Feijoo, G. (2006). Life cycle assessment of wood wastes: A case study of ephemeral architecture. *Science of the Total Environment*, 357(1–3), 1–11. <https://doi.org/10.1016/j.scitotenv.2005.04.017>
- Roque, A. J., Da Silva, P. F., Rodrigues, G., & Almeida, R. (2016). Recycling of CDW and Steel Slag in Drainage Layers of Transport Infrastructures. *Procedia Engineering*, 143(Ictg), 196–203. <https://doi.org/10.1016/j.proeng.2016.06.025>
- Rudjord, F. (2018). *Master thesis: Recycling of Glass Wool Waste* (Issue June, pp. 1–87). NTNU - Norwegian University of Science and Technology. <http://hdl.handle.net/11250/2576495>
- Sáez, P. V., Del Río Merino, M., Porras-Amores, C., & González, A. S. A. (2014). Assessing the accumulation of construction waste generation during residential building construction works. *Resources, Conservation and Recycling*, 93(2014), 67–74. <https://doi.org/10.1016/j.resconrec.2014.10.004>
- Santoro, A. (2020). *From demolition waste to circular construction through partnerships – Reusing old bricks in North Jutland*. Aalborg University.

- Sassi, P. (2002). *Study of current building methods that enable the dismantling of building structures and their classifications according to their ability to be reused, recycled or downcycled*. In-house publishing. <https://www.irbnet.de/daten/iconda/CIB3043.pdf>
- Scialpi, G., & Perrotti, D. (2022). The use of urban biowaste and excavated soil in the construction sector: A literature review. *Waste Management and Research*, 40(3), 262–273. <https://doi.org/10.1177/0734242X211000430>
- Svensson, N., Norén, A., Modin, O., Karlfeldt Fedje, K., Rauch, S., Strömvall, A. M., & Andersson-Sköld, Y. (2022). Integrated cost and environmental impact assessment of management options for dredged sediment. *Waste Management*, 138, 30–40. <https://doi.org/10.1016/j.wasman.2021.11.031>
- Tonini, D., Martinez-Sanchez, V., & Astrup, T. F. (2013). Material resources, energy, and nutrient recovery from waste: Are waste refineries the solution for the future? *Environmental Science and Technology*, 47(15), 8962–8969. <https://doi.org/10.1021/es400998y>
- Tóth, G., Jones, A., & Montanarella, L. (2013). LUCAS Topsoil Survey: Methodology, Data, and Results. In *Publications Office of the European Union, ...* <https://doi.org/10.2788/97922>
- UEPG. (2023). *Aggregates - Products*. <https://www.aggregates-europe.eu/aggregates/products/>
- Väntsi, O., & Kärki, T. (2014). Mineral wool waste in Europe: A review of mineral wool waste quantity, quality, and current recycling methods. *Journal of Material Cycles and Waste Management*, 16(1), 62–72. <https://doi.org/10.1007/s10163-013-0170-5>
- Villoria Sáez, P., & Osmani, M. (2019). A diagnosis of construction and demolition waste generation and recovery practice in the European Union. *Journal of Cleaner Production*, 241. <https://doi.org/10.1016/j.jclepro.2019.118400>
- Vrancken, K. C., & Laethem, B. (2000). Recycling options for gypsum from construction and demolition waste. *Waste Management Series*, 1(C), 325–331. [https://doi.org/10.1016/S0713-2743\(00\)80045-8](https://doi.org/10.1016/S0713-2743(00)80045-8)
- Wahlström, M., Laine-Ylijoki, J., Jämström, H., Kaartinen, T., Erlandsson, M., Cousins, A. P., Wik, O., Suer, P., Oberender, A., Hjelm, O., Birgisdóttir, H., Butera, S., Astrup, T. F., & Jørgensen, A. (2014). *Environmentally sustainable construction products and materials – Assessment of release* (Issue March). Nordic Innovation. <http://www.nordicinnovation.org/Publications/environmentally-sustainable-construction-products-and-materials-assessment-of-release-and-emissions/>
- Whittaker, M. J., Grigoriadis, K., Soutsos, M., Sha, W., Klinge, A., Paganoni, S., Casado, M., Brander, L., Mousavi, M., Scullin, M., Correia, R., Zerbi, T., Staiano, G., Merli, I., Ingrosso, I., Attanasio, A., & Largo, A. (2021). Novel construction and demolition waste (CDW) treatment and uses to maximize reuse and recycling. *Advances in Building Energy Research*, 15(2), 253–269. <https://doi.org/10.1080/17512549.2019.1702586>
- Wiprächtiger, M., Haupt, M., Heeren, N., Waser, E., & Hellweg, S. (2020). A framework for sustainable and circular system design: Development and application on thermal insulation materials. *Resources, Conservation and Recycling*, 154(December 2019), 104631. <https://doi.org/10.1016/j.resconrec.2019.104631>
- WOOL2LOOP. (2020). *WOOL2LOOP Final Report - Mineral wool waste back to loop with advanced sorting, pre-treatment, and alkali activation* (pp. 1–52).
- Xu, M., Ai, X., Huang, L., Fan, L., Yang, J., Pei, Z., Feng, D., & Yi, J. (2022). Utilization of RCAs arising from excavated soil in CTBM: Laboratory characterization and environmental impact assessment. *Journal of Cleaner Production*, 375(September), 134221. <https://doi.org/10.1016/j.jclepro.2022.134221>
- Youcai, Z., & Sheng, H. (2017). General Introduction of Construction and Demolition Waste. *Pollution Control and Resource Recovery*, 1–14. <https://doi.org/10.1016/b978-0-12-811754-5.00001-4>
- Zampori, L., & Pant, R. (2019). Suggestions for updating the Product Environmental Footprint (PEF) method. In *Publications Office of the European Union*. <https://doi.org/10.2760/424613>
- Zhang, C., Hu, M., Di Maio, F., Sprecher, B., Yang, X., & Tukker, A. (2022). An overview of the waste hierarchy framework for analyzing the circularity in construction and demolition waste management in Europe. *Science of the Total Environment*, 803, 149892. <https://doi.org/10.1016/j.scitotenv.2021.149892>
- Zhang, C., Hu, M., Sprecher, B., Yang, X., Zhong, X., Li, C., & Tukker, A. (2021). Recycling potential in building energy renovation: A prospective study of the Dutch residential building stock up to 2050. *Journal of Cleaner Production*, 301, 126835. <https://doi.org/10.1016/j.jclepro.2021.126835>

- Zhang, C., Hu, M., Yang, X., Miranda-Xicotencatl, B., Sprecher, B., Di Maio, F., Zhong, X., & Tukker, A. (2020). Upgrading construction and demolition waste management from downcycling to recycling in the Netherlands. *Journal of Cleaner Production*, 266, 121718. <https://doi.org/10.1016/j.jclepro.2020.121718>
- Zhang, N., Zhang, H., Schiller, G., Feng, H., Gao, X., Li, E., & Li, X. (2020). Unraveling the Global Warming Mitigation Potential from Recycling Subway-Related Excavated Soil and Rock in China Via Life Cycle Assessment. *Integrated Environmental Assessment and Management*, 17(3), 639–650. <https://doi.org/10.1002/ieam.4376>
- Zhou, H., Zhang, W., Li, L., Zhang, M., & Wang, D. (2021). Environmental impact and optimization of lake dredged-sludge treatment and disposal technologies based on life cycle assessment (LCA) analysis. *Science of the Total Environment*, 787. <https://doi.org/10.1016/j.scitotenv.2021.147703>

CONFIDENTIAL – WORK IN PROGRESS

List of abbreviations and definitions

BAT	Best Available Techniques
CAPEX	Capital Expenditure
CDW	Construction and Demolition Waste
CRCA	Coarse Recycled Concrete Aggregate
DfD	Design for Deconstruction
EF	Environmental Footprint
EoL	End-of-Life
EoW	End-of-Waste
EPS	Expanded Polystyrene
EWC	European Waste Code
FU	Functional Unit
GHG	Greenhouse Gas
HBCD	Hexabromocyclododecane
IPPC	Integrated Pollution Prevention and Control
KPI	Key Performance Indicator
LCA	Life Cycle Assessment
ELCC	Environmental life cycle Costing
LoW	List of Waste
LWA	Light Weight Aggregates
MACC	Marginal Abatement Cost Curves
MFA	Material Flow Analysis
OPEX	Operational Expenditure
PAM	Polyacrylamide
PVC	Polyvinylchloride
RA	Recycled Aggregates
RAC	Recycled Aggregate Concrete
RCA	Recycled Concrete Aggregate
TRL	Technology Readiness Level
WFD	Waste Framework Directive

Definitions

Backfilling	is defined in Art. 3(17a) as “any recovery operation where suitable non-hazardous waste is used for purposes of reclamation in excavated areas or for engineering purposes in landscaping. Waste used for backfilling must substitute non-waste materials, be suitable for the aforementioned purposes, and be limited to the amount strictly necessary to achieve those purposes.”
Material recovery	is defined in Art. 3(15a) of Directive 2008/98/EC as “any recovery operation, other than energy recovery and the reprocessing into materials that are to be used as fuels or other means to generate energy. It includes, inter alia, preparing for reuse, recycling and backfilling”.
Preparing for reuse	means checking, cleaning or repairing recovery operations, by which products or components of products that have become waste are prepared so that they can be reused without any other pre-processing” (Directive 2008/98/EC, Art. 3(16)).
Recycling	means any recovery operation by which waste materials are reprocessed into products, materials or substances whether for the original or other purposes. It (..) does not include energy recovery and the reprocessing into materials that are to be used as fuels or for backfilling operations” (Directive 2008/98/EC, Art. 3(17)).

CONFIDENTIAL – WORK IN PROGRESS

List of boxes

Box 1. Treatment of the CDW mineral fraction: changes observed following the update of the definition of backfilling.....38

CONFIDENTIAL – WORK IN PROGRESS

List of figures

- Figure 1.** MFA showing the origin of building-related material flows from countries, regions, building types and demolition and renovation activities in 2020 in the EU27 (infrastructure waste not included). Notice that the total inflow of material to construction and renovation was estimated to ca. 1 004 000 kt.....16
- Figure 2.** MFA showing origin of building-related material flows from countries, regions, building types and demolition and renovation activities in 2050 in the EU27 (infrastructure waste not included). Notice that the total inflow of material to construction and renovation was estimated to ca. 1 594 000 kt.....17
- Figure 3.** Materials and methods for the literature review on infrastructure CDW.....20
- Figure 4.** Treatment of the mineral fraction of CDW in the analysed EU Member States in 2020. Disposal is defined as landfill, incineration without energy recovery and other disposal. Note that data for Ireland 2020 is not available and data from 2018 has been used.....38
- Figure 5.** Treatment of the excavated soil fraction of CDW in the analysed Member States in 2020. Disposal is defined as landfill, incineration without energy recovery and other disposal. Note that data for Ireland 2020 is not available and data from 2018 has been used.....41
- Figure 6.** Treatment of the dredging spoil fraction of CDW in the analysed Member States in 2020. Disposal is defined as landfill, incineration without energy recovery and other disposal. Note that data for Ireland and Czechia 2020 is not available and data from 2018 has been used.....42
- Figure 7.** General system boundaries of the life cycle assessment and costing. Waste is assumed to be generated burden-free as the upstream impacts of the production would be the same across all management scenarios. All operations involving generation are included (e.g., demolition and conditioning) (blue continuous boxes). System expansion is applied to credit material and energy recovery (green dashed boxes).....46
- Figure 8.** Characterised climate change results per tonne of CDW fraction managed with breakdown of the contributions in 2020. Values above zero represent burdens, while values below zero represent savings. The final net impact, per each individual category, is the sum of burdens and savings and is represented with a black dot. The error bars represent the standard deviation around the net result. For the abbreviations used please refer to Table 11.....51
- Figure 9.** Environmental life cycle cost results per tonne of CDW fraction managed with breakdown of the contributions. Values above zero represent costs, while values below zero represent revenues. The final net impact, per each individual category, is the sum of costs and revenues and is represented with a black dot. The error bars represent the standard deviation around the net result. For the abbreviations used please refer to Table 11.....53
- Figure 10.** Marginal abatement cost curve for the maximum recycling potential (MRP) scenario. Notice that the impacts and costs of the baseline are accounted for as avoided. DDS: dredging spoils; EPS: expanded polystyrene; ESR: excavated soil; PVC: poly vinyl chloride.....64
- Figure 11.** Marginal abatement cost curve for the maximum preparing for reuse potential (MPP) scenario. Notice that the impacts and costs of the baseline are accounted for as avoided. DDS: dredging spoils; EPS: expanded polystyrene; ESR: excavated soil; PVC: poly vinyl chloride.....65

List of tables

Table 1. Description of the CDW fractions considered in this study with a correlation of the LoW and EWC-stat codes.....	10
Table 2. Current CDW generation in 29 European countries, as well as total CDW generation for all 27 Member States (EU27) and for EU27 + Norway. CDW data are presented as both incl. and excl. soil, track ballast, dredging spoils and asphalt, with a detailed focus on soil waste generation.....	12
Table 3. Current average CDW composition (expressed as % of the total per capita CDW amounts) for EU27 and EU27+Norway. Data are presented both excluding and including soil, track ballast, dredging spoils, and asphalt.....	14
Table 4. Theoretical CDW composition from building demolition and renovation activities estimated via MFA. Notice that this composition only refers to CDW from buildings and excludes infrastructure waste and soil waste. As such, it cannot be directly compared to the fractional composition reported for CDW as a whole in Table 3.....	18
Table 5. Numbers of publications according to the material collection process.....	20
Table 6. Qualitative characterisation of the detected publications.....	20
Table 7. Amounts and comparison between asphalt waste fraction in the European countries and asphalt secondary raw materials (reclaimed asphalt and asphalt recycled aggregates).....	22
Table 8: Summary of technologies and management options reported in the literature for the different CDW material fractions. CD: Conventional demolition; DfD: Design for Deconstruction; SD: Selective demolition.....	24
Table 9. Overview of the management pathways for individual material fractions of CDW in the EU estimated for the current situation based on data reported by Member States and on the available techno-scientific literature. Values are rounded.....	42
Table 10. Overall recovery rate for CDW across the EU Member States (in %).....	43
Table 11. Description of the scenarios modelled in this study for the different fractions with details on the life cycle stages and the product substitutability factors (when applicable).....	47
Table 12. Combination of the results obtained in Figure 8 and Figure 9 reporting the outcome of the net impact on climate change (CC) category and the conventional (financial) environmental life cycle costs (Costs), per each individual fraction and associated management.....	55
Table 13. Estimation of the share of waste material fraction that can be potentially sent for 'preparing for reuse'. In column #2, in brackets, we report the percent of material available for reuse preparing for reuse i.e., corrected for process losses.....	58
Table 14. Partitioning of the generated CDW across management pathways in the two scenarios analysed (MRP and MPP). The percentage reflects the share of the CDW generated sent to the treatment (e.g., sent to 'preparing for reuse') and not what is considered reused or recycled in practice. However, losses are duly considered in the LCA calculation. CON: concrete; ALU: aluminium; BRK: bricks; C&T: ceramic and tiles; DDS: dredging spoils; EPS: expanded polystyrene; ESR: excavated soil; GLA: glass; GLW: glass wool; GYP: gypsum; INC: incineration; LN: landfilling; PVC: poly vinyl chloride; REC: recycling; RBB: recovery/backfilling. STE: steel; STW: stone wool; WOD: wood.....	63
Table 15. Marginal cost, total GHG emission reductions and total cost for the MPR and MPP scenarios by material fraction.....	66
Table 16. Template for questions within the survey and the statistics of the results obtained.....	72
Table 17. Bilateral dialogues between JRC and stakeholders.....	73

Annexes

Annex 1. Remaining impact categories results

This annex reports the remaining impact category results for the analysis in 2020. The abbreviations in the following tables correspond to: OD – Ozone depletion; HT can – Human toxicity, cancer; HT no car – Human toxicity, non-carcinogenic; PM – Particulate matter; IR – Ionising radiation; POF – Photochemical ozone formation; Aci – Acidification; EU Ter – Eutrophication, terrestrial; EU Fre – Eutrophication, freshwater; EU Mar – Eutrophication, marine; RU en – Resource use, energy carrier; RU min – Resource use, minerals and metals; WU – Water use; LU – Land use; EcoTox – Ecotoxicity, freshwater; SC – Societal costs.

Table A1. Remaining environmental impact categories for concrete

Management option	OD	HT can	HT no car	PM	IR	POF	Aci	Eu Ter	Eu Fre	Eu Mar	RU en	RU min	WU	LU	EcoTox	SC
	<i>kg CFC-11 eq</i>	<i>CTUh</i>	<i>CTUh</i>	<i>Disease incidences</i>	<i>kBq U-235 eq.</i>	<i>mol H+ eq</i>	<i>mol N eq</i>	<i>kg N eq.</i>	<i>kg P eq.</i>	<i>kg N eq</i>	<i>MJ</i>	<i>kg SB eq</i>	<i>m3 water eq</i>	-	<i>CTUe</i>	<i>EUR</i>
REU	9.6E-07	-9.7E-09	-4.3E-07	5.6E-07	-1.3E+00	-7.1E-02	-1.1E-01	-3.4E-01	-1.2E-03	-2.6E-02	-1.8E+02	-2.3E-04	-6.2E+01	-1.6E+02	-6.7E+02	-8.1E+01
REC-CEM	4.4E-06	2.2E-09	-9.6E-08	3.6E-06	1.9E-01	1.1E-01	5.2E-02	3.4E-01	-6.5E-04	3.3E-02	1.3E+02	-2.4E-05	-5.0E+01	2.5E+01	-1.9E+02	7.6E+01
REC-RA	2.1E-06	1.0E-09	7.3E-08	1.3E-06	4.1E-01	5.4E-02	4.5E-02	1.8E-01	2.2E-05	1.7E-02	1.3E+02	-2.5E-06	-5.0E+01	2.0E+01	7.9E+01	4.4E+01
LAN	3.28E-06	5.54E-09	1.30E-07	2.50E-06	9.42E-01	1.11E-01	9.14E-02	3.8E-01	8.34E-05	3.49E-02	2.15E+02	3.07E-05	7.42E-01	1.48E+02	1.53E+02	4.8E+01

Table A2. Remaining environmental impact categories for wood

Management option	OD	HT can	HT no car	PM	IR	POF	Aci	Eu Ter	Eu Fre	Eu Mar	RU en	RU min	WU	LU	EcoTox	SC
	<i>kg CFC-11 eq</i>	<i>CTUh</i>	<i>CTUh</i>	<i>Disease incidences</i>	<i>kBq U-235 eq.</i>	<i>mol H+ eq</i>	<i>mol N eq</i>	<i>kg N eq.</i>	<i>kg P eq.</i>	<i>kg N eq</i>	<i>MJ</i>	<i>kg SB eq</i>	<i>m3 water eq</i>	-	<i>CTUe</i>	<i>EUR</i>
REU	2.7E-06	-4.2E-08	-3.7E-07	9.5E-07	1.7E+00	-2.3E-01	-3.9E-01	-1.6E+00	-5.1E-02	-1.1E+00	4.5E+02	7.4E-05	-1.3E+01	-4.7E+04	-4.8E+03	-1.5E+02
REC-PBD	-1.3E-05	8.1E-08	-9.5E-07	-1.1E-05	-7.1E+00	-8.5E-01	-6.5E-01	-2.5E+00	-6.0E-03	-2.3E-01	-1.4E+03	1.0E-04	7.6E+00	-2.3E+05	-1.2E+03	-6.7E+01
LAN	3.28E-06	5.54E-09	1.30E-07	2.50E-06	9.42E-01	1.11E-01	9.14E-02	3.84E-01	8.34E-05	3.49E-02	2.15E+02	3.07E-05	7.42E-01	1.48E+02	1.53E+02	2.9E+01
INC	-5.0E-05	-1.6E-07	-3.3E-06	-1.5E-05	-5.5E+01	-1.4E+00	-3.0E+00	-5.8E+00	-1.4E-02	-4.7E-01	-1.2E+04	-1.2E-03	-1.2E+02	-1.8E+04	-9.3E+03	-1.0E+03

Table A3. Remaining environmental impact categories for steel

Management option	OD	HT can	HT no car	PM	IR	POF	Aci	Eu Ter	Eu Fre	Eu Mar	RU en	RU min	WU	LU	EcoTox	SC
	<i>kg CFC-11 eq</i>	<i>CTUh</i>	<i>CTUh</i>	<i>Disease incidences</i>	<i>kBq U-235 eq.</i>	<i>mol H+ eq</i>	<i>mol N eq</i>	<i>kg N eq.</i>	<i>kg P eq.</i>	<i>kg N eq</i>	<i>MJ</i>	<i>kg SB eq</i>	<i>m3 water eq</i>	-	<i>CTUe</i>	<i>EUR</i>
REU	-8.7E-05	-1.1E-05	-5.1E-05	-1.9E-04	-4.1E+01	-8.4E+00	-8.9E+00	-2.0E+01	-8.9E-02	-1.8E+00	-2.7E+04	-3.4E-02	-4.2E+02	-1.3E+04	-5.8E+04	-9.2E+02
REC-STE	-3.8E-05	-1.8E-06	5.3E-04	-7.0E-05	4.6E+01	-3.8E+00	-2.4E+00	-7.4E+00	-4.0E-02	-6.7E-01	-5.9E+03	-2.0E-02	-8.8E+01	-3.2E+03	-2.8E+04	-2.1E+02
LAN	3.28E-06	5.54E-09	1.30E-07	2.50E-06	9.42E-01	1.11E-01	9.14E-02	3.84E-01	8.34E-05	3.49E-02	2.15E+02	3.07E-05	7.42E-01	1.48E+02	1.53E+02	2.9E+01

Table A4. Remaining environmental impact categories for aluminium

Management option	OD	HT can	HT no car	PM	IR	POF	Aci	Eu Ter	Eu Fre	Eu Mar	RU en	RU min	WU	LU	EcoTox	SC
	<i>kg CFC-11 eq</i>	<i>CTUh</i>	<i>CTUh</i>	<i>Disease incidences</i>	<i>kBq U-235 eq.</i>	<i>mol H+ eq</i>	<i>mol N eq</i>	<i>kg N eq.</i>	<i>kg P eq.</i>	<i>kg N eq</i>	<i>MJ</i>	<i>kg SB eq</i>	<i>m3 water eq</i>	-	<i>CTUe</i>	<i>EUR</i>
REU	-7.5E-04	-2.4E-05	-3.6E-04	-7.5E-04	-5.2E+02	-3.2E+01	-7.1E+01	-9.6E+01	-4.0E-01	-8.6E+00	-1.5E+05	-1.7E-02	-9.5E+03	-2.0E+04	-2.2E+05	-3.3E+03
REC-ALU	-5.3E-04	-1.6E-05	-2.7E-04	-5.3E-04	-1.7E+02	-2.0E+01	-4.9E+01	-6.1E+01	-2.9E-01	-5.6E+00	-8.9E+04	8.2E-03	-6.8E+03	3.4E+04	-1.5E+05	-2.3E+03
LAN	3.28E-06	5.54E-09	1.30E-07	2.50E-06	9.42E-01	1.11E-01	9.14E-02	3.84E-01	8.34E-05	3.49E-02	2.15E+02	3.07E-05	7.42E-01	1.48E+02	1.53E+02	2.9E+01

Table A5. Remaining environmental impact categories for PVC

Management option	OD	HT can	HT no car	PM	IR	POF	Aci	Eu Ter	Eu Fre	Eu Mar	RU en	RU min	WU	LU	EcoTox	SC
	<i>kg CFC-11 eq</i>	<i>CTUh</i>	<i>CTUh</i>	<i>Disease incidences</i>	<i>kBq U-235 eq.</i>	<i>mol H+ eq</i>	<i>mol N eq</i>	<i>kg N eq.</i>	<i>kg P eq.</i>	<i>kg N eq</i>	<i>MJ</i>	<i>kg SB eq</i>	<i>m3 water eq</i>	-	<i>CTUe</i>	<i>EUR</i>
REC-PVC	-6.8E-04	-7.7E-07	-1.8E-05	-5.4E-05	-8.6E+00	-4.1E+00	-6.0E+00	-1.3E+01	-4.8E-02	-1.2E+00	-3.4E+04	-1.7E-02	-3.3E+02	-3.0E+03	-2.7E+04	-6.5E+02
LAN	3.28E-06	5.54E-09	1.30E-07	2.50E-06	9.42E-01	1.11E-01	9.14E-02	3.84E-01	8.34E-05	3.49E-02	2.15E+02	3.07E-05	7.42E-01	1.48E+02	1.53E+02	2.9E+01

INC	-1.3E-04	-3.9E-07	-9.1E-06	-3.9E-05	-1.2E+02	-3.6E+00	-7.2E+00	-1.5E+01	-3.2E-02	-1.2E+00	-2.9E+04	-2.8E-03	-2.7E+02	-4.5E+04	-2.3E+04	-7.9E+02
-----	----------	----------	----------	----------	----------	----------	----------	----------	----------	----------	----------	----------	----------	----------	----------	----------

Table A6. Remaining environmental impact categories for EPS

Management option	OD	HT can	HT no car	PM	IR	POF	Aci	Eu Ter	Eu Fre	Eu Mar	RU en	RU min	WU	LU	EcoTox	SC
	<i>kg CFC-11 eq</i>	<i>CTUh</i>	<i>CTUh</i>	<i>Disease incidences</i>	<i>kBq U-235 eq.</i>	<i>mol H+ eq</i>	<i>mol N eq</i>	<i>kg N eq.</i>	<i>kg P eq.</i>	<i>kg N eq</i>	<i>MJ</i>	<i>kg SB eq</i>	<i>m³ water eq</i>	-	<i>CTUe</i>	<i>EUR</i>
REC-EPS	-4.3E-05	-3.6E-07	-6.7E-06	-7.5E-05	-3.7E+01	-5.4E+00	-8.4E+00	-1.5E+01	-1.1E-02	-1.3E+00	-4.7E+04	-1.0E-03	-1.1E+03	-1.5E+04	-9.0E+03	-8.7E+02
LAN	3.28E-06	5.54E-09	1.30E-07	2.50E-06	9.42E-01	1.11E-01	9.14E-02	3.84E-01	8.34E-05	3.49E-02	2.15E+02	3.07E-05	7.42E-01	1.48E+02	1.53E+02	2.9E+01
INC	-1.4E-04	-4.3E-07	-1.0E-05	-4.1E-05	-1.5E+02	-4.0E+00	-8.3E+00	-1.6E+01	-3.8E-02	-1.3E+00	-3.3E+04	-3.4E-03	-3.3E+02	-4.7E+04	-2.5E+04	-9.4E+02

Table A7. Remaining environmental impact categories for Gypsum

Management option	OD	HT can	HT no car	PM	IR	POF	Aci	Eu Ter	Eu Fre	Eu Mar	RU en	RU min	WU	LU	EcoTox	SC
	<i>kg CFC-11 eq</i>	<i>CTUh</i>	<i>CTUh</i>	<i>Disease incidences</i>	<i>kBq U-235 eq.</i>	<i>mol H+ eq</i>	<i>mol N eq</i>	<i>kg N eq.</i>	<i>kg P eq.</i>	<i>kg N eq</i>	<i>MJ</i>	<i>kg SB eq</i>	<i>m³ water eq</i>	-	<i>CTUe</i>	<i>EUR</i>
REC-GYP	-3.3E-05	-8.5E-08	-3.7E-07	-6.5E-06	-7.7E+00	-3.1E-01	-5.3E-01	-1.6E+00	-6.1E-03	-2.1E-01	-1.6E+03	-8.9E-04	-1.2E+02	-8.8E+03	-4.3E+03	4.8E+01
LAN	3.28E-06	5.54E-09	1.30E-07	2.50E-06	9.42E-01	1.11E-01	9.14E-02	3.84E-01	8.34E-05	3.49E-02	2.15E+02	3.07E-05	7.42E-01	1.48E+02	1.53E+02	2.9E+01

Table A8. Remaining environmental impact categories for ceramic & tiles

Management option	OD	HT can	HT no car	PM	IR	POF	Aci	Eu Ter	Eu Fre	Eu Mar	RU en	RU min	WU	LU	EcoTox	SC
	<i>kg CFC-11 eq</i>	<i>CTUh</i>	<i>CTUh</i>	<i>Disease incidences</i>	<i>kBq U-235 eq.</i>	<i>mol H+ eq</i>	<i>mol N eq</i>	<i>kg N eq.</i>	<i>kg P eq.</i>	<i>kg N eq</i>	<i>MJ</i>	<i>kg SB eq</i>	<i>m³ water eq</i>	-	<i>CTUe</i>	<i>EUR</i>
REU	-4.8E-05	-4.5E-07	-1.4E-05	-1.5E-03	-1.8E+01	-1.6E+00	-2.8E+00	-6.1E+00	-1.8E-02	-5.0E-01	-8.7E+03	-2.0E-02	-2.0E+02	-7.1E+03	-1.6E+04	-3.8E+02
REC-CEM	-6.4E-07	-2.0E-08	-2.1E-06	-1.7E-06	-6.2E-01	-4.9E-01	-5.0E-01	-2.1E+00	-5.1E-03	-1.7E-01	-2.9E+02	-1.6E-04	-3.0E+01	5.7E+01	-2.9E+03	3.2E+01

REC-RA	3.7E-06	4.3E-09	1.4E-07	2.8E-06	1.2E+00	1.3E-01	1.2E-01	4.5E-01	1.4E-04	4.1E-02	2.8E+02	1.9E-05	-4.5E+01	8.9E+01	1.7E+02	7.1E+01
LAN	3.64E-06	6.29E-09	1.44E-07	2.95E-06	1.18E+00	1.35E-01	1.13E-01	4.71E-01	1.22E-04	4.29E-02	2.58E+02	3.51E-05	1.15E+00	1.61E+02	1.76E+02	3.7E+01

Table A9. Remaining environmental impact categories for glass wool

Management option	OD	HT can	HT no car	PM	IR	POF	Aci	Eu Ter	Eu Fre	Eu Mar	RU en	RU min	WU	LU	EcoTox	SC
	<i>kg CFC-11 eq</i>	<i>CTUh</i>	<i>CTUh</i>	<i>Disease incidences</i>	<i>kBq U-235 eq</i>	<i>mol H+ eq</i>	<i>mol N eq</i>	<i>kg N eq.</i>	<i>kg P eq.</i>	<i>kg N eq</i>	<i>MJ</i>	<i>kg SB eq</i>	<i>m³ water eq</i>	-	<i>CTUe</i>	<i>EUR</i>
REC-GLW	3.6E-06	6.1E-09	1.5E-07	1.9E-06	1.3E+00	6.3E-02	5.6E-02	1.4E-01	1.5E-04	1.8E-02	2.7E+02	4.1E-05	6.0E-01	1.5E+02	-1.9E+03	7.1E+01
LAN	3.28E-06	5.54E-09	1.30E-07	2.50E-06	9.42E-01	1.11E-01	9.14E-02	3.84E-01	8.34E-05	3.49E-02	2.15E+02	3.07E-05	7.42E-01	1.48E+02	1.53E+02	2.9E+01

Table A10. Remaining environmental impact categories for stone wool

Management option	OD	HT can	HT no car	PM	IR	POF	Aci	Eu Ter	Eu Fre	Eu Mar	RU en	RU min	WU	LU	EcoTox	SC
	<i>kg CFC-11 eq</i>	<i>CTUh</i>	<i>CTUh</i>	<i>Disease incidences</i>	<i>kBq U-235 eq</i>	<i>mol H+ eq</i>	<i>mol N eq</i>	<i>kg N eq.</i>	<i>kg P eq.</i>	<i>kg N eq</i>	<i>MJ</i>	<i>kg SB eq</i>	<i>m³ water eq</i>	-	<i>CTUe</i>	<i>EUR</i>
REC-STW	3.5E-06	3.4E-09	1.5E-07	2.1E-06	1.0E+00	9.2E-02	8.5E-02	3.1E-01	1.1E-04	2.8E-02	2.6E+02	1.7E-05	-5.4E+01	8.8E+01	1.6E+02	7.3E+01
LAN	3.28E-06	5.54E-09	1.30E-07	2.50E-06	9.42E-01	1.11E-01	9.14E-02	3.84E-01	8.34E-05	3.49E-02	2.15E+02	3.07E-05	7.42E-01	1.48E+02	1.53E+02	2.9E+01

Table A11. Remaining environmental impact categories for bricks

Management option	OD	HT can	HT no car	PM	IR	POF	Aci	Eu Ter	Eu Fre	Eu Mar	RU en	RU min	WU	LU	EcoTox	SC
	<i>kg CFC-11 eq</i>	<i>CTUh</i>	<i>CTUh</i>	<i>Disease incidences</i>	<i>kBq U-235 eq</i>	<i>mol H+ eq</i>	<i>mol N eq</i>	<i>kg N eq.</i>	<i>kg P eq.</i>	<i>kg N eq</i>	<i>MJ</i>	<i>kg SB eq</i>	<i>m³ water eq</i>	-	<i>CTUe</i>	<i>EUR</i>
REU	-1.8E-05	-2.5E-07	-1.5E-06	-8.4E-06	-4.5E+00	-6.2E-01	-6.4E-01	-2.0E+00	-2.5E-03	-1.8E-01	-2.2E+03	-1.1E-03	-3.4E+01	-1.1E+03	-1.9E+03	-3.7E+02
REC-CEM	-1.4E-06	-2.4E-08	-2.4E-06	-2.3E-06	-1.6E+00	-5.6E-01	-5.9E-01	-2.4E+00	-5.7E-03	-2.0E-01	-4.7E+02	-2.0E-04	-3.5E+01	-1.3E+01	-3.3E+03	2.1E+01

REC-CON	-1.5E-05	-2.1E-07	-1.1E-06	-7.1E-06	-6.1E-01	-5.0E-01	-4.4E-01	-1.6E+00	-1.5E-03	-1.4E-01	-1.4E+03	-8.4E-04	-4.9E+00	-6.9E+02	-1.4E+03	5.7E+01
REC-RA	3.4E-06	4.5E-09	1.5E-07	2.3E-06	1.9E+00	1.2E-01	1.3E-01	4.0E-01	3.0E-04	3.7E-02	3.7E+02	3.6E-05	-4.3E+01	1.4E+02	2.1E+02	7.5E+01
LAN	3.28E-06	5.54E-09	1.30E-07	2.50E-06	9.42E-01	1.11E-01	9.14E-02	3.84E-01	8.34E-05	3.49E-02	2.15E+02	3.07E-05	7.42E-01	1.48E+02	1.53E+02	2.9E+01

Table A12. Remaining environmental impact categories for glass

Management option	OD	HT can	HT no car	PM	IR	POF	Aci	Eu Ter	Eu Fre	Eu Mar	RU en	RU min	WU	LU	EcoTox	SC
	<i>kg CFC-11 eq</i>	<i>CTUh</i>	<i>CTUh</i>	<i>Disease incidences</i>	<i>kBq U-235 eq.</i>	<i>mol H+ eq</i>	<i>mol N eq</i>	<i>kg N eq.</i>	<i>kg P eq.</i>	<i>kg N eq</i>	<i>MJ</i>	<i>kg SB eq</i>	<i>m3 water eq</i>	-	<i>CTUe</i>	<i>EUR</i>
REU	-1.4E-04	-3.5E-07	-8.1E-06	-1.3E-04	-4.3E+01	-5.8E+00	-1.2E+01	-2.4E+01	-2.4E-02	-2.0E+00	-1.5E+04	-1.6E-02	-3.2E+02	-9.9E+03	-2.6E+04	-5.8E+02
REC-GLA	-1.02E-04	1.55E-07	2.07E-05	-9.23E-06	-2.50E+01	-1.6E+00	-3.9E+00	-8.4E+00	-1.06E-02	-5.41E-01	-8.1E+03	-1.21E-02	-1.9E+02	-7.4E+03	-1.8E+04	1.2E+01
REC-RA	4.2E-06	5.6E-09	1.8E-07	2.9E-06	1.9E+00	1.4E-01	1.4E-01	4.7E-01	2.9E-04	4.3E-02	4.0E+02	4.0E-05	-4.6E+01	1.5E+02	2.4E+02	7.6E+01
LAN	3.28E-06	5.54E-09	1.30E-07	2.50E-06	9.42E-01	1.11E-01	9.14E-02	3.84E-01	8.34E-05	3.49E-02	2.15E+02	3.07E-05	7.42E-01	1.48E+02	1.53E+02	2.9E+01

Table A13. Remaining environmental impact categories for excavated soils

Management option	OD	HT can	HT no car	PM	IR	POF	Aci	Eu Ter	Eu Fre	Eu Mar	RU en	RU min	WU	LU	EcoTox	SC
	<i>kg CFC-11 eq</i>	<i>CTUh</i>	<i>CTUh</i>	<i>Disease incidences</i>	<i>kBq U-235 eq.</i>	<i>mol H+ eq</i>	<i>mol N eq</i>	<i>kg N eq.</i>	<i>kg P eq.</i>	<i>kg N eq</i>	<i>MJ</i>	<i>kg SB eq</i>	<i>m3 water eq</i>	-	<i>CTUe</i>	<i>EUR</i>
REU-RCB	-1.2E-07	-9.7E-11	1.3E-09	-2.4E-07	-3.9E-01	1.0E-02	1.0E-02	5.0E-02	1.6E-05	4.7E-03	-2.5E+01	-2.1E-05	-3.9E+01	1.0E+01	1.0E+01	3.7E-01
REC-LIM	1.5E-06	-2.6E-08	-3.6E-07	-3.3E-06	-6.2E+00	-1.6E-01	-2.2E-01	-7.8E-01	-2.0E-02	-7.0E-02	-4.4E+02	-5.2E-04	-1.0E+02	3.9E+02	-7.4E+02	-5.2E+00
REC-CEM	4.0E-08	1.3E-08	5.0E-07	5.6E-07	2.9E+00	9.0E-02	1.3E-01	3.8E-01	1.0E-02	3.0E-02	2.6E+02	-2.2E-04	6.5E+02	-1.8E+02	3.9E+02	5.6E+00
REC-IND	-7.0E-07	-1.8E-08	-1.0E-07	-9.5E-07	3.4E+00	-1.0E-02	2.0E-02	-5.0E-02	6.2E-04	-2.6E-03	8.2E+01	-2.6E-04	-1.6E+01	1.1E+01	-6.5E+01	3.0E-01

LAN	3.3E-07	4.2E-09	4.5E-08	1.4E-07	2.4E-01	6.0E-02	6.0E-02	2.5E-01	7.0E-04	2.0E-02	0.0E+00	0.0E+00	7.6E+00	3.8E+02	1.0E+02	1.7E+00
-----	---------	---------	---------	---------	---------	---------	---------	---------	---------	---------	---------	---------	---------	---------	---------	---------

Table A14. Remaining environmental impact categories for dredging spoils

Management option	OD	HT can	HT no car	PM	IR	POF	Aci	Eu Ter	Eu Fre	Eu Mar	RU en	RU min	WU	LU	EcoTox	SC
	<i>kg CFC-11 eq</i>	<i>CTUh</i>	<i>CTUh</i>	<i>Disease incidences</i>	<i>kBq U-235 eq.</i>	<i>mol H+ eq</i>	<i>mol N eq</i>	<i>kg N eq.</i>	<i>kg P eq.</i>	<i>kg N eq</i>	<i>MJ</i>	<i>kg SB eq</i>	<i>m3 water eq</i>	-	<i>CTUe</i>	<i>EUR</i>
REU	3.1E-07	-2.2E-10	5.2E-09	3.3E-07	-3.5E-01	3.0E-02	2.0E-02	1.0E-01	-3.9E-05	1.0E-02	1.5E+00	-2.3E-05	-4.5E+01	1.7E+00	1.6E+01	7.0E-01
REC-RCB	1.1E-06	8.6E-09	1.4E-07	1.4E-06	1.0E+00	8.0E-02	1.5E-01	4.8E-01	4.2E-03	8.0E-02	4.9E+02	1.5E-04	-3.5E+01	8.2E+01	5.1E+02	3.7E+00
REC-CEM	-1.7E-06	9.6E-09	-3.6E-07	-3.4E-07	-5.6E+00	-1.3E-01	-1.1E-01	-4.2E-01	-1.0E-02	-3.0E-03	1.3E+01	2.6E-04	-9.3E+01	-4.0E+02	-2.5E+02	-7.0E+00
REC-IND	4.1E-07	-1.5E-08	3.1E-09	5.5E-07	6.0E+00	6.0E-02	1.6E-01	3.7E-01	4.9E-03	7.0E-02	6.4E+02	-1.6E-04	6.7E+00	8.9E+01	4.1E+02	3.7E+00
LAN	1.6E-06	1.3E-08	1.9E-07	1.8E-06	1.7E+00	1.4E-01	2.0E-01	7.0E-01	4.9E-03	1.0E-01	5.2E+02	1.8E-04	1.8E+01	4.6E+02	6.1E+02	5.1E+00

Annex 2. Sensitivity results for wood fraction including the cascading use and greener energy use

Table A15. Data and results of the sensitivity analysis for wood fraction including four life cycles in the cascading use with current energy mix (2020).

Cascading calculation - Current energy mix						
Particleboard/waste input			0.59	0.56	0.54	
		1 st life	2 nd life	3 rd life	4 th life	
Recycling	kg	1000	592	332	180	
Incineration	kg	1000	592	332	180	

		1 st life	2 nd life	3 rd life	4 th life	Total 2 cycles	Total 4 cycles
Reuse	kg CO ₂ -eq.	-52	-52	-52	-52	-103	-206
Recycling	kg CO ₂ -eq.	-69	-41	-23	-12	-110	-145
Incineration	kg CO ₂ -eq.	-265	-157	-149	-144	-423	-716
Production	kg CO ₂ -eq.		374	210	114	374	697
Incineration + Production	kg CO ₂ -eq.					-49	-18

Virgin Production impact	kg CO ₂ -eq./t particleboard	631
--------------------------	---	-----

Source: Own elaboration

Table A16. Data and results of the sensitivity analysis for wood fraction including four life cycles in the cascading use with future energy mix (2050).


Cascading calculation - Future energy mix						
Particleboard/waste input			0.59	0.56	0.54	
		1 st life	2 nd life	3 rd life	4 th life	
Recycling	kg	1000	592	332	180	
Incineration	kg	1000	592	332	180	

		1 st life	2 nd life	3 rd life	4 th life	Total 2 cycles	Total 4 cycles
Reuse	kg CO ₂ -eq.	-52	-52	-52	-52	-103	-206
Recycling	kg CO ₂ -eq.	-69	-41	-23	-12	-110	-145
Incineration	kg CO ₂ -eq.	-100	-59	-33	-18	-159	-211
Production	kg CO ₂ -eq.		374	210	114	374	697
Incineration + Production	kg CO ₂ -eq.	-100	315	176	96	215	487

Virgin Production impact	kg CO ₂ -eq./t particleboard	631
--------------------------	---	-----

Source: Own elaboration

Figure A1. Characterised climate change results per tonne of CDW fraction managed with breakdown of the contributions in 2050. Values above zero represent burdens, while values below zero represent savings. The final net impact, per each individual category, is the sum of burdens and savings and is represented with a black dot. The error bars represent the standard deviation around the net result. For the abbreviations used please refer to Table 11.

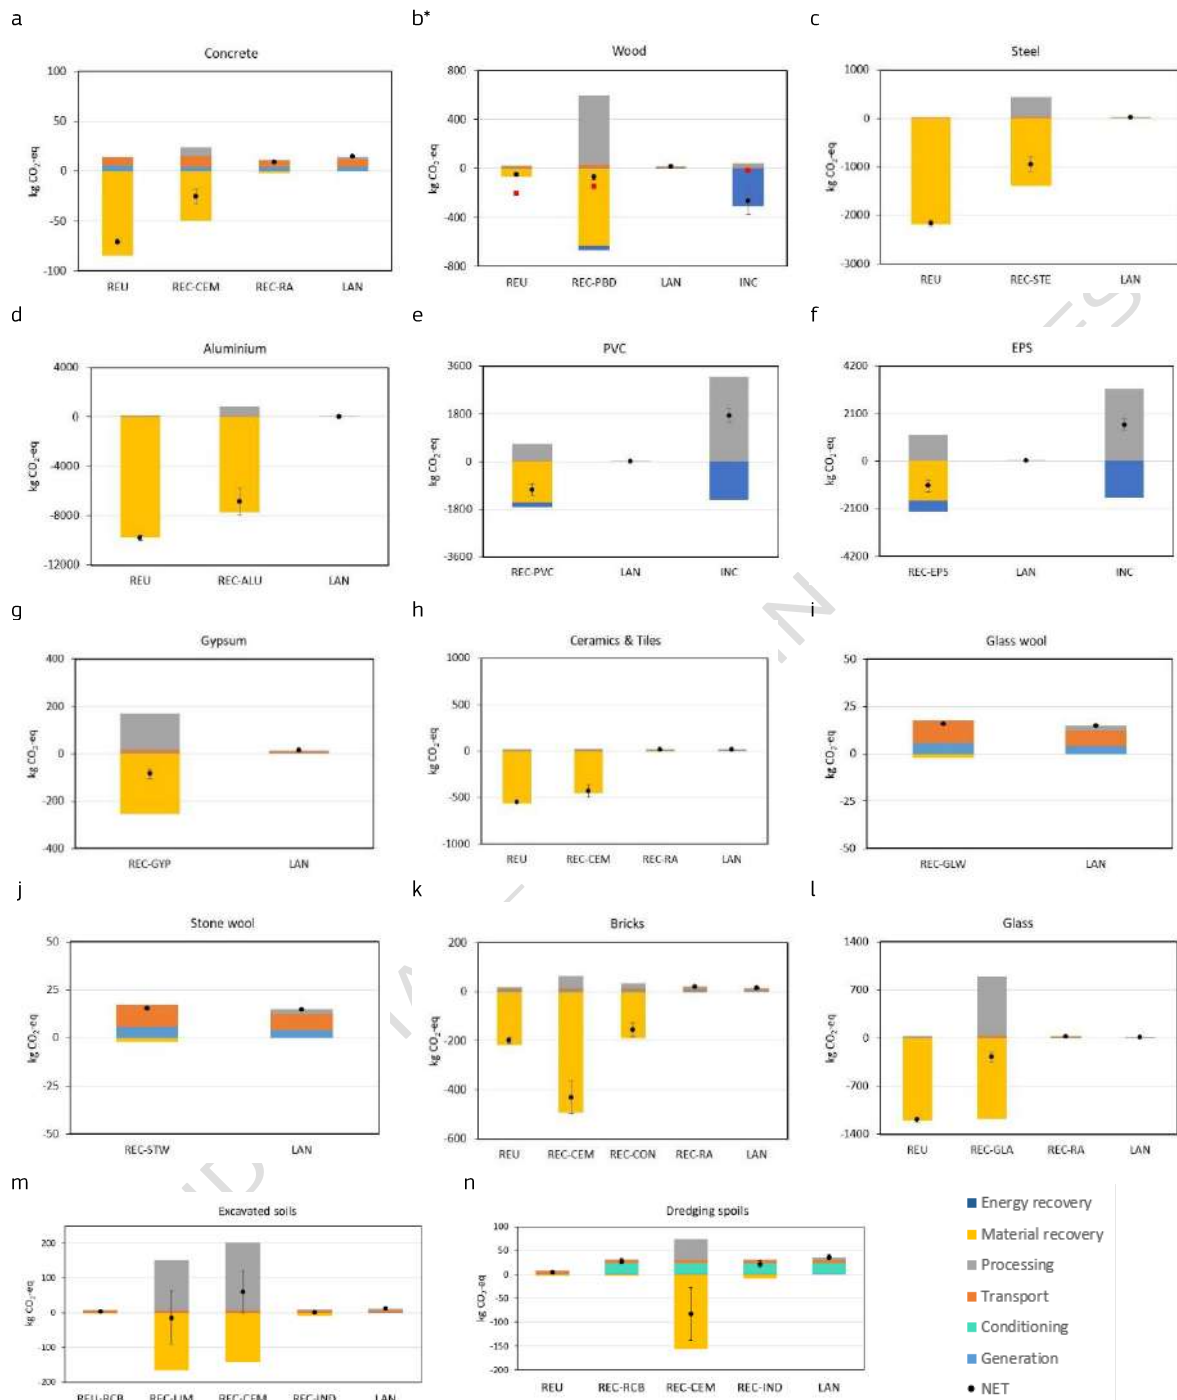

Source: Own elaboration

GETTING IN TOUCH WITH THE EU

In person

All over the European Union there are hundreds of Europe Direct centres. You can find the address of the centre nearest you online (european-union.europa.eu/contact-eu/meet-us_en).

On the phone or in writing

Europe Direct is a service that answers your questions about the European Union. You can contact this service:

- by freephone: 00 800 6 7 8 9 10 11 (certain operators may charge for these calls),
- at the following standard number: +32 22999696,
- via the following form: european-union.europa.eu/contact-eu/write-us_en.

FINDING INFORMATION ABOUT THE EU

Online

Information about the European Union in all the official languages of the EU is available on the Europa website (european-union.europa.eu).

EU publications

You can view or order EU publications at op.europa.eu/en/publications. Multiple copies of free publications can be obtained by contacting Europe Direct or your local documentation centre (european-union.europa.eu/contact-eu/meet-us_en).

EU law and related documents

For access to legal information from the EU, including all EU law since 1951 in all the official language versions, go to EUR-Lex (eur-lex.europa.eu).

Open data from the EU

The portal data.europa.eu provides access to open datasets from the EU institutions, bodies and agencies. These can be downloaded and reused for free, for both commercial and non-commercial purposes. The portal also provides access to a wealth of datasets from European countries.

